MD-3-A 36

# PACKAGE TICKET

CODE RT695 LOT K2J51

| P.O | NET WT/PKG. | NO. PKG. | PACK WT. | LOCATION |
|---|---|---|---|---|
| | | 27 | 2621 | 32 |
| | | | | |
| | | | | |
| | | | | |
| | | | | |
| | | | | |

**STUMP**

TOTAL NET WT. 2621

LUMP WT. 2653 PKG. N-CODE

PROD. SUPV. RH DATE 11/11 OPERATOR 292

C

0·98 +
1·11 +
0·95 +
1·01 +
0·93 +
0·91 +
1·03 +
0·95 +
0·79 +
0·91 +
0·89 +
0·93 +
1·05 +
0·97 +
1·08 +
1·09 +
1·16 +
0·92 +
1·05 +
1·10 +
1·08 +
1·06 +
0·76 +
0·93 +
0·81 +
1·01 +
0·75 +

027

26·21 ↓

DUP050101921

PRODUCT NAME = "BON" RED DARK NON-BLEEDING

CG 36 CODE RT-695-D PKG ____

LOT K2551 FIRED @ 5:10 pm ON 10/21/82

EST. WT. 2608* LBS.

36/107

PROCESSES APPROVED BY
RT-695-D (O) EWK 12/7/81

TYPED BY KLW

MAKING NOTES SPLIT-OFF 1 DRUM 70# TO LOT H2S07 FIRED While GRINDING

JOB NAME 36RT695DPN

= PRESSING =

INSTRUCTIONS

| | | | | | |
|---|---|---|---|---|---|
| VAT | 107 | | | | |
| DATE | 10-7-82 | | | | |
| TIME | 12:10 pm | | | | |
| RELEASED BY | | | | | |
| PRESS | 32 | 33 | 35 | 36 | 39 |
| NO. OF CAKES | 60 | 60 | 60 | 60 | 60 |

PRESS WITHOUT AGITATION
WASH TO 250 M MHOS WITH 35-75F WATER
TEST AFTER 16 HOURS
LOAD ON 12 CARS

SAMPLES JAR
DELIVER TO CTL FOR COLOR

RECORD

| PRESSLOAD | 1ST | 2ND | 3RD | 4TH | 5TH |
|---|---|---|---|---|---|
| STARTED | 5 15 AM | | | | |
| CAKES USED | 60 | | | | |
| WATER ON | 1 PM | | | | |
| HRS. WASHED | 15½ | | | | |
| M MHOS | | | | | |
| HRS. WASHED | 122 | | | | |
| M MHOS | | | | | |
| HRS. WASHED | | | | | |
| M MHOS | | | | | |
| CAKE CONDITION | | | | | |
| NO CARS LOADED | 10 | | | | |

EXPLAIN LOSSES 2

SAMPLED BY
RELEASED BY

= DRYING =

DRY 24 HOURS AT 180*F

MN COLOR

SAMPLES
DELIVER TO

LUMP: — OK — WET — SALTS — CONTAMINATD

ADDITIONAL DRYING HOURS REQUIRED

NO DRUMS 15
LUMP WGT 2653

NO CARS PULLED
SAMPLED BY
RELEASED BY A.K

= GRINDING =

MILL 5 HSP 1/8"RP SCREEN 3500 RPM
MAX. TEMP. 140 F
MN COLOR
IF FOLLOWING RT-531-D/RT-539-D CLEAN MILL THOROUGHLY; CHANGE BAG & HOSE DOWN EXHAUST SYSTEM. NAPHTHANIL CAUSES BAD TOLUOL BLEED.
INERT MILL WITH CO2 WHEN GRINDING PER O.P.# O.F. 0043
SAMPLE WITHOUT MIXING
SAMPLES: ENVELOPE & 2 PINT CANS
DELIVER TO CTL

SCREEN RPM
MAX. TEMP. F

EXPLAIN LOSSES

DATE MIXED

SAMPLED BY
RELEASED BY

DUP050101922

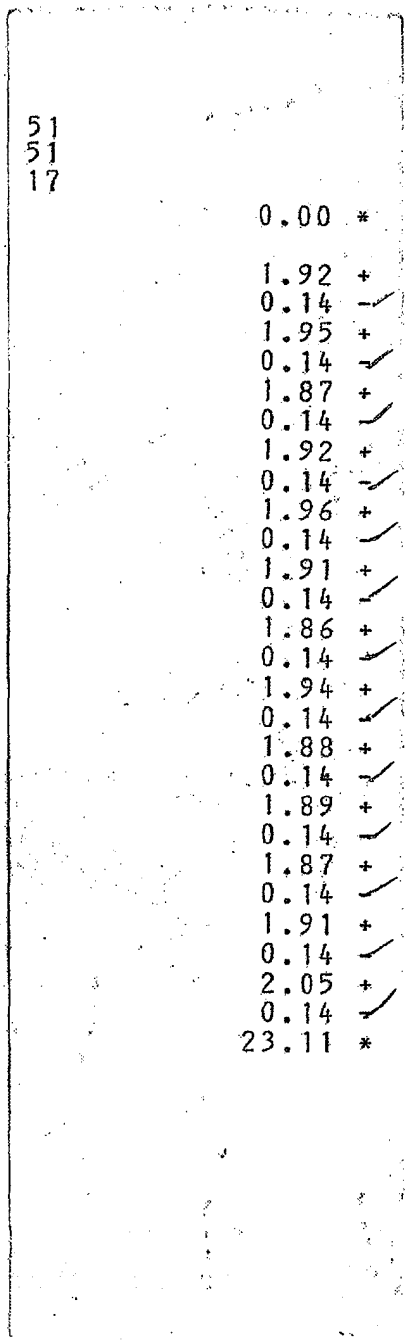


DUP050101923

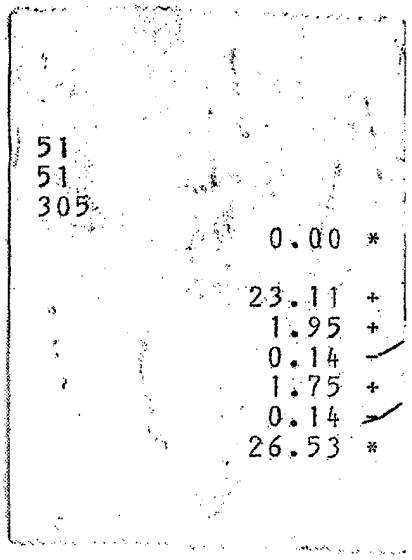
51
51
305
0.00 *
23.11 +
1.95 +
0.14 -
1.75 +
0.14 -
26.53 *