

Vista Polymers
A Division of
Vista Chemical Company

Highway 25
Post Office Box 91

Aberdeen, Mississippi 39730-0091
Phone (601) 369-8111

A

CERTIFICATE OF ANALYSIS

Fax No. 215-997-8998

Date: September 8, 1992

Customer: Penn Color
2755 Bergey Road
Hatfield, PA 19440

Product: 5265

VISTA

Attention: Howard Demonty

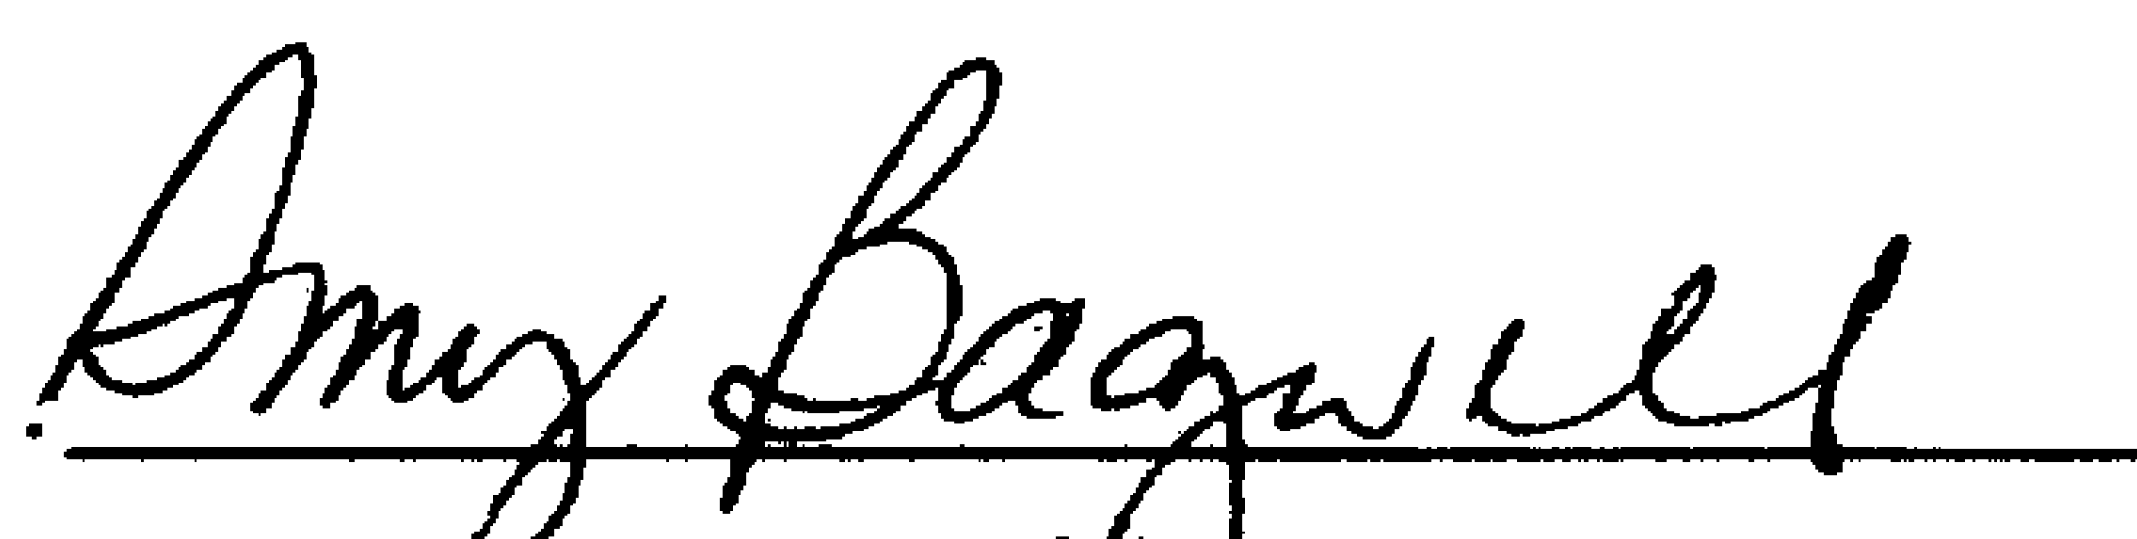
Lot No.: 05026

Ship Date: September 8, 1992

Order No.: 0015805-000

<u>Property</u>	<u>Test Method</u>	<u>Analysis</u>
Moisture, %	ABR-1A	0.16
Bulk Density, gm/cc	ABR-2A	0.546
Contamination, BLK/BRN	ABR-5A	7 / 2
Particle Size Dist.	ABR-3 <u>40 mesh</u> 0.0	<u>200 mesh</u> 19.2 <u>Pan</u> 3.2
Residual VCM, ppm	ABGC-26	0.035
Inherent Viscosity	ABR-10	0.66

Polyvinyl Chloride, Virgin Resin, Not Reprocessed.


Amy E. Bagwell
Laboratory Supervisor

(601) 369-3624

VAB.0001202377

RESIN BAG BLEND

BLEND NO: 05026 PRODUCT: 5265 DATE: 9/4/92 TIME/TESTED BY: 2200 40/MS

Avg. Microns, 5225/5325/5415:

SKID NO.	% MOIST	BLACK/ BROWN CONT.	PARTICLE SIZE DISTRIBUTION							BULK DENS H/P	S/7 MIN. H/P	DRY TIME	C O L O R			% GLASSY	VISC.	RVCM
			40	60	80	100	120	140	200	PAN			L	A	B			
CON- POSITE RESULTS	COMPOSITE OF 1, 13, 14		0.00	0.03	1.91	16.82	4.42	15.60	9.58	1.60								
			0.0	0.1	3.8	13.6	28.9	31.2	19.2	3.2	50	8ms	18.5	99.5	10.3	41.6	9	.035
SKID #1	.14	3/2															.658	
SKID #4	.10	7/2																
SKID #7	.09	5/3																
SKID #10	.11	2/1																
SKID #13	.16	4/4															.664	
SKID #16	.09	5/3																
SKID #19	.08	2/2																
SKID #22																		
SKID #25																		
SKID #28																		
SKID #31																		
SKID #34																		
SKID #37																		