

THE STORY *of* WHITE-LEAD

A DESCRIPTION OF THE PROCESS
BY WHICH LEAD ORE IS PREPARED
FOR PAINT, BY THE MANUFACTURERS
OF DUTCH BOY PRODUCTS

NATIONAL LEAD COMPANY

NEW YORK BOSTON BUFFALO CHICAGO
CINCINNATI CLEVELAND ST. LOUIS SAN FRANCISCO

John T. Lewis & Bros. Co., Philadelphia
(National Lead & Oil Co., Pittsburgh.)



The Story of White-Lead

The illustrations show the primitive manufacturing processes in their proper order. The position of the picture on the page also shows how the operation progresses from that in the factory. For example, on page 1, the picture at the bottom illustrates operations on the ground floor, pure to show them on the third or top floor.

LEAD is one of the metals which apparently have been known to man from the earliest days. It is mentioned in the Bible and other ancient writings.

Not suitable for money or jewelry, and therefore never classed as one of the so-called precious metals, lead has certain characteristics which make it invaluable in many of the modern arts and industries.

Uses of Metal Lead

Metal lead is used chiefly for the better grades of plumbing, for roofs, for lining vats and rooms exposed

to acids, for making bearing metal rollers, such weights, shot and lead balls, lead comes (the strips separating the panes in art glass windows), and for various other purposes where a soft, heavy, durable metal is required.

The chemical derivatives of lead are quite as important as the metal itself. Such beautiful paint pigments as chrome yellow and American vermilion are secured by chemically combining chromic acid with lead. The brilliant orange pigment seen so frequently on steel bridges and the skeletons of skyscrapers is lead oxide (red lead). Fine cut glass is 40 per cent or

more lead. The glaze on fine china and pottery is lead. Finally, passing by many other uses of this remarkable metal, there remains white-lead, the most important derivative of all.


White-lead is used in numerous ways, but its wildest use by far is as paint. It needs only to be mixed with linseed oil and it becomes a perfect white paint—a fact which does not hold true of any other known substance. The addition of tinting material gives any desirable color.

We speak of white-lead as a pigment. All paints, properly so-called, are mixtures of solid particles or pigment and a liquid or vehicle.

White-lead is nature's true paint pigment because when mixed with linseed oil (the only liquid that satisfactorily answers the purpose

of a vehicle) it yields a perfect paint.

As a paint pigment, white-lead has been used since the Christian era. The Romans called it "ceruse." From descriptions of its manufacture found in ancient writings, and from the fact that the white-lead of the



Romans contained acetate of lead, we know that the old-time method of manufacture was not different in principle from that of to-day. Progress has been in the direction of higher purity, greater fineness, and safer working conditions.


The Dutch are credited with being the originators of the process by which most white-lead is made—the Old Dutch Process. Investigations are that the Dutch, through intimate trade relations, obtained this process from the Venetians, who, with the Genoese, dominated

the seas during part of the 15th and 16th centuries, and whose trade was every part of the world.

The Chemistry of It

White-lead is a white powder known as lead carbonate. It is a chemical compound and when carefully mixed with linseed oil, about 100 parts of carbonate of lead and 1 part of linseed oil, it is a perfect body of lead.


The chemical name for white-lead is $PbCO_3$, which means that two molecules of lead (Pb) combine with one molecule of carbon dioxide (CO_2) to form a molecule of lead carbonate. Explaining still more fully the chemical composition, the formula that there are in a molecule of lead the following, carbon (C), which stand for the name, platinum (Pt), about 100 (100), and Hydrogen (H).

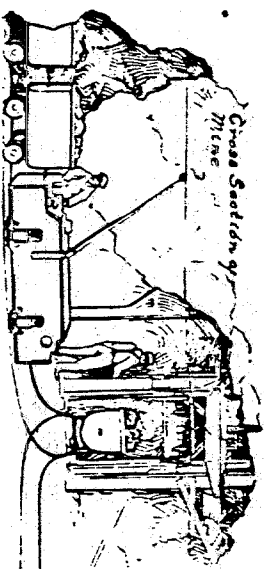

the sea during part of the middle ages and whose trade reached to every part of the world then known.


The Chemistry of White-Lead

White-lead is a white, exceedingly fine powder known as basic lead carbonate. It is a chemical compound analyzing, when carefully manufactured, about 69 per cent carbonate of lead and 31 per cent hydrate of lead. The chemical symbol for white-lead is $2PbCO_3 \cdot Pb(OH)_2$, which means that two molecules of lead carbonate ($PbCO_3$) and one molecule of lead hydrate ($Pb(OH)_2$) combine to produce a molecule of basic lead carbonate. Explaining still further the chemical composition, the formula shows that there are in a molecule of white-lead the following elements: Lead (Pb), which stands for the Latin name, plumbum; Carbon (C), Oxygen (O), and Hydrogen (H).



A Long Road to Travel

It sounds simple and easy enough to say that white-lead is made by subjecting lead, such as that seen in a piece of lead pipe or the nose of a cartridge, to the fumes of acetic acid (vinegar), in the presence of a carbonic acid gas, then, thoroughly pulverizing by grinding, washing, and sifting, and finally mixing into a thick paste with a little linseed oil. The actual process, however, is far from simple and is most interesting. Not only must the lead first be mined and refined, but when it starts in its point form on the side of a house, it has a long road to travel, with many bumps and turns. Lead exists in nature as an ore, generally in combination with sulphur as lead sulphide or galena, which is usually associated with other minerals.



Some ore-bearing rock is found near the surface, but most of it is found at a depth of five to six hundred feet. It has to be blasted loose.



After mining, the ore-bearing rock goes to crushers of various sizes which gradually break it into smaller and smaller pieces. The biggest crushers are powerful enough to take into their huge jaws chunks of rock measuring as much as four or five feet each way and chew them up into small bits. From the smallest crusher, the rock which is now as fine as coarse sand is conveyed in water to "concentrating" tables. Here the lead ore is separated from the associated earth and other waste or "gangue." The table is on a slant and the separation is accomplished by a jerking back and forth which causes the heavy pieces of rock containing lead to go one way and the lighter waste to go the other way. Thus partially cleaned, the lead ore, or "concentrate," as it is now called, goes to the smelter, where it is carefully roasted and smelted

in blast furnaces. This treatment drives off the sulphur, and crude lead is obtained.

The crude lead is refined to remove the copper, silver, and other impurities. For even silver, though a precious metal, is here an undesirable citizen and must be expelled. This is done by a curious process, depending partly upon an attraction which silver has for zinc. Pieces of zinc thrown into the molten lead quickly melt, and by stirring the liquid mass the silver and zinc particles soon become attached to each other. When the stirring stops, the zinc and silver compound, being lighter than lead, soon floats to the top, where it is easily skimmed off and poured into the bottom molds seen on the edge of the big kettle. Now this bullion is later heated to such a degree that the zinc is volatilized leaving the silver free is another story.

From Pigs to Paint



The refining done, the lead is siphoned into mounds, set in the

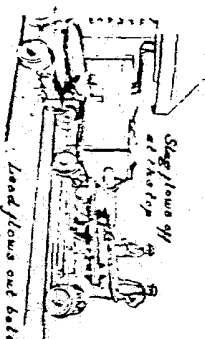

Some ore-bearing rock is found near the surface, but most of it is found at a depth of five to six hundred feet. It has to be blasted loose.


After mining, the ore-bearing rock goes to crushers of various sizes which gradually break it into smaller and smaller pieces. The biggest crushers are powerful enough to take into their huge jaws chunks of rock measuring as much as four or five feet each way and chew them up into small bits.

From the smallest crusher, the rock which is now as fine as coarse sand is conveyed in water to "concentrating" tables. Here the lead ore is separated from the associated earth and other waste or "gangue". The table is on a slant and the separation is accomplished by a jerking back and forth which causes the heavy pieces of rock containing lead to go one way and the lighter waste to go the other way. Thus partially cleaned, the lead ore, or "concentrates" as it is now called, goes to the smelter, where it is carefully roasted and smelted in blast furnaces. This treatment drives off the sulphur, and crude lead is obtained.

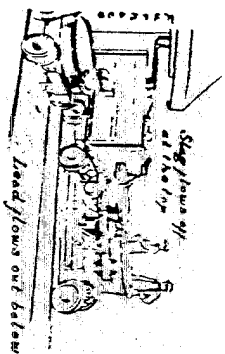

The crude lead is refined to remove the copper, silver, and other impurities. For even silver, though a precious metal, is here an undesirable citizen and must be got rid of. This is done by a curious process, depending partly upon an attraction which silver has for zinc. Pieces of zinc thrown into the molten lead quickly melt, and by stirring the liquid mass, the silver and zinc particles soon become attached to each other. When the stirring stops, the zinc and silver easily skinned off and poured into the bullion molds seen on the edge of the big kettle. How this bullion is later heated to such a degree that the zinc is volatilized leaving the silver free is another story.

From Pigs to Pans
The refining done, the lead is allowed into months, set in the rim of a huge horizontal wheel, which cast it into lead pigs. A lead pig measures about four inches by five inches by twenty-two inches and weighs about ninety pounds.

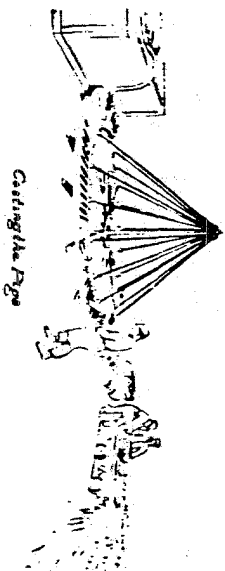

In the form of pigs, the metal goes to the white-lead factory. The first operation there is melting the pigs and reasting the lead into metal discs which are called "buckles," because of their fan-like resemblance to the shoe buckles of Colonial times. These discs are about five inches in diameter and one-fourth of an inch thick with perforated centers.

The pressing is done in molds which are linked together into an endless chain or belt that travels on two pulleys. Near one of the pulleys the chain moves along under the support of a kettle from which the molten lead runs just fast enough to fill each buckle mold as it passes. By the time each mold in its turn reaches the pulley on the other end, the lead has hardened, and as the chain makes the turn the buckle, knocked loose by an automatic hammer, drops into a little cart.

In this cart, which is suspended from a monorail track, the buckles are carried to the stack house or correlling shed. Here workmen place them in earthenware correlling pots.

A correlling pot is somewhat like a flower-pot, but so shaped that the buckles, which are piled but rest upon a shoulder some two inches from the base of the pot, from ten to fourteen buckles are put in each pot and in its top the bottom is poured about one half pint of weak acetic acid (usually vinegar).

Laying the Stack
The stack house gets its name from the fact that white lead is correllled in stacks. Each stack consists of alternate layers of discs of spent tankard oak bark that has been used in tanning, and about twenty inches thick and filled correlling pots, each layer separated from the one above by a

summer, drops into a
tr, which is suspended
over track, the buckets
to the stack house or
shed. Here workmen
in earthenware corrod-

ing pot is somewhat
pot, just so shaped that
which are piled flat,
a shoulder some two
the base of the pot,
a fourteen buckets are
pot and in its cup-like
poured about one-half
ak acetic acid (prac-

ing the Stack


a house gets its name
act that white lead is
stacks. Each stack
alternate layers of
ot tankard (oak bark
ren used in tanneries)
ny inches thick and
ding pots, each layer
on the one above by a



floor of loose boards. An ordinary
stack will measure twenty-two
feet long, twenty feet wide, and
thirty feet high.

What Happens in the Stack

The first thing to happen in this
huge pile of lead buckets, shredded
bark, and acetic acid is the slow
decomposition of the bark. It
ferments and creates a heat strong
enough to warm the acetic acid
until vapor is given off. Slowly
the fumes steam up thru the per-
forations in the buckets, which
gradually turn white with a coat-
ing of lead acetate. At the same
time the fermenting tankard is
generating carbonic acid gas (car-
bon dioxide). As fast as the
acetic acid fumes turn the metal
lead to lead acetate, the carbon
dioxide turns the lead acetate to
basic lead carbonate. This two-
change process begins on all ex-
posed portions of the metal bucket
and progresses continuously in-
ward until the conversion into
basic lead carbonate is practically
complete.

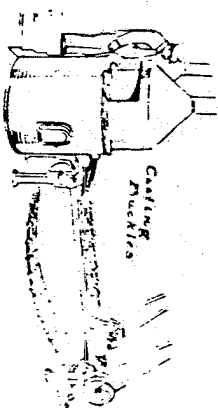

The heat in the stack reaches a
temperature of 125 degrees Fahren-
heit. If an egg is set down into
one of the small wooden ventilat-
ing flues, which are left here and
there when the stack is built, it is
readily cooked.

The process of corrosion usually
takes from ninety to one hundred
and thirty days. By that time
probably eighty per cent of the
metal has become lead carbonate.
The stacks are then torn down as
the workmen say, they are "thawed"
or "stripped." The acetic acid
has evaporated, the lead buckets are
found in their original shape, only
so brittle that they may be crum-
bled in the fingers. But instead
of being bluish gray they are now
snow white; for it is the nature of
lead to turn white when it corrodes,
just as iron turns red and copper
turns green when they corrode.

Safety First

The contents of the corroding
pots are emptied into large covered
boxes to which is attached a pipe
with an in-draft to absorb all dust




...when I make it possible in many of the modern arts and industries.


Uses of Metal Lead

Metal lead is used chiefly for the better grades of paint, for roofs, for lining vaults and rooms exposed

to air. Such beautiful paint pigments as chrome yellow and American vermilion are secured by chemically combining chromic acid with lead. The brilliantly orange pigment seen so frequently on scaffolding and the skeletons of skyscrapers is lead oxide (red lead). Fine cut glass is 40 per cent or

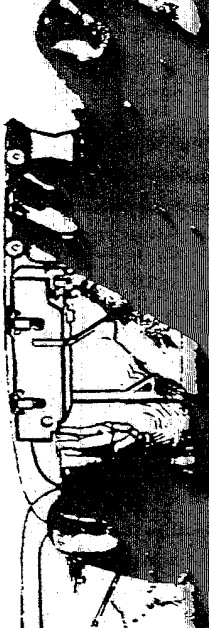

001635

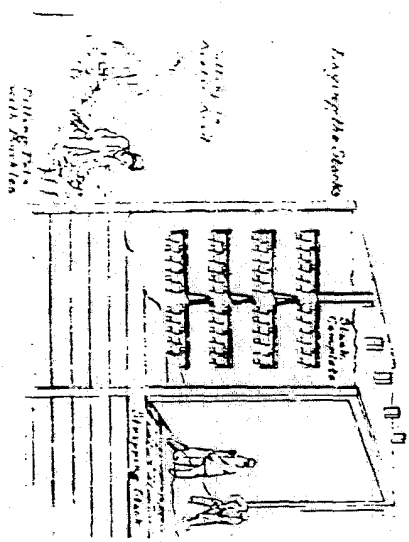

which might otherwise fill the air. This dust collector is the invention of National Lead Company's engineers and is a very important contribution to the "Safety First" movement.

Next comes the pulverizing process, which goes on in machinery so constructed that here, too, the workman is protected from possibly harmful dust.


A revolutionary arrangement is to have the pulverizing process take place in a huge cylindrical screen where the material is thoroughly shaken up and the larger pieces of unrotted lead are worked out.

The mass is then dropped into a hopper and passed thru a set of corrugated rollers. These pulverize the brittle, corroded parts and

simply flatten out the uncorroded metal parts. In some plants there are two of these rollers with a screen between them.

From the pulverizing rollers the metal is passed to a series of cylindrical screens which revolve almost horizontally, but with just enough tip or slant to carry the ground material, which is fed in at the higher end, gradually along toward the lower end. The first of these screens has rather coarse meshes or slats and most of the pulverized carbonaceous stuff while the scraps of metal tumble out at the open and lower end of cylinder No. 1.

The white-lead that slips thru the meshes is conveyed to cylinder No. 2, where the same process is repeated. The

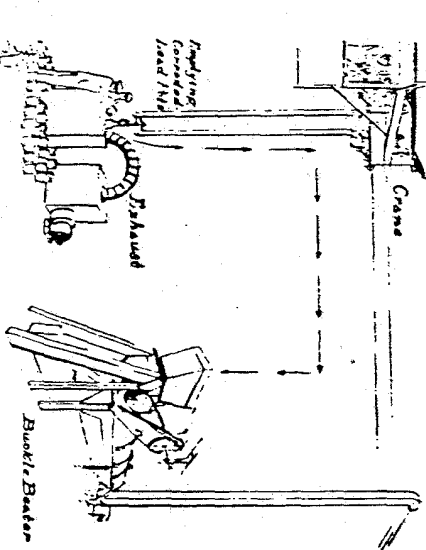

only difference is that the meshes of the screen are finer, and smaller particles of unrotted lead which slipped thru cylinder No. 1 are here worked out. In all the cylinders, whatever their number, the same process is repeated, except that each cylinder is finer meshed than the one before it.


The purpose of every step is to let the pulverized white-lead thru and screen the metal lead out. All the slitting is in straighten chambers.

The scrap metal which rolls out of the ends of the cylinders, one after the other, is dropped thru a chute into a bin, from which it is finally taken and remelted with a new lot of pig lead.

By the time the carbonaceous stuff from the series of screens, it is fairly clean and pretty well pulverized. It looks like fine, white vermilion, but it is not nearly fine enough for use in paint.

The Water Mills


Water-grinding is the next step. It is done between huge millstones placed horizontally one above the other. These stones measure from four and a half to five feet in diameter. In some mills the lower stone is stationary and the upper stone revolves, resting its full weight upon the lower stone. In other mills the upper stone is fixed and the lower stone

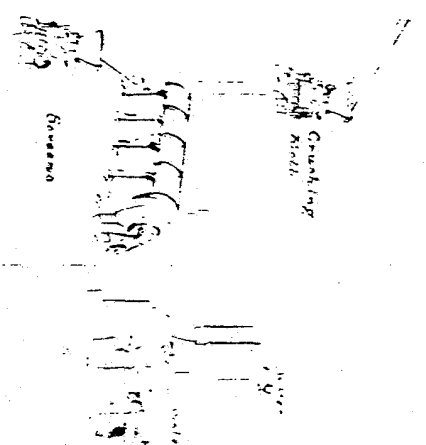

revolves, being pressed against the upper stone by powerful, adjustable screws.


As the slitted white-lead runs into the water mills from the screens it is delivered into mixing tubs where water is added. The resultant milky mixture is then fed down to the mills thru the "eye," whose bottom is so close to the hole in the center of the upper stone, and is continually

ground until it flows from between the millstones into a large box where water is added. The resultant milky mixture is then fed down to the mills thru the "eye," whose bottom is so close to the hole in the center of the upper stone, and is continually

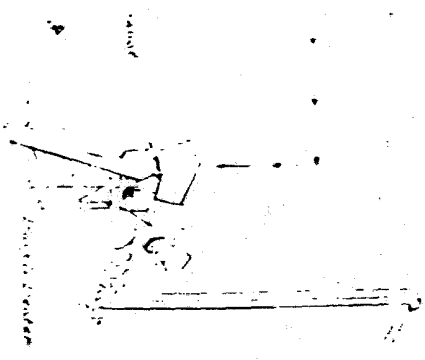

At the time the carbonate gas is added, the water is stirred, and the mixture is allowed to settle. The water is then poured off, and the residue is dried in a furnace, not too hot, for enough for use in the mill.

At the time the carbonate gas is added, the water is stirred, and the mixture is allowed to settle. The water is then poured off, and the residue is dried in a furnace, not too hot, for enough for use in the mill.

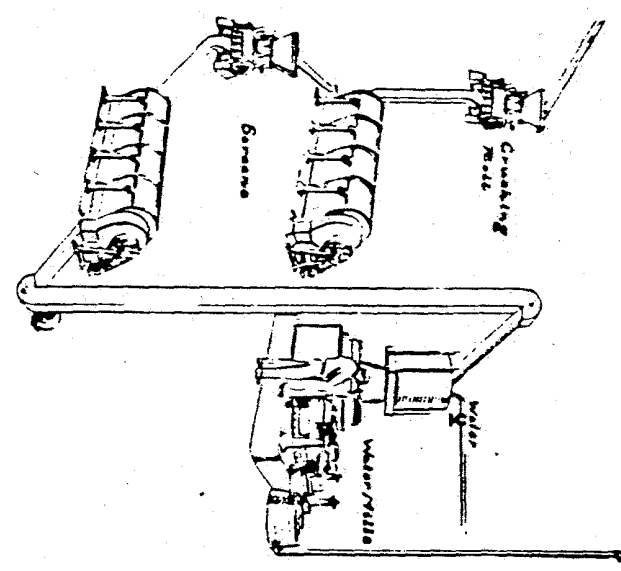


revolves, being pressed against the upper stone by powerful, adjustable screws.

As the sifted white-head comes to the water-mills from the screens it is delivered into mixing tubs, where water is added. The resultant milky mixture is then fed slowly to the mills thru the "eye," a six-inch hole in the center of the upper stone, and is continually

ground until it finally comes out from between the stones at their outer edges.

From the water-mills, the mixture of white-head and water runs into the "drag box." This is a water-tight box, measuring twenty-five feet long and five feet wide, whose bottom is so inclined that the depth is nothing at one end and five feet at the other end. When

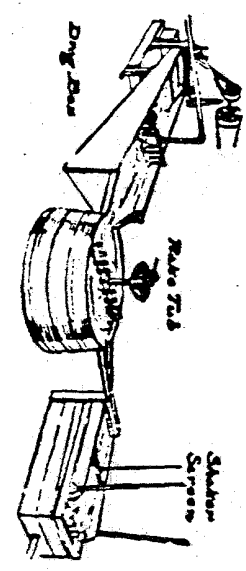

the mills are in operation, the drag box is always full to overflowing and the box is so set that the overflow is from the top edge at the deep end.



Some Particles Fine Enough to Float

The finest particles of white-head are most likely to float and naturally are the first to overflow. The coarser particles, being heavier, settle. A heavy sediment would soon form in the bottom of the drag box were it not for the "drags," a device which consists of two endless chains running lengthwise, one chain on each side of the box. They travel close to the bottom over revolving pulleys and are fitted with brass cradles at intervals of about four feet. The motion is such that the bars keep dragging the head-and-water mixture up the inclined bottom toward the shallow end, away from the overflow. In fact, each bar picks a little of the heavy pulp up over the shallow end of the box. This

The Last Tool for Fineness

From the rake tube the white-head flows upon a screen of silk bolting cloth with meshes so minute that there are 57,000 or more of them to the square inch. This is called, besides

NT 001636

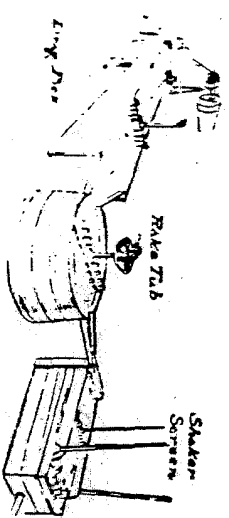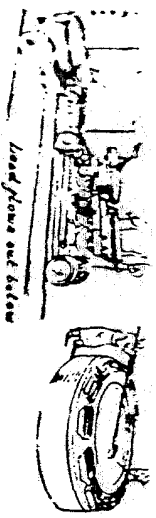

the mills are in operation, the drag box is always full to overflowing and the box is so wet that the overflow is from the top edge of the box and not from the sides.

Some Particles Fine Enough to Float

The finest particles of white lead are most likely to float and naturally are the first to overflow. The coarser particles, being heavier, settle. A heavy sediment would soon form in the bottom of the drag box were it not for the stirrer, which consists of two cross-bars running lengthwise, one chain on each side of the box. They travel close to the bottom over revolving pulleys and are fitted with large rollers at intervals of about four feet. The operation is such that the bars keep it giving the lead and water mixture up the inclined bottom toward the shallow end, away from the overflow. In fact, each bar pulls a fifth of the heavy pulp up over the shallow end of the box. This

heavy, coarser pulp is carried back to the water-mills for another grinding.

Observe that through the process of manufacture the machinery is designed to reject all along the line the material which is not of suitable fineness.

The milk-like liquid which has washed over the end of the drag box flows into and then a series of "rake" tubs, so named because they are equipped with slowly revolving arms of steel which keep the lead and water stirred up, causing the finer white-lead to float on top of the water. The coarser particles settle. Here, too, the white-lead is washed of all traces of acid and other impurities.


The Last Test for Fineness

From the rake tubs the white-lead floats upon a screen of silk bailing cloth with meshes so minute that there are 27,000 or more of them to the square inch. This shaker screen, as it is called, stands

on wobbly legs and is jiggled mechanically with a quick, jerky motion to keep the meshes from becoming clogged.

Particles which will not pass through the microscopic openings in this silk screen are rejected as too coarse for Dutch Boy white-lead.

the other, each having a double bottom thru which the screen passes. A forced circulation of warm air over the surface of the pans really absorbs the moisture from the drying lead. The whole apparatus is enclosed in a dust-proof structure.

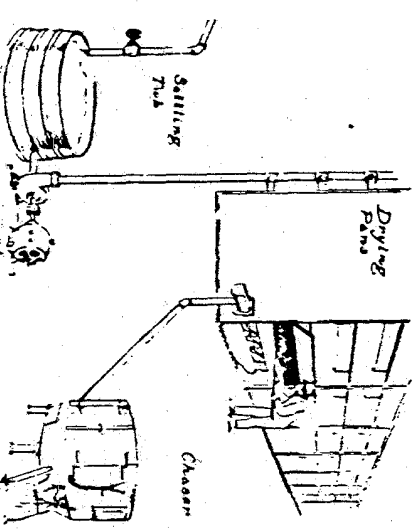

and are returned to the mills to be reground. That white-lead passes thru the screen is pumped into steam-jacketed pans to be dried.

A Dustproof Drying Apparatus

In National Lead Company's improved system, a drying battery consists of four pans, one above

The system of air circulation, controlled by a suction fan, is such that when a door in front of one of the pans is opened there is a strong in-current of air. Thus the workman may safely stand in front of the door and rake the dried lead toward the front of the pan, where it drops to a screw conveyor.

The engineers of National Lead Company designed this safe system of drying white-lead and other lead salts to all companies who care to use it.

The screw conveyor carries the dry white-lead to the storage hopper and the weighing apparatus, which also are dust-tight. When the scales indicate that as much white-lead has run into the hopper as is to be mixed at one time, the feed is cut off. Another screw conveyor then carries the contents of the hopper to an enclosed "chaser" to be mixed with the proper amount of pure linseed oil. The usual proportion is about eight per cent of oil to thirty-two per cent of lead.


The Linseed Oil is Finally Ground In

In the chaser is a mill-stone, weighing a ton and a half, which travels around and around in an




upright position. By the pressure of the heavy interlocking and churning of the lead with the white-lead, the latter is broken up, thus assuring the best addition of lead to the white-lead. Then a small gate in the bottom of each hopper allows the lead to drop into a set of mills, where it comes a final grinding. The white-lead is then packed in steel kegs, one of them filled by weight, the others all packed with lead.

Next, all paste white-lead is packed in 12 1/2 x 23 x 50-pound steel kegs, though can one, two, three and five pound are sold for the convenience of consumers. The steel made by National Lead Company are pressed out of single sheet steel and are therefore made

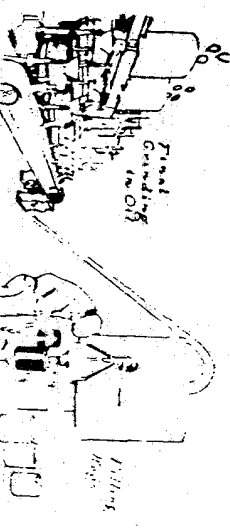

ably legs and in jiggled motion with a quick, jerky motion to keep the mixture from being clumped. The particles which will not pass through the microscopic openings in the screen are rejected as too large for Dutch boy white-lead.

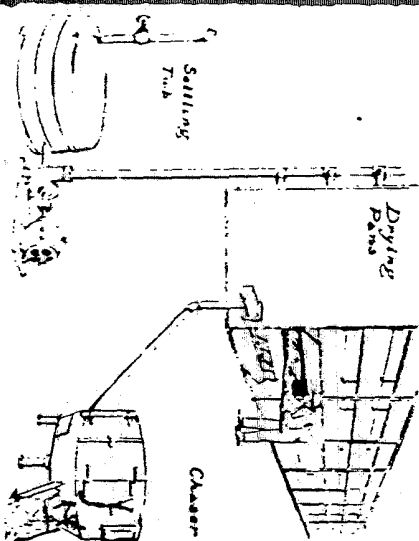

are returned to the mills to be ground. That which passes through the screen is pumped into steam-heated pans to be dried.

The system of air circulation, controlled by a suction fan, is such that when a door in front of one of the pans is opened there is a strong in-current of air. Thus the workman may safely stand in front of the door and rake the dried lead toward the front of the pan, where it drops to a screw conveyor.

The engineers of National Lead Company designed this safe system of drying white-lead and offer it freely to all competitors who care to use it.

The screw conveyor carries the dry white-lead to the storage hopper and the weighing apparatus, which also are dust-tight. When the scales indicate that as much white-lead has run into the hopper as is to be mixed at one time, the feed is cut off. Another screw conveyor then carries the contents of the hopper to an enclosed "chaser" to be mixed with the proper amount of pure linseed oil. The usual portion is about eight per cent of oil to ninety-two per cent of lead.

The Linseed Oil is Finally Ground In


In the chaser is a mill-stone, weighing a ton and a half, which travels around and around in an



upright position. By this process the thorough incorporation and machine-mixing of the linseed oil with the white-lead are assured, thus simplifying the later addition of linseed oil, turpentine or other by the painter.

Through a small gate in the bottom of each chaser the white-lead paste drops to a set of mills where it receives a final grinding and emerges in dough-like chunks as the white-lead of commerce. All that remains to be done is to pack it in steel kegs, every one of them filled by weight, and ship them off to market.

Nearly all paste white-lead is packed in 12½, 25, 50, or 100 pound steel kegs, though cans of one, two, three and five pounds are sold for the convenience of small consumers. The steel kegs made by National Lead Company are pressed out of single sheets of steel and are therefore seamless.

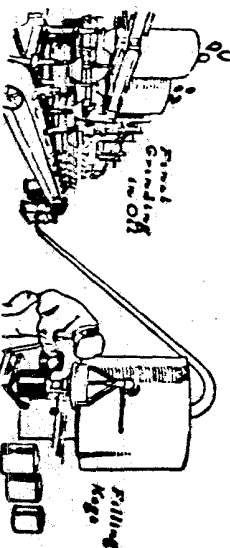

N L 1 001638