

11 7863



THE DOW CHEMICAL COMPANY

TEXAS DIVISION
FREEPORT TEXAS 77541

W. F. CRAWFORD

PLAINTIFF'S EXHIBIT

DOW-674

ANALYTICAL METHOD

September 30, 1968

Method No. TC-AM-68-15

DETERMINATION OF ACID-SOLUBLE IRON IN ASBESTOS

1. Scope

- This method is suitable for the determination of 0.2% or more of acid-soluble iron in asbestos.

2. Principle

- Iron is solubilized by digestion of the asbestos with hot hydrochloric acid. The iron is reduced with stannous chloride and then measured by titration with standard potassium dichromate.

3. Safety Precautions

Strong mineral acids are used in this procedure. Care should be exercised to prevent spilling of the acids on the skin or clothing. If this occurs, wash the affected areas immediately with large quantities of water. The eyes should be protected with safety glasses or chemical goggles.

4. Reagents

- (a) Hydrochloric acid, ACS reagent.
(b) Stannous chloride solution. Weigh 6 grams of the dihydrate ($\text{Sn Cl}_2 \cdot 2\text{H}_2\text{O}$) into a 250 ml beaker and add approximately 60 ml concentrated hydrochloric acid. Heat gently for solution, and then dilute to approximately 100 ml with water. Store in an amber bottle.
(c) Mercuric chloride, saturated aqueous solution. Add approximately 10 grams of reagent grade HgCl_2 to a glass bottle for each 100 ml solution required. Add distilled water and shake the solution vigorously for approximately one minute.

Iron analysis, detn of, in asbestos
1 of 3 pages

Asbestos iron detn

570203751

(d) Diphenylamine indicator solution, 1% dissolved in concentrated sulfuric acid. Alternate preparation: To one gram of barium diphenylamine sulfonate in 100 ml water, add approximately 0.5 grams sodium sulfate. Acidify the solution with dilute sulfuric acid and heat gently on the hot plate. Stir occasionally to aid precipitation. Filter the hot solution through a close-textured filter paper catching the filtrate in an amber dropper bottle. Discard the paper and precipitate.

(e) Sulfuric-phosphoric acid mixture. While stirring, add 150 ml concentrated ACS reagent sulfuric acid to 500 ml cold distilled water. Follow this by adding, while stirring, 150 ml concentrated phosphoric acid. Dilute the mixture to approximately 1,000 ml with distilled water.

(f) Potassium dichromate, 0.1N solution. Weigh 4.904 grams of dried $K_2Cr_2O_7$. Dissolve in distilled water and dilute to one liter in a liter volumetric flask.

Standardize the solution as follows: Weigh to the nearest 0.1 mg approximately 0.2 grams high purity iron wire in a 400 ml beaker and add 20 ml concentrated hydrochloric acid. Attach cover glass and heat the solution gently until the iron is dissolved. Complete the standardization according to the following procedure beginning with the addition of stannous chloride and continuing throughout the procedure.

5. Procedure

(a) Weigh approximately 2 grams of the asbestos to three decimal places on the analytical balance and transfer to 400 ml beakers. Add 100 ml distilled water and 50 ml concentrated hydrochloric acid. Add cover glasses and boiling chips to the beakers and place on the hot plate. Boil gently for a minimum of one hour, adding more water as needed to maintain the volume essentially constant.

(b) To the hot solutions, add while stirring stannous chloride drop by drop until the solutions are colorless. Now add 3 to 5 drops in excess. Place the solutions in an ice bath for cooling. When cold, quickly add 20 ml saturated mercuric chloride solution while stirring vigorously (note 7a). Continue stirring for approximately 30 seconds. Place the beakers in the cold bath for 5 to 10 minutes.

(c) Dilute the solutions to approximately 250 ml with distilled water and add 15 ml of the sulfuric acid-phosphoric acid mixture. Add about 10 drops of the diphenylamine indicator solution. While stirring, titrate with 0.1N potassium dichromate until a permanent dark blue color is reached. This color should persist for 30 seconds.

510200752

6. Calculations

$$\text{Normality of K}_2\text{Cr}_2\text{O}_7 = \frac{\text{grams of pure iron taken}}{\text{ml titrant} \times 0.05585}$$

$$\% \text{ Iron (Fe)} = \frac{\text{ml} \times \text{Normality of K}_2\text{Cr}_2\text{O}_7 \times 5.585}{\text{grams sample}}$$

$$\% \text{ Iron Oxide (Fe}_2\text{O}_3) = \% \text{ Iron (Fe)} \times 1.43$$

7. Notes

A white feathery precipitate should appear at this point. If no precipitate is evident, not enough stannous chloride was added; if a dark precipitate appears, too much stannous chloride was added. If either of the latter two situations develops, the test must be repeated using a greater or lesser quantity of the stannous chloride.

W. F. Crawford
Central Laboratory
A-1203 Building

ga

510203753

B-14070

10060

MIDLAND
October 10, 1968

12

R. A. Smith
B-205
Freeport, Texas

PAPER: Determination of Acid-Soluble Iron in Asbestos.
W. F. Crawford

This method, containing the standard liability clause, is approved
for outside distribution.

We are retaining three copies for our files.

Comments:

- E. E. Schilling-Disclaimer stamp should be applied to copies
going outside Dow.
- F. W. Koerker-Omit Author's name and add legal paragraph to copies
for outside distribution.

E. Monroe
Corporate R. & D.
mm

B-14070

*cc: T. H. Grogg
17 H. Bdy 12-13-68*

ST0203754



ROUTING SHEET FOR THE RELEASE OF TECHNICAL INFORMATION

TECHNICAL INFORMATION SERVICES

566 BLDG., MIDLAND, MICHIGAN

IN ORDER TO SAFEGUARD THE INTEREST OF THE DOW CHEMICAL COMPANY AND ITS AUTHORS, ALL TALKS, PAPERS, PUBLICATIONS, ARTICLES, NEWS RELEASES, ETC., FOR RELEASE OUTSIDE THE COMPANY, MUST FIRST BE APPROVED. TECHNICAL INFORMATION MUST BE APPROVED BY MIDLAND TECHNICAL INFORMATION SERVICES AND OTHER MATERIAL BY THE PUBLIC RELATIONS DEPARTMENT.

NOTE: SEND 4 COPIES OF MATERIAL TO TECHNICAL INFORMATION SERVICES, 566 BLDG., MIDLAND, MICH.

ALL INFORMATION ABOVE "*" OF THIS FORM IS TO BE SUPPLIED AT SOURCE.

RECEIVED
CORPORATE R & D

OCT 7 1968

TITLE OF PROPOSED TALK OR PUBLICATION

Determination of Acid-Soluble Iron in asbestos

AUTHORS

W. F. Crawford

anal

SUBMITTED

NAME

R. G. Smith

DATE

10-3-68

DEADLINE DATE

none

BY

PLANT ADDRESS

B-205

DIVISION

Texas

PLANT PHONE NO.

238-2158

TO WHAT PROCESS IS THE INFORMATION IN THIS PAPER RELATED?

IS THIS INFORMATION
COVERED BY PATENTS
— DISCLOSURES?

CHECK ONE

☐ YES

☒ NO

IF "YES",
COMPLETE
FOLLOWING



DISCLOSURE NO.

CASE NO.

PATENT NO.

WHERE AND WHEN TALK IS TO BE PRESENTED

PROBABLE PUBLICATION OR DISTRIBUTION

To our suppliers of asbestos: Johns-Manville and G.A.F. Corp.

NOTE: YOUR APPROVAL IS TAKEN TO MEAN THAT AS FAR AS YOU KNOW, THE RELEASE OF THIS INFORMATION WILL NOT CAUSE THE COMPANY EMBARRASSMENT FROM THE VIEWPOINT OF LIABILITY, TRADE AGREEMENTS, PATENTS OR FUTURE DEVELOPMENTS.

ROUTING TO:	APPROVED BY: (SIGNATURE)	DATE	COMMENTS (ATTACH EXTRA SHEETS IF NECESSARY)
DEPT. HEAD	R. G. Smith (method Editor)	10-3-68	
PATENT	E. Schulling	10-8-68	Disclaimer stamp should be applied to all copies going outside Dow
12-7			
Hester			
M. Wolf			

NOTE: ALWAYS RETURN YOUR SIGNED COPY OF THIS SHEET ALONG WITH THE MANUSCRIPT TO TECHNICAL INFORMATION SERVICES.

APPROVED FOR RELEASE BY

E. Manual
10/10/68

LIMITATIONS



ROUTING SHEET FOR THE RELEASE OF TECHNICAL INFORMATION
TECHNICAL INFORMATION SERVICES 566 BLDG., MIDLAND, MICHIGAN

IN ORDER TO SAFEGUARD THE INTEREST OF THE DOW CHEMICAL COMPANY AND ITS AUTHORS, ALL TALKS, PAPERS, PUBLICATIONS, ARTICLES, NEWS RELEASES, ETC., FOR RELEASE OUTSIDE THE COMPANY, MUST FIRST BE APPROVED. TECHNICAL INFORMATION MUST BE APPROVED BY MIDLAND TECHNICAL INFORMATION SERVICES AND OTHER MATERIAL BY THE PUBLIC RELATIONS DEPARTMENT.

NOTE: SEND 4 COPIES OF MATERIAL TO TECHNICAL INFORMATION SERVICES, 566 BLDG., MIDLAND, MICH.

ALL INFORMATION ABOVE "*" OF THIS FORM IS TO BE SUPPLIED AT SOURCE.

TITLE OF PROPOSED TALK OR PUBLICATION

Determination of Acid-Soluble Iron in asbestos

AUTHORS

W. F. Crawford

SUBMITTED BY	NAME <i>R. G. Smith</i>	DATE <i>10-3-68</i>	DEADLINE DATE <i>none</i>
	PLANT ADDRESS <i>B-205</i>	DIVISION <i>Texas</i>	PLANT PHONE NO. <i>238-2158</i>

TO WHAT PROCESS IS THE INFORMATION IN THIS PAPER RELATED?

IS THIS INFORMATION COVERED BY PATENTS - DISCLOSURES?	CHECK ONE ☐ YES ☒ NO	IF "YES", COMPLETE FOLLOWING	DISCLOSURE NO.	CASE NO.	PATENT NO.
---	--	------------------------------	----------------	----------	------------

WHERE AND WHEN TALK IS TO BE PRESENTED

PROBABLE PUBLICATION OR DISTRIBUTION

To our suppliers of asbestos: Johns-Manville and G.A.F. Corp.

NOTE: YOUR APPROVAL IS TAKEN TO MEAN THAT AS FAR AS YOU KNOW, THE RELEASE OF THIS INFORMATION WILL NOT CAUSE THE COMPANY EMBARRASSMENT FROM THE VIEWPOINT OF LIABILITY, TRADE AGREEMENTS, PATENTS OR FUTURE DEVELOPMENTS.

ROUTING TO:	APPROVED BY: (SIGNATURE)	DATE	COMMENTS (ATTACH EXTRA SHEETS IF NECESSARY)
DEPT. HEAD ☒	<i>R. G. Smith (method Editor)</i>	<i>10-3-68</i>	
PATENT			
<i>Kroeker</i>	<i>F. W. Kroeker</i>	<i>10-7-68</i>	<i>Omit author's name and add legal paragraph to copies for outside distribution.</i>
<i>M. Wolf</i>			

NOTE: ALWAYS RETURN YOUR SIGNED COPY OF THIS SHEET ALONG WITH THE MANUSCRIPT TO TECHNICAL INFORMATION SERVICES.

APPROVED FOR RELEASE BY

LIMITATIONS

ST0283756



ROUTING SHEET FOR THE RELEASE OF TECHNICAL INFORMATION
TECHNICAL INFORMATION SERVICES 566 BLDG., MIDLAND, MICHIGAN

IN ORDER TO SAFEGUARD THE INTEREST OF THE DOW CHEMICAL COMPANY AND ITS AUTHORS, ALL TALKS, PAPERS, PUBLICATIONS, ARTICLES, NEWS RELEASES, ETC., FOR RELEASE OUTSIDE THE COMPANY, MUST FIRST BE APPROVED. TECHNICAL INFORMATION MUST BE APPROVED BY MIDLAND TECHNICAL INFORMATION SERVICES AND OTHER MATERIAL BY THE PUBLIC RELATIONS DEPARTMENT.

NOTE: SEND 4 COPIES OF MATERIAL TO TECHNICAL INFORMATION SERVICES, 566 BLDG., MIDLAND, MICH.

ALL INFORMATION ABOVE "*" OF THIS FORM IS TO BE SUPPLIED AT SOURCE.

TITLE OF PROPOSED TALK OR PUBLICATION

Determination of Acid Soluble Iron in asbestos

AUTHORS

W. F. Crawford

SUBMITTED BY	NAME <i>R. A. Smith</i>	DATE <i>10-3-68</i>	DEADLINE DATE <i>none</i>
	PLANT ADDRESS <i>B-205</i>	DIVISION <i>Texas</i>	PLANT PHONE NO. <i>238-2158</i>

TO WHAT PROCESS IS THE INFORMATION IN THIS PAPER RELATED?

IS THIS INFORMATION COVERED BY PATENTS — DISCLOSURES?	CHECK ONE ☐ YES ☒ NO	IF "YES", COMPLETE FOLLOWING	DISCLOSURE NO.	CASE NO.	PATENT NO.
---	--	------------------------------------	----------------	----------	------------

WHERE AND WHEN TALK IS TO BE PRESENTED

PROBABLE PUBLICATION OR DISTRIBUTION

To our suppliers of asbestos: Johns Manville and G.A.F. Corp.

NOTE: YOUR APPROVAL IS TAKEN TO MEAN THAT AS FAR AS YOU KNOW, THE RELEASE OF THIS INFORMATION WILL NOT CAUSE THE COMPANY EMBARRASSMENT FROM THE VIEWPOINT OF LIABILITY, TRADE AGREEMENTS, PATENTS OR FUTURE DEVELOPMENTS.

ROUTING TO:	APPROVED BY: (SIGNATURE)	DATE	COMMENTS (ATTACH EXTRA SHEETS IF NECESSARY)
DEPT. HEAD	<i>R. A. Smith (method Editor)</i>	<i>10-3-68</i>	
PATENT			
	<i>W. F. Crawford</i>	<i>10-7-68</i>	


ST0203757

NOTE: ALWAYS RETURN YOUR SIGNED COPY OF THIS SHEET ALONG WITH THE MANUSCRIPT TO TECHNICAL INFORMATION SERVICES.

APPROVED FOR RELEASE BY

LIMITATIONS

21 3870

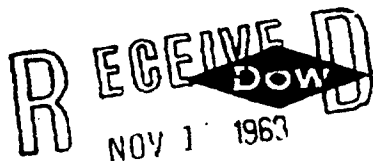

CENTRAL RESEARCH INDEX

THE DOW CHEMICAL COMPANY

MIDLAND, MICHIGAN

ANALYTICAL METHOD

September 30, 1968

17537

THIS IS A FILE COPY. FOR
OUTSIDE DISTRIBUTION OB-
TAIN COPIES WITH LIABIL-
ITY CLAUSE AND WITHOUT
DOW REFERENCE

Method No. TC-AM-68-15

DETERMINATION OF ACID-SOLUBLE IRON IN ASBESTOS

1. Scope

— This method is suitable for the determination of 0.2% or more of acid-soluble iron in asbestos.

2. Principle

— Iron is solubilized by digestion of the asbestos with hot hydrochloric acid. The iron is reduced with stannous chloride and then measured by titration with standard potassium dichromate.

3. Safety Precautions

Strong mineral acids are used in this procedure. Care should be exercised to prevent spilling of the acids on the skin or clothing. If this occurs, wash the affected areas immediately with large quantities of water. The eyes should be protected with safety glasses or chemical goggles.

4. Reagents

(a) Hydrochloric acid, ACS reagent.

(b) Stannous chloride solution. Weigh six grams of the dihydrate ($\text{SnCl}_2 \cdot 2\text{H}_2\text{O}$) into a 250 ml beaker and add approximately 60 ml concentrated hydrochloric acid. Heat gently for solution, then dilute to approximately 100 ml with water. Store in an amber bottle.

(c) Mercuric chloride, saturated aqueous solution. Add approximately 10 grams of reagent grade HgCl_2 to a glass bottle for each 100 ml solution required. Add distilled water and shake the solution vigorously for approximately one minute.

(d) Diphenylamine indicator solution, 1% dissolved in concentrated sulfuric acid. Alternate preparation: To one gram of barium diphenylamine sulfonate in 100 ml water, add approximately 0.5 grams sodium sulfate. Acidify the solution with dilute sulfuric acid and heat gently on the hot plate. Stir occasionally to aid precipitation. Filter the hot solution through a close-textured filter paper catching the filtrate in an amber dropper bottle. Discard the paper and precipitate.

ST0203037

Asbestos iron determination
Iron analysis method of asbestos

(e) Sulfuric-phosphoric acid mixture. While stirring, add 150 ml concentrated ACS reagent sulfuric acid to 500 ml cold distilled water. Follow this by adding, while stirring, 150 ml concentrated phosphoric acid. Dilute the mixture to approximately 1,000 ml with distilled water.

(f) Potassium dichromate, 0.1N solution. Weigh 4.904 grams of dried $K_2Cr_2O_7$. Dissolve in distilled water and dilute to one liter in a liter volumetric flask.

Standardize the solution as follows: Weigh to the nearest 0.1 mg approximately 0.2 grams high purity iron wire in a 400 ml beaker and add 20 ml concentrated hydrochloric acid. Attach cover glass and heat the solution gently until the iron is dissolved. Complete the standardization according to the following procedure beginning with the addition of stannous chloride and continuing throughout the procedure.

5. Procedure

(a) Weigh approximately 2 grams of the asbestos to three decimal places on the analytical balance and transfer to 400 ml beakers. Add 100 ml distilled water and 50 ml concentrated hydrochloric acid. Add cover glasses and boiling chips to the beakers and place on the hot plate. Boil gently for a minimum of one hour, adding more water as needed to maintain the volume essentially constant.

(b) To the hot solutions, add while stirring stannous chloride drop by drop until the solutions are colorless. Now add 3 to 5 drops in excess. Place the solutions in an ice bath for cooling. When cold, quickly add 20 ml saturated mercuric chloride solution while stirring vigorously (see note). Continue stirring for approximately 30 seconds. Place the beakers in the cold bath for 5 to 10 minutes.

(c) Dilute the solutions to approximately 250 ml with distilled water and add 15 ml of the sulfuric acid-phosphoric acid mixture. Add about 10 drops of the diphenylamine indicator solution. While stirring, titrate with 0.1N potassium dichromate until a permanent dark blue color is reached. This color should persist for 30 seconds.

6. Calculations

$$\text{Normality of } K_2Cr_2O_7 = \frac{\text{grams of pure iron taken}}{\text{ml titrant} \times 0.05585}$$

$$\% \text{ Iron (Fe)} = \frac{\text{ml} \times \text{Normality of } K_2Cr_2O_7 \times 5.585}{\text{grams sample}}$$

$$\% \text{ Iron Oxide (Fe}_2\text{O}_3) = \% \text{ Iron (Fe)} \times 1.43$$

570203038

7. Notes

A white feathery precipitate should appear at this point. If no precipitate is evident, not enough stannous chloride was added; if a dark precipitate appears, too much stannous chloride was added. If either of the latter two situations develops, the test must be repeated using greater or lesser quantity of the stannous chloride.

* * * * *

The analytical procedures given herein have been adapted from literature sources or developed upon the basis of experimental data which are believed to be reliable. In the hands of a qualified analyst they are expected to yield results of sufficiency accuracy for their intended purposes. However, The Dow Chemical Company makes no representation or warranty whatsoever concerning the procedures or results to be obtained and assumes no liability in connection with their use. Users are cautioned to confirm the suitability of the methods by appropriate tests. Anyone wishing to reproduce or publish the material in whole or in part should request written permission from The Dow Chemical Company.

W. F. Crawford
Central Laboratory

ST0203039