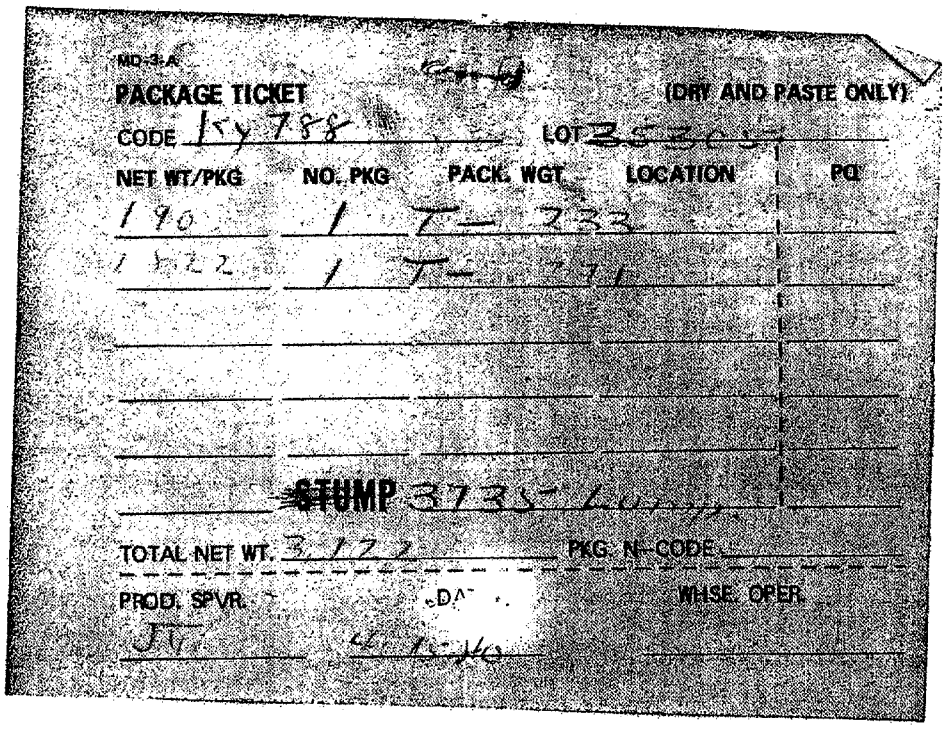


MD-3-A

PACKAGE TICKET (DRY AND PASTE ONLY)

CODE 15y788 LOT 35303

NET WT/PKG	NO. PKG	PACK. WGT.	LOCATION	PC
190	1	T- 233		
1922	1	T- 231		
	STUMP 3733 Lot			

TOTAL NET WT. 3122 PKG. N--CODE

PROD. SPVR. D.A. WHSE. OPER.

JV 4 10:40

N32265

22 Totes

CG 03 CODE KY-788-D PKG. ____

244→ APR 11 35305

EST. WGT. 960 LBS.

OK
AP

Total Wgt. 3560# Req(_____)

PROCESSING INSTRUCTIONS: BATCH UNIT

PROCESSES	APPROVED BY
KY-788-D (J)	~~EMK 9/22/76~~
	DCG 9/27/76
TYPED BY	
NE 2/17/77	

MAKING NOTES

REMARKS

NAME: "KROLOR" YELLOW - LIGHT NON-BLEEDING

INSTRUCTIONS -PRESSING- RECORD

VAT	244			
DATE	4-12-80			
TIME	10:00 AM			
RELEASED BY				
PRESS	22	23	24	
NO. OF CAKES	46	46	46	

PRESS With AGITATION
WASH TO 2000 OHMS with 35-75°F water
TEST AFTER 2 HOURS
LOAD on 6 cars

PRESSLOAD	1ST	2ND	3RD	4TH	5TH
STARTED	1300M				
CAKES USED	46				
WATER ON	3AM				
HRS. WASHED	5				
OHMS	2000				
HRS. WASHED					
OHMS					
HRS. WASHED					
OHMS					
CAKE CONDITION					
NO. CARS LOADED	6+2				

EXPLAIN LOSSES

SAMPLES 1- 8oz JAR
DELIVER TO CTL for Color
SAMPLED BY #52 RELEASED BY

-DRYING-

1-Dry 12 hrs at 220 °F N.V.
2-Then Dry 8 hrs at 160 °F

LUMP: - OK - WET - SALTS - CONTAMINATED

ADDITIONAL DRYING HOURS REQUIRED

No Drums 15

SAMPLES
DELIVER TO
NO. CARS PULLED LUMP WGT. 3735
SAMPLED BY RELEASED BY

-GRINDING-

MILL 939 HSP 3/32" RP SCREEN 3500 RPM
MAX. TEMP. 150 °F

SCREEN RPM
MAX. TEMP. °F

EXPLAIN LOSSES

SAMPLE AFTER / WITHOUT MIXING
SAMPLES 1 Env. & 1 Pt can
DELIVER TO C T L

DATE MIXED
SAMPLED BY RELEASED BY

N32265.01

DUP050457342

3530
4100
18

0.00 *

2.63 +
0.14 -
2.62 +
0.14 -
2.65 +
0.14 -
2.60 +
0.14 -
2.73 +
0.14 -
2.63 +
0.14 -
2.67 +
0.14 -
2.57 +
0.14 -
2.57 +
0.14 -
2.69 +
0.14 -
2.61 +
0.14 -
2.62 +
0.14 -
2.62 +
0.14 -
2.63 +
0.14 -
2.61 +
0.14 -
37.35 *

N32265.02