

Fire Properties of Polyvinyl Chloride

Polyvinyl chloride (PVC, or vinyl) possesses excellent fire performance properties. In particular, it will not burn once the source of heat or flame is removed. This results from PVC having 56.8% chlorine in its base polymer weight. It is well known that chlorine is one of the few elements that confers good fire properties to a polymer.^{1,2}

Samples of unplasticized (rigid) vinyl, such as those found in pipe, siding or vertical blinds, have higher ignition temperature, lower flame spread and lower heat released in a fire than similar samples of wood. When PVC is plasticized to make it into flexible products such as wire coatings, upholstery, medical blood bags or wall coverings, the fire properties become less favorable, depending on the amount and kind of plasticizer and other additives used. However, most plasticized PVC products in use will not continue to burn once the flame source is removed, even if not additionally fire-retarded.

The actual fire properties of PVC have been calculated from the results of small-scale and full-scale tests, and interpreted in terms of overall fire hazard.

FIRE HAZARD

The fire hazard of a product is determined by a combination of factors including its ignitability and flammability, the amount of heat released from it when it burns, the rate at which this heat is released, the flame spread, the smoke production and the toxicity of the smoke.

Ignitability

If a material does not ignite, it will not contribute to fire hazard and thereby cannot endanger lives. Most organic materials do, however, ignite and the lower the ignition temperature, the greater the hazard.

Figure 1 presents the self-ignition and flash-ignition temperatures of a variety of common materials, as measured by a standard test (ASTM D1929). With a flash ignition temperature of 346°C, PVC is among the least easily ignited polymers.

Flammability


Once ignited, the greater the flammability of a material, the greater the hazard associated with it. One of the most reliable quantitative small-scale flammability tests is the limited oxygen index test (LOI; ASTM D2863), which gives the limiting concentration of oxygen in the atmosphere necessary for sustained combustion. In general, a material with LOI of more than 21 should not burn in air at room temperature, and, one with LOI of more than 25-27 will only burn under extreme conditions. Table 1 shows that very few common materials have an LOI higher than PVC.

When PVC is plasticized in order to achieve flexibility, its LOI is lower than that of rigid PVC; the exact value will depend on the formulation. Phthalate plasticizer affects the LOI of PVC as shown in Figure 2. Because typical wire and cable compounds contain only 15-35 percent plasticizer, most will not burn in air unless a source of heat or flame is applied.

Flame Spread

The tendency of a material to spread flame can be measured using the radiant panel test, ASTM E162. Results from this test (Table 2) show that PVC is one of the materials with the lowest flame spread rating; it will not spread flame on its own.

Figure 1

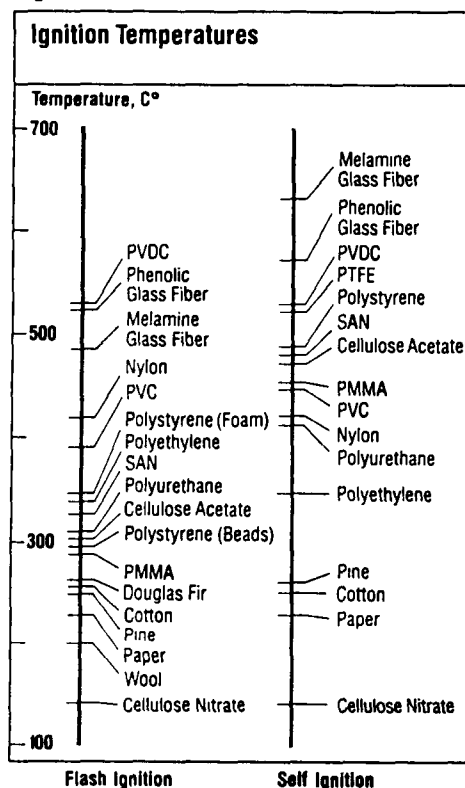

CTL016279

Table 1²⁻⁴

Limiting Oxygen Indices of Various Materials

Material	LOI
Polyacetal	14.9
Polyoxymethylene	15.7
Cotton	16-17
Natural rubber	17.2
PMMA	17.4
Polyethylene	17.4
Polypropylene	17.4
Polystyrene	17.6-18.3
Polyacrylonitrile	18.0
SAN	18.0
ABS	18.3-18.8
Rayon	18.7-18.9
Cellulose	19.0
PET	20.0
PVF	22.6
Nylon 6,6	24-29
Wool	25.2
Polycarbonate	26-28
Neoprene rubber	26.3
Modacrylic	26.8
Nomex	28.5
Polysulphone	30-32
Leather (FR)	34.8
Polyimide	36.5
PVDF	43.7
PVC (rigid)	45-49
Carbon black rod	59-63
PVDC	60.0
Chlorinated PVC	60-70
PTFE	95.0

Note: The fire performance for this test improves as the LOI becomes higher.

Heat Release

A burning object will spread a fire to nearby products only if it gives off enough heat to ignite them. Moreover, the heat has to be released fast enough not to be dissipated or lost while traveling through the cold air surrounding anything not on fire. Therefore, the most important flammability property, in terms of fire hazard, is the heat released. Figures 3 and 4 present normalized results for total heat released and maximum rate of heat released for a variety of materials, as measured by an Ohio State University rate of heat release calorimeter (OSU-RHR, ASTM E906).⁶ They show that most materials are more prone to ignite other products than PVC.

Smoke

The amount of smoke that materials produce when they burn also is important because smoke obscures light and hinders escape from a fire.

The most common method for measuring smoke from burning products is the U. S. National Bureau of Standards (NBS) smoke chamber in the vertical mode (ASTM E662), and results from it are shown in Figure 5. This test is now known, however, to be seriously flawed; the principal deficiencies identified are

shown in Table 3. The most important of the problems with the NBS smoke chamber is that its results misrepresent the smoke found in real fires.

One example of this is the effect of sample orientation. Some materials melt or drip when exposed to flame. When samples of such materials are exposed vertically in the NBS smoke chamber test, the molten portions will have escaped the effect of the radiant heat source. This means that some of the material does not burn during the test. If these dripping products are exposed horizontally, the entire sample will be consumed. The test, therefore, measures an amount of smoke artificially lower than what would be formed in a realistic scenario (see Table 4). PVC, however, does not melt or drip and the test, thus, gives the same smoke production results in the vertical or horizontal orientations. Therefore, when the smoke results of other materials are corrected for the melting effect by changing the orientation, the relative ranking of PVC in terms of smoke production changes. In fact, its smoke production figures become very similar to those of other materials regarded as low smoke producing, such as polyethylene or polypropylene (Table 5).

Table 2⁴

Surface flammability of some materials

Material	Thickness (mm)	Flame spread index
Chlorinated PVC	3	4
Polyether sulphone	3	5
PVC	4	10
Polyester	3	30-56
FR polystyrene	3	59
FR polycarbonate	6	73
Polycarbonate	3	88
Red oak	19	99
Phenolic resin	2	114
Plywood (fir)	6	143
Hardboard	6	185
GRP polyester (21%)	2	239
FR acrylic	3	316
Polystyrene	2	355
Acrylic	6	416
Polyurethane foam (flexible)		1490
Polyurethane foam (rigid)		2220

Note: The fire performance for this test improves as the flame spread ratings become lower.

CTL016 30


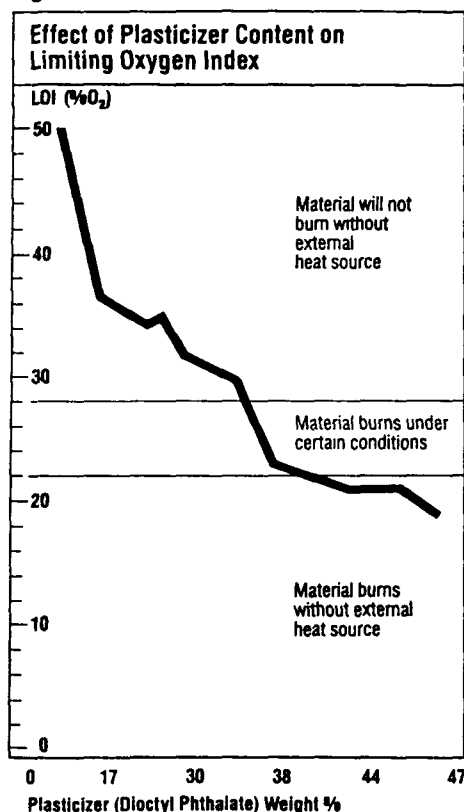
Figure 2⁵

Figure 3

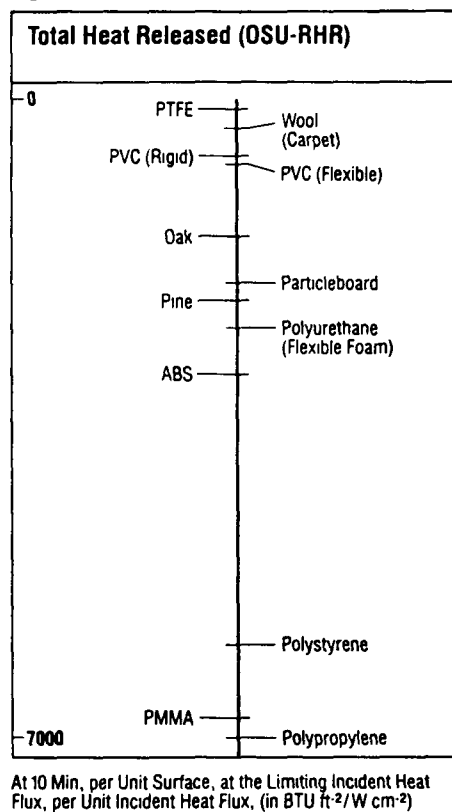

At 10 Min, per Unit Surface, at the Limiting Incident Heat Flux, per Unit Incident Heat Flux, (in BTU ft⁻²/W cm⁻²)

Even when corrections are made, however, the NBS smoke chamber cannot address the fact that fire hazard from smoke depends on how much product burns and how much heat is associated with it. This can be done by measuring smoke production from materials using a smoke parameter.⁸ This is a test, developed by NBS, which measures the amount of smoke produced in the form most relevant to fire hazard by combining the light obscuration with the rate of heat released. It has been measured^{4,11} on another, newer rate of heat release instrument: the NBS Cone calorimeter (ASTM E5- Proposal P-190).¹² Results from this instrument correlate with full-scale fires.¹³⁻¹⁵ Table 6 indicates that standard rigid PVC has a smoke parameter less than one tenth of that of other plastic materials such as polyester, polyethylene, or polypropylene, with low smoke production numbers in the NBS smoke chamber test (Figure 5). Flexible PVC compounds have higher smoke parameters than rigid ones, due to the effect of the plasticizer.


Mass Loss

In addition to heat and smoke release, fire hazard also depends heavily on the release of toxic combustion products into the atmosphere – that is, on the mass loss rate of a material. If a product loses mass very rapidly, a hazardous accumulation of dangerous smoke will develop more easily. The rate of mass loss for most flame retarded materials is relatively similar. The other results shown in Table 6 – rates of mass loss and of heat release – also measured with the NBS Cone calorimeter, indicate that PVC has both a very low maximum rate of heat release and a low rate of mass loss.

Toxicity


Finally, fire hazard also is associated with the toxicity of the smoke itself. Figure 6 presents some results on the toxic potency of the smoke of a variety of common materials, as measured by the NBS cup furnace toxicity test,¹⁸ and compares them with the intrinsic toxic potency of other poisons and toxic gases, as well as with textbook toxicity categories.¹⁹

Figure 4

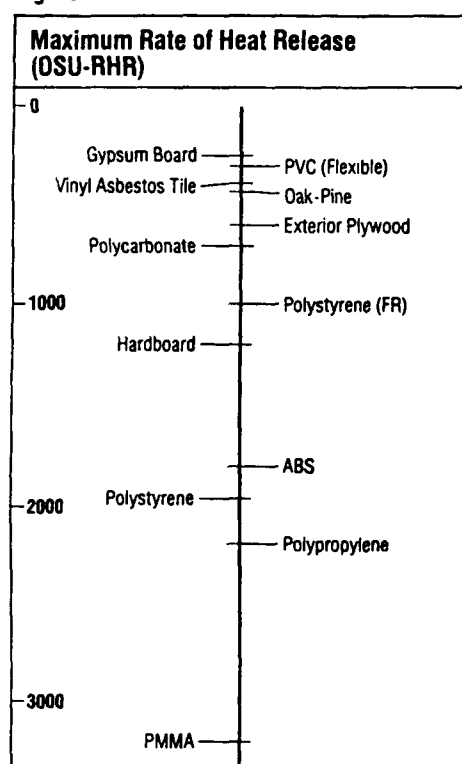

At an Incident Heat Flux of 2 W cm⁻² (in BTU min⁻¹ ft⁻²)

Figure 5

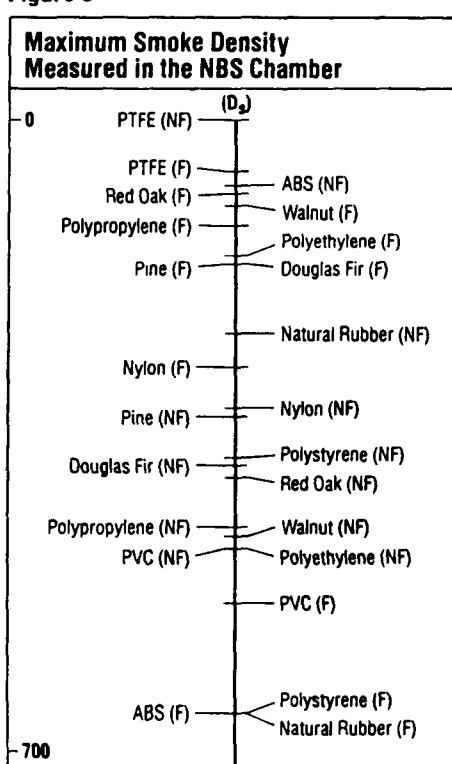

F = flaming mode; NF = nonflaming mode

Table 7

Lethal Exposure Doses for Common Gases

Gas	LED ppm min	Animals	ODL ^a ppm ²⁸	Peak in Fire ppm ^{29,30}
CO	192,000 ^b	rats	—	7,450
Acrolein	2,500-5,000 ^c	baboons	0.16	98
HCl	112,000-169,000 ^d	rats	0.77	280
HCl	ca 150,000 ^e	baboons	0.77	280
HCN	4,800 ^f	rats	0.58	9

^aOdor detection level^b30 min exposure, within exposure deaths; Reference 27^c5 min exposure; post-exposure deaths; Reference 21^d30-60 min exposure, post-exposure deaths; Reference 20^e5-15 min exposures, with no deaths; Reference 20^f30 min exposure, within exposure deaths; Reference 26Table 8³⁵Results of Corner Burn Room Fire Test^a

Material	Temp. at door (°C)	Heat generated at 13 minutes (MJ)	Peak smoke at door (OD/m) ^b	Smoke yield (g)	NBS Smoke Dm ^c
Crib only	171	32.6	1.6	106	—
Low smoke rigid PVC	178	25.6	4.6	187	94
Chlorinated PVC	169	30.2	1.5	93	53
Rigid PVC	188	31.7	8.3	384	780
FR Acrylic	322	36.6	>15.1	398	435
FR ABS	748	70.2	>15.1	>900	900
Wood (oak)	558	89.8	9.6	746	106
Polycarbonate	382	133.7	>15.1	>2500	247

^aA 6.3 kg wood crib was used in all experiments.^bOD/m: optical density per meter^cDm: maximum smoke density.HYDROGEN CHLORIDE
DECAY

A series of studies was done to investigate the "lifetime" of HCl in a fire atmosphere.³¹⁻³⁴ These studies showed that HCl reacts very rapidly with most common construction surfaces (cement block, ceiling tile, gypsum board, etc.). Therefore, the peak HCl concentration found in a fire is much lower than would be predicted from the chlorine content of the burning material. Moreover, this peak concentration soon decreases and HCl disappears completely from the air. Figure 7 shows the HCl concentration-time pattern for several identical experiments where PVC

wire insulation (containing the chlorine equivalent of 8,700 ppm of HCl) was electrically decomposed in the presence of sorptive surfaces. The peak concentration of HCl found in this simulated plenum was only 10% of the theoretical concentration.

One of the consequences of these studies is that toxicity tests carried out in glass or plastic exposure chambers may exaggerate the toxicity of PVC smoke. On these surfaces, HCl does not decay as fast as on real-use surfaces, so that toxic gases are present longer than in real fires.

PVC PERFORMANCE IN
LARGE SCALE TESTS

It is probably of much greater importance to understand how PVC behaves in a real full-scale fire than to understand the results of small-scale tests, some of which are of questionable validity. A series of tests was conducted in which a corner, floor to ceiling, was paneled with different materials including wood and rigid PVC. Table 8 shows that the PVC panels added nothing whatsoever to the total heat generated and next to nothing to the temperature measured at the door of the room, as compared to the ignition source itself (a wood crib).³⁵ The smoke emitted by the burning PVC caused the room to become somewhat darker than when the crib burned alone, however, the darkness was much less than that generated when the wood panels were burned. The wood also gave off a very considerable amount of additional heat, much hotter temperatures at the door, and a large mass of smoke particulates. Other materials, with the exception of chlorinated PVC (CPVC), similarly generated much more smoke and heat than the PVC panels.

It is also interesting to note that the smoke yield in the full-scale tests did not correlate with that in the NBS smoke chamber. The reason for this lack of correlation is that the largest smoke yield in the NBS smoke chamber was given by those materials burning least extensively in the large-scale test.

CTL016284

Figure 6

Toxic Potency (Lethal Dose) of Substances and of Smoke (LD ₅₀ in mg/kg)			
100,000 Non Toxic			
10,000 Slightly Toxic	Ethanol (16,000)		
1,000 Moderately Toxic	Ethylbenzene (6,250) Naphthalene (2,500)	CO ₂ (1,400) CFC II (940)	
100 Very Toxic	Methanol (425) Aspirin (250) DDT (130)	Chloroform (300) Ether (273)	Polystyrene Red Oak Douglas Fir
10 Extremely Toxic	Phenobarbital (27) Paraquat (7)	HCl (27) CO (22)	Wool PVC ABS Modacrylic
1	Nicotine (1)		
0.1 Supertoxic	Cocaine (0.5) Strychnine (0.27)	HCN (0.75) TDI (0.5) Acrolein (0.4) Phosgene (0.17)	PTFE (F) PTFE (NF)
0.01	Tiger Snake Poison (0.048) Dioxin (0.025) Beaked Sea Snake Poison (0.012)		
0.001			
0.0001	Botulinus Toxin (0.0002)		
Categories	Poisons	Gases	Smokes


Large-scale experiments have also been carried out to investigate HCl decay. These show that, even if massive amounts of PVC are decomposed in a plenum space above a room, no HCl filters down into the room below unless driven by an air conditioning system, while other gases do accumulate in the room.^{31, 34} Even with an air conditioning system, the concentrations in the room were found to be of virtually no toxicological concern. Consequently, high concentrations of HCl are unlikely to reach rooms other than that of origin and unlikely to affect victims in the post-flashover period.

Two other interesting studies have investigated the effects of burning PVC electrical products behind a wall (non-metallic tubing)³⁶ or a ceiling (conduit, non-metallic tubing, wire coating).³⁷ It was found, in both cases, that the temperatures and concentrations of toxic gases in the room would be lethal long before there would be any effect resulting from the combustion of the PVC products.

SUMMARY

- 1) The most important cause of fire deaths is CO, produced when all organic materials burn.
- 2) PVC is less flammable than most organic materials and it will not continue burning unless there is a powerful external source of heat.
- 3) When PVC eventually burns, it gives off less heat and does so more slowly than most materials.
- 4) The smoke produced by burning PVC is within the same range as that of many other materials.
- 5) The toxicity of PVC combustion products is comparable to that of most organic materials.
- 6) PVC is unusual in that, when it burns, it releases HCl, which is irritating. However, HCl odor is easily detectable (at less than 1 ppm) and HCl does not incapacitate or become dangerous until it reaches concentrations much higher than those measured in real fires.
- 7) HCl is unique among common fire gases in that it decays by reacting very rapidly with most construction surfaces and consequently, is not transported easily to other rooms.

Figure 7

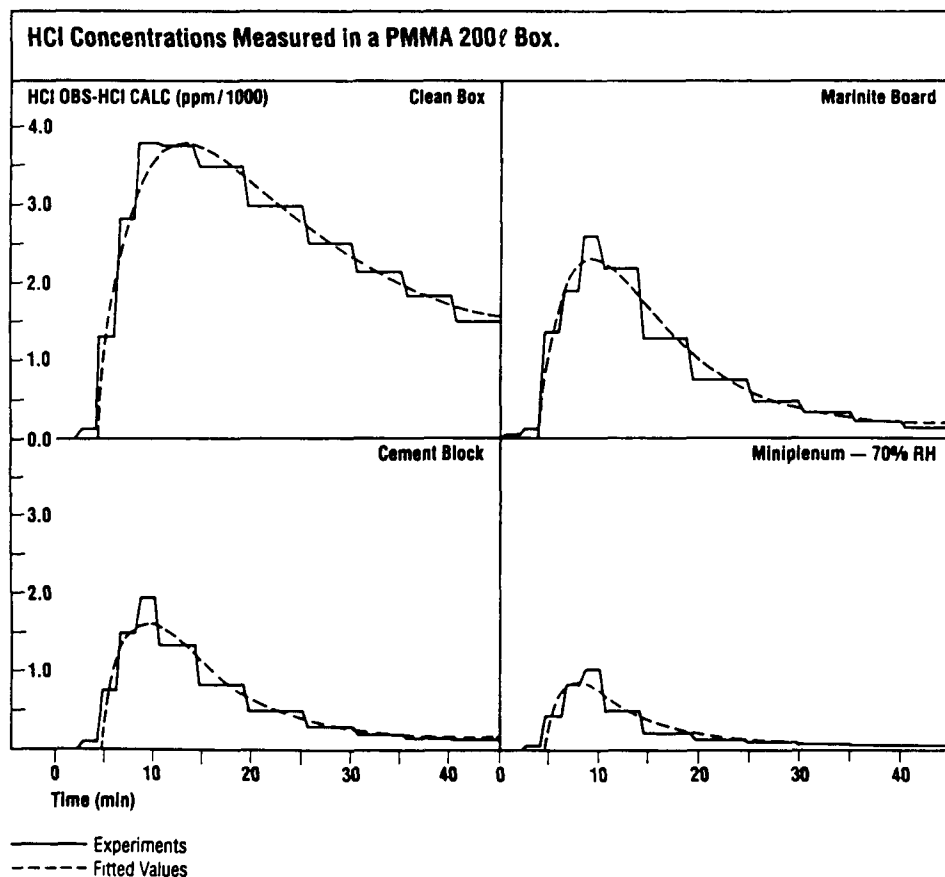

REFERENCES

1. C.F. Cullis and M.M. Hirschler, "The Combustion of Organic Polymers," Oxford University Press, Oxford (1981).
2. M.M. Hirschler, "Developments in Polymer Degradation," Vol. 5, (G. Scott, editor), Applied Polymer, Barking, Chapter 5, p. 102 (1982).
3. C.J. Hilado, "Flammability Handbook of Plastics," 3rd. Ed., Technomic Publishing, Lancaster, PA (1982).
4. M.M. Hirschler, *Journal of Fire Sciences* 5, 289 (1987).
5. J.M. Avento and I. Touval, "Flame Retardants (Antimony)," *Kirk-Othmer Encyclopedia of Chemical Technology*, Vol. 10, 3rd. Ed., Wiley (1980).
6. E.E. Smith, "Ignition, Heat Release and Noncombustibility of Materials, ASTM STP 502," (A.F. Robertson, editor), p. 119, American Society for Testing and Materials, Philadelphia (1972).
7. L.H. Breden and M. Meisters, *Journal of Fire and Flammability*, 7, 234 (1976).
8. V. Babrauskas, *Journal of Fire and Flammability* 12, 51 (1981).
9. J.G. Quintiere, *Fire and Materials*, 6, 145 (1982).
10. V. Babrauskas, SPE RETEC conference on "PVC: THE ISSUES," Atlantic City, p. 41 (1987).
11. G.F. Smith, SPE RETEC conference on "PVC: THE ISSUES," Atlantic City p. 124 (1987).
12. V. Babrauskas, "Development of the Cone Calorimeter. A Bench-Scale Heat Release Rate Apparatus Based on Oxygen Consumption," National Bureau of Standards, NBSIR 82-2611 (1982).
13. V. Babrauskas, "Bench-Scale Methods for Prediction of Full-Scale Fire Behavior of Furnishings and Wall Linings," Society of Fire Protection Engineers, Boston, Technology Report 84-10 (1984).
14. V. Babrauskas, *Journal of Fire Sciences* 2, 5 (1984).
15. V. Babrauskas and J.F. Krasny, "Fire Safety. Science and Engineering, ASTM STP 882" (T.Z. Harmathy, editor), p. 268, American Society for Testing and Materials, Philadelphia (1985).
16. M.M. Hirschler and G.F. Smith, "Fire Safety Progress in Regulations, Technology and New Products," Fire Retardant Chemicals Assoc. Fall Conference Oct. 18-21, Monterey, CA, p. 133 (1987).
17. W.D. Walton and W.H. Twilley, "Heat Release and Mass Loss Rate Measurements for Selected Materials," National Bureau of Standards NBSIR 84-2960 (1984).
18. B.C. Levin, A.J. Fowell, M.M. Birky, M. Paabo, A. Stolte and D. Malek, "Further Development of a Test Method for the Assessment of the Acute Inhalation Toxicity of Combustion Products," National Bureau of Standards NBSIR 82-2532 (1982).
19. L.J. Casarett, "Toxicology - The Basic Science of Poisons," (L. Casarett and J. Doull, editors), Macmillan, New York, p. 24, (1975).
20. G.E. Hartzell, S.C. Packham, A.F. Grand and W.G. Switzer, *Journal of Fire Sciences* 3, 195 (1985).
21. H.L. Kaplan, A.F. Grand, W.G. Switzer, D.S. Mitchell, W.R. Rogers and G.E. Hartzell, *Journal of Fire Sciences* 3, 228 (1985).
22. H.L. Kaplan and G.E. Hartzell, *Journal of Fire Sciences* 2, 286 (1984).
23. K.I. Darmer, E.R. Kinkead and L.C. DiPasquale, *Journal of the American Industrial Hygienists Association* 35, 623 (1974).
24. H.L. Kaplan, R.K. Hinderer and A. Anzueto, *Journal of Fire Sciences* 5, 149 (1987).
25. H.L. Kaplan, M.M. Hirschler, W.G. Switzer and A.W. Coaker, proceedings of the 13th International Conference on Fire Safety (C.J. Hilado, editor), Product Safety Corp., San Francisco, p. 279 (1988).
26. V. Babrauskas, B.C. Levin and R.G. Gann, *Fire Journal*, 81(2), 22 (1987).
27. G.E. Hartzell, A.F. Grand and W.G. Switzer, *Journal of Fire Sciences* 6, 368 (1987).
28. J.E. Amoores and E. Hautala, *Journal of Applied Toxicology* 3, 272 (1983).
29. W.A. Burgess, R.D. Treitman and A. Gold, "Air Contaminants in Structural Firefighting," N.F.P.C.A. Project 7X008, Harvard School of Public Health (1979).
30. A.F. Grand, H.L. Kaplan and G.H. Lee, "Investigation of Combustion Atmospheres in Real Fires," U.S.F.A. Project 80027, Southwest Research Institute (1981).
31. J.J. Beitel, C.A. Bertelo, W.F. Carroll, R.A. Gardner, A.F. Grand, M.M. Hirschler and G.F. Smith, *Journal of Fire Sciences* 4, 15 (1986).
32. C.A. Bertelo, W.F. Carroll, M.M. Hirschler and G.F. Smith, Fire Safety Science, proceedings of the 1st International Symposium (C.E. Grant and P.J. Pagni, editors), p. 1079, Hemisphere, Washington (1986).
33. J.J. Beitel, C.A. Bertelo, W.F. Carroll, A.F. Grand, M.M. Hirschler and G.F. Smith, *Journal of Fire Sciences* 5, 105 (1987).
34. F.M. Galloway and M.M. Hirschler, "Mathematical Modeling of Fires, ASTM STP 983" (J.R. Mehaffey, editor), American Society for Testing and Materials, Philadelphia p. 35 (1987).
35. G.F. Smith and E.D. Dickens, proceedings of the 8th International Conference on Fire Society (C.J. Hilado, editor), Product Safety, p. 227, San Francisco (1983).
36. I.A. Benjamin, *Journal of Fire Sciences* 5, 25 (1987).
37. M.M. Hirschler, *Journal of Fire Sciences* 6, (1988).

This report has been prepared by the Technical Committee of the Vinyl Institute as a service to its members and their customers and is based on literature and information believed to be accurate.

No warranty or guaranty, expressed or implied, is made for the accuracy or completeness of the information provided herein and neither the Vinyl Institute nor its members or contributors assume any responsibility for the accuracy or completeness of the information contained in this document.

CTL016286

RECEIVED
NOV 22 1983
BRUCE J. BROCKA

Figures 1, 3, 4, 5, 6 and 7 reprinted with the permission of the *Journal of Fire Sciences*, ©1987 Technomic Publishing, Lancaster, PA, USA

©1988 The Vinyl Institute