

Transene Company Eliminates its Use of PFAS and Saves Money

TRANSENE COMPANY, INC.

SUMMARY

Transene worked with the Toxics Use Reduction Institute (TURI), the Massachusetts Office of Technical Assistance (OTA), and the University of Massachusetts Lowell (UMass Lowell) to find safer alternatives to PFAS for etching in the semiconductor industry. The research, evaluation, and implementation of the safer alternatives took place over an 18-month period and resulted in cost savings, in addition to a healthier environment for employees and customers.

Transene Company, a manufacturer of advanced materials for the electronics industry, wanted to find viable alternatives to perfluoroalkyl substances (PFAS) use in semiconductor manufacturing in response to customer demands for PFAS-free products. Because PFAS have unique properties that can be difficult to replace, Transene's president, Christopher Christuk, turned to TURI and the University of Massachusetts (UMass) Lowell for help.

PFAS, a class of thousands of chemicals, are often dubbed "forever chemicals" because they never fully break down in the environment. Found in a wide array of consumer and industrial products such as waterproof fabrics, food packaging, dental floss and nonstick cookware, PFAS are associated with numerous health risks, including cancer, liver damage, decreased fertility and increased risk of asthma and thyroid disease.

Surfactants based on PFAS are widely used for etching in the semiconductor industry because they are extremely stable even under strongly acidic and alkaline conditions. Although effective, the toxicity and high persistence of PFAS necessitate their replacement with non-toxic and environmentally friendly alternatives.

The Challenge

PFAS have unique properties that can be difficult to replace in certain applications. In the specific case of semiconductor production, PFAS provides a remarkable reduction of surface tension, improvement of wetting characteristics, compatibility with alkaline and acidic solutions, heat resistance, chemical inertness, and increased etching efficiency.

When looking to replace PFAS for their customers, Transene had a clear list of requirements that any alternative needed to meet. This included:

- **Compatibility:** Strong acidic/oxidizing solutions—nitric acid and phosphoric acid, among others
- **Performance:** Surface tension reduction should be comparable to what is achieved by PFAS surfactants
- **Effectiveness:** Performs at concentrations below 0.1%
- **Less hazardous and toxic:** Contain no highly hazardous chemicals
- **Stability:** Greater than a one-year shelf life

The Process

The research, evaluation, and implementation of the safer alternatives took place over an 18-month period, which began when TURI awarded UMass Lowell Prof. Ramaswamy Nagarajan a research grant. The grant funded a research team that worked with Transene and TURI to find and develop viable alternatives to the use of PFAS in this application. They identified safer solutions and performed experiments to compare the properties of the alternatives.

TURI staff and their research partners at UMass Lowell provided the resources and equipment to test the performance of various alternatives against Transene's requirements.

"This collaboration accelerated our ability to manufacture and sell safer etching products, which helps companies in the electronics supply chain meet new regulatory requirements and protect health and the environment."

— Christopher Christuk, President of Transene Company

Research Approach and Evaluation of Alternatives

After identifying various alternatives that fit the requirements of Transene, the research team evaluated alternatives for toxicity and other potential hazards using TURI's Pollution Prevention Options Analysis System (P2OASys), which allows users to easily compare the relative hazards associated with chemical or process changes. TURI evaluated each of the viable alternatives to ensure that Transene would not be switching to another harmful solution.

Although one chemical alternative ranked as High in terms of its level of hazard, three of the other proposed alternatives fell in the Medium level of hazard according to the P2OASys evaluation, representing a significant improvement over the incumbent PFAS technology. When tested for performance, these replacements performed comparably to PFAS-based formulations, which was verified by the positive user feedback received regarding performance and no reported negative effects on the final products.

Color	Level of Hazard
	Low (L)
	Medium (M)
	High (H)
	Very High (VH)

Benefits and Outcomes

Transene Company provided evaluation samples of the new, safer etching solutions to several of their key customers. After receiving positive test results from their customers, Transene was able to convert customers to the new, safer etching solutions.

Because of TURI's research and innovative solution—designed specifically for Transene—over 90% of their customers in industries such as radio frequency and microwave chips, lasers, aerospace, and defense have switched to using the new, safer etching products without PFAS. Christuk hopes to see 100% customer adoption by the end of 2023.


Not only did replacing PFAS result in safer products for customers and a safer workplace for workers, the safer alternative identified by TURI and partners also benefitted Transene's bottom line. The alternative resulted in an ongoing cost savings as well: the PFAS-based surfactants cost \$2,400 per gallon, but the new safer surfactants cost only \$80 per gallon.

TURI developed the Pollution Prevention Options Analysis System (P2OASys) tool to help companies determine whether the toxics use reduction (TUR) options they are considering improve upon their existing process when looking at environmental, health and safety endpoints. By using P2OASys, unforeseen negative environmental, worker or public health impacts may be identified prior to adopting the proposed changes.

Potential hazards posed by current and alternative processes identified during the TUR planning process are compared using data endpoints for eight main categories that encompass chemical, physical, psychological and environmental hazards.



The Toxics Use Reduction Institute (TURI) at UMass Lowell provides the resources and tools to help Massachusetts companies and communities make the Commonwealth a safer place to live and work. Established by the state's Toxics Use Reduction Act of 1989, TURI provides research, training, technical support, laboratory services and grant programs to reduce the use of toxic chemicals while enhancing the economic competitiveness of Massachusetts businesses. Learn more at <http://www.turi.org> or contact info@turi.org.



Safer and effective alternatives to perfluoroalkyl-based surfactants in etching solutions for the semiconductor industry

Rashmi Sharma^{a,1}, Shreyas Shelke^{b,1}, Mohammad Bagheri Kashani^{b,1}, Gregory Morose^c, Christopher Christuk^d, Ramaswamy Nagarajan^{b,*}

^a Department of Chemistry, University of Massachusetts Lowell, Lowell, MA, 01854, USA

^b Department of Plastics Engineering, University of Massachusetts Lowell, Lowell, MA, 01854, USA

^c Toxics Use Reduction Institute (TURI), Lowell, MA, 01852, USA

^d Transene Company Inc., Danvers, MA, 01923, USA

ARTICLE INFO

Handling Editor: Zhen Leng

Keywords:

PFAS
Surfactant
Etching
Semiconductor
Alkyl polyglucoside
Pluronic

ABSTRACT

Surfactants based on poly and perfluoroalkyl substances (PFAS) such as Fluoroalkyl sulfonamide, fluoroalkyl sulfonyl amino propane sulfonic acid, and potassium perfluorooctane sulfonate surfactants are widely used in etching solutions in the semiconductor industry to improve the wetting characteristics of the etchant and substrates.

Their excellent stability in strongly acidic, alkaline, and oxidizing etching solutions such as Tetramethyl ammonium hydroxide (TMAH), perchloric acid/ceric ammonium nitrate aqueous solution (chrome), ammonium hydrogen fluoride solution, or buffered oxide etchant (BOE) and a mixture of phosphoric, acetic, and nitric acid etchant (PAN), has warranted their continuous use as a surfactant.

The toxicity and extremely high persistence of PFAS necessitate their replacement with less toxic and effective alternative surfactants.

A generic methodology is described for the identification of safer alternative surfactants and the experimental validation of properties to facilitate the drop-in replacement of these safer surfactants in etching solutions for the semiconductor industry. Hydrophilic-Lipophilic Balance (HLB) values, critical micelle concentration (CMC), compatibility, and wetting characteristics of etchants were analyzed on substrates relevant to the semiconductor industry.

Biobased *BG10* alternative surfactant outperformed PFAS surfactant in improving the wetting characteristics of the TMAH etchant on substrates of interest as evidenced by the significantly lower contact angle. The wetting characteristics of the PAN and BOE etchants containing *BG10* and *CG50* surfactants were comparable to PFAS surfactants.

Toxicity comparisons indicated that these alternatives are far less hazardous to human health than PFAS. These safer alternatives have been tested successfully by over 100 semiconductor companies. These companies have provided positive feedback with no reported deleterious effects on the final products. This successful approach opens new possibilities for the replacement of PFAS in numerous other applications where PFAS is commonly used as a surfactant. Using this methodology, alkyl polyglucosides with trade names *BG10* and *CG50* and polyoxyethylene surfactants of *Brij35* and *BrijS100* were identified as alternatives to PFAS surfactants.

1. Introduction

Poly and Per-fluoroalkyl substances (PFAS) refer to a large class of more than a hundred distinct compounds that contain at least one fluorine atom (Buck et al., 2011). Due to their unique characteristics,

PFAS are widely used in the production of various consumer goods such as food packages, firefighting foams, omniphobic textiles, paints, sealants, and pesticides (Glüge et al., 2020; Kissa, 2001).

Fluorinated surfactants, which constitute a prominent subgroup of PFAS, consist of hydrophobic fluorinated chains and hydrophilic

* Corresponding author.

E-mail address: ramaswamy.nagarajan@uml.edu (R. Nagarajan).

¹ Authors contributed equally.

headgroups. The remarkable properties of PFAS surfactants stem from the high electronegativity, low polarizability, and reduced size of fluorine atoms, resulting in robust C–F bonds, feeble intermolecular forces within –CF₂–, and potent hydrophobic interactions. As a consequence, these surfactants exhibit exceptional traits, such as high chemical and thermal stability, strong surface activity, high wetting ability, and incompatibility with both water and hydrocarbons (Kancharla et al., 2022). Fluorinated surfactants lower the surface tension of water (from around 72 mN/m to less than 16 mN/m) beyond the threshold at which hydrocarbon-type surfactants cease to function (Alexander et al., 2014). The hydrophobic group being extremely resistant to chemical attack, the fluorinated surfactants may be used in conditions where conventional surfactants do not survive (Gaines, 2022). Fluorosurfactants are far more expensive per unit volume compared to conventional hydrocarbon surfactants due to their high production costs (Farn, 2006), therefore, they are frequently used in situations where other substances cannot provide the desired performance or where PFAS can be used in much smaller amounts while still maintaining the same performance as a larger amount of a non-fluorinated chemical (Buck et al., 2012).

The many advantageous characteristics of PFAS have led to their extensive use as surfactants in etching solutions within the semiconductor industry (Ober et al., 2022) where PFAS surfactants are used to improve the wettability of the etching solutions and the substrates while remaining stable in a strong acidic to alkaline etching solutions (Tansel, 2022).

However, PFAS exhibit exceptional stability for extended periods, potentially spanning hundreds of years (Mahinroosta and Senevirathna, 2020), which accounts for their ubiquitous occurrence in various disposable products like cosmetics (Whitehead et al., 2021), agricultural commodities (Scher et al., 2018), and abandoned food packages (Cousins et al., 2020). Additionally, PFAS have been detected in different environmental segments, including drinking water (Quinones and Snyder, 2009), rainwater, and groundwater (Guardian et al., 2020; Daly et al., 2018), promoting bioaccumulation and biomagnification in many existing species (Genualdi et al., 2022) as well as humans (Carriosa et al., 2021; Zhou et al., 2021). Studies have investigated the health effects of human populations unknowingly exposed to PFAS, with complications ranging from premature skin aging (Mousavi et al., 2021), malignancies, higher cholesterol levels, and impaired immunological and liver functions, to serious birth abnormalities (Bonefeld-Jørgensen et al., 2014).

Numerous industries have transitioned from utilizing long-chain fluorosurfactants, specifically perfluoro octane sulfonic acid (PFOS), to shorter-chain fluorinated surfactants in order to decrease the persistence of the surfactants (Wang et al., 2013). Nevertheless, this substitution strategy is not sustainable given that the shorter-chain per- and poly-fluoroalkyl substances (PFAS) are also deemed hazardous to human and environmental health (Brendel et al., 2018). Further studies have demonstrated that short-chain PFAS are even more mobile in the environment and more difficult to remove from drinking water than long-chain PFAS (Sun et al., 2016; Cousins et al., 2016). The revelation of these human health problems has prompted the Stockholm Convention to prohibit the manufacture of long-chain PFAS (Radley-Gardner et al., 2016), which highlights the urgency of finding safer alternatives for these substances.

In this study, the aim is to develop a methodology for the replacement of PFAS surfactants utilized in etching solutions in the semiconductor industry. In pursuit of this objective, the safer alternatives identified should perform similarly to the PFAS surfactants that are being replaced.

The hydrophilic-lipophilic balance (HLB) of surfactants was considered the primary criterion for the preliminary selection of potential replacements for PFAS. (Sassi et al., 2020). The surfactants must be compatible with the etching solutions for prolonged times. Therefore, a three-month compatibility test was performed to assess stability in and compatibility with etching solutions. Subsequently, the surface tension

of the etching solutions containing alternative surfactants was measured, to evaluate their ability to reduce the surface tension of the etchants, effectively. The critical micelle concentrations were calculated from the surface tension versus concentration plot. This was compared to etchant solutions containing PFAS as the surfactant (Perinelli et al., 2020). The main objective of using surfactants in the etching solutions in the semiconductor industry is to improve the wettability of the etchants and substrates. Therefore, contact angle measurements were carried out to evaluate the performance of the alternative surfactants in improving the wettability of substrates. (Nasalapure et al., 2021; Abdullah et al., 2022). Since the replacements are aimed to be less toxic than PFAS surfactants, preliminary toxicity assessment comparisons were carried out using the P2OAsys toxicity assessment tool. The safer alternative was designed to be a 'drop-in' replacement for PFAS surfactant that can be utilized at the industrial scale. Industrial trials were performed using a quality-tracking method with manufacturers in the semiconductor industry - the main consumers of these etching solutions.

Fig. 1 illustrates a generic methodology for the identification of safer and effective alternative surfactants for etching solutions in semiconductor industry, based on the fundamental characteristics of the surfactants employed and their intended application as described in the method section.

2. Experimental

2.1. Materials

2.1.1. Etching solutions

Four different types of etching solutions were used to examine the alternatives for PFAS surfactants. Tetra methyl ammonium hydroxide or TMAH (2.38% w/v aqueous solution) with the trade name of *Novo Developer 342*, prepared with a low metal grade TMAH concentrate from Transene Company Inc. with a weight ratio of 25% w/w was used.

Perchloric acid/ceric ammonium nitrate aqueous solution, commercially available as *Chrome Etchant 9051*, prepared by Transene Company Inc., with the perchloric acid content of 5.2% w/w from ACS Reagent and ceric ammonium nitrate content of 7.5% w/w from Ganzhou Wanfeng Advanced Materials Technology Co., Ltd was also included.

Buffered oxide etchant commercially available as *BOE Etchant* is referenced as BOE X: Y where X is the volume ratio component of Ammonium Fluoride 40% (w/w) (Transene low metal grade), and Y is the volume ratio component of Hydrofluoric Acid 49% (w/w) (Transene low metal grade) was used. In this study, the alternative surfactants were tested in a 6:1 vol ratio.

PAN Etchants, or Phosphoric Acid-Acetic Acid-Nitric Acid solutions, was used with the trade name *PAN Etch Special*, with the ratio of 17-1-1-2, where numeric values are based on volumes of digit 1: 85% Phosphoric Acid (w/w) Transene low metal grade, digit 2: Acetic Acid Transene low metal grade, digit 3: 69–70% Nitric Acid (w/w) Transene low metal grade, digit 4: Deionized Water were all used as received.

2.1.2. PFAS surfactants

The PFAS-based surfactants Fluoroalkyl sulfonamide (*Novec 4200*), fluoroalkyl sulfonyl amino propane sulfonic acid (*Novec 4300*), and potassium perfluorooctane sulfonate surfactants (*FC95*) were all purchased from 3M Company and used as received.

2.1.3. Alternative surfactants

Alkyl polyglucosides or APG-based surfactants - *Triton BG10*, *Triton CG50*, and *Triton CG110* were purchased from DOW Chemicals and were used as received. *Brij 35*, a lauryl polyethylene glycol ether-based surfactant, was obtained from ThermoFisher Scientific Company and was utilized without any further processing. Other polyoxyethylene surfactants *Brij 58* (polyethylene glycol hexadecyl ether) and *Brij S100* (polyethylene glycol ether of stearyl alcohol) were obtained from Sigma-

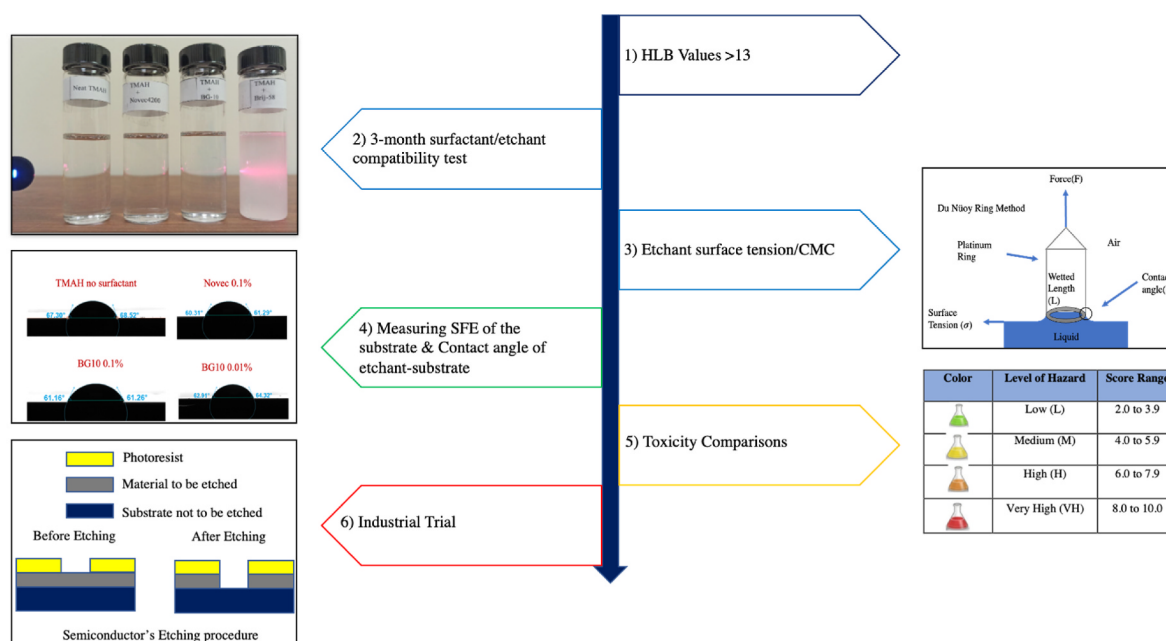


Fig. 1. Schematic of the methodology for finding safer and effective alternative surfactants for PFAS surfactants.

Millipore USA and were used as received.

2.1.4. Semiconductor substrates

Four substrates, commonly used in the semiconductor industry, were obtained to carry out the surface free energy measurements. Photoresist-coated silicon wafers, the aluminum oxide-coated and chromium-coated silicon wafers as well as the glass substrates were provided by Kemlab™ Inc., and Transene Company, Inc. respectively. The substrates were all used as received and were selected based on the recommendations of Transene Company Inc.

2.2. Test methods and parameters

2.2.1. HLB values

Hydrophilic-lipophilic balance (HLB) is one of the most commonly used metrics for comparing surfactants and their performance. The values range from 0 to 20 from highly lipophilic in the range of 0–6, and highly hydrophilic for higher than 13. The values for commercially available alternative surfactants that were investigated for this work have been obtained from technical data sheets of the vendor websites. Surfactants for etching solutions in semiconductor industries must be compatible with aqueous and polar systems. Therefore, for this work, surfactants with HLB values higher than 13 are chosen.

2.2.2. Compatibility test

A three-month compatibility test was carried out to make sure the alternative surfactants exhibit similar properties including stability in these etching solutions. For this purpose, etching solutions containing 0.1 and 0.01 wt% alternative surfactants were prepared. Maintaining a clear solution without phase separation was the desired result for ensuring compatibility. A semiconductor laser beam was passed through vials containing etching solutions with surfactant alternatives to observe if there was the scattering of light (due to turbidity) caused by potential incompatibility.

2.2.3. Surface tension and critical micelle concentration (CMC)

Surface tension measurements were conducted using the Du Nöuy ring method as described in ASTM D1331-11 'Standard Test Methods for Surface and Interfacial Tension of Solutions of Surface-Active Agents'-Method A. Measurements were carried out at room temperature (24 °C)

using a KSV Sigma 70 surface tensiometer that was calibrated with deionized water before use. Each test was repeated five times. The reference value for the interfacial tension of water/air at 24 °C is around 72 mN/m. Before use, the Du Nöuy ring and the glass container were thoroughly cleaned by rinsing in deionized water, and finally, the ring was flame dried using a propane gas burner. Surface tension was measured three times for each concentration. The average error of <0.5 mN/m was regularly obtained. The CMC is calculated as the point where the baseline surface tension intersects with the linearly declining slope.

2.2.4. Surface free energy (SFE) and wettability through contact angle measurements

Owens-Wendt-Rabel-Kaelble (OWRK) method was utilized to calculate the surface free energy of the substrates. This was achieved by measuring the contact angle of multiple distinct liquids using ASTM D5946. This method sums up the polar dispersive components of the interaction (K. L. Mittal, 2009) and provides information on the overall surface free energy and its constituents.

The liquid surface tension, γ_{LV} , is the sum of a dispersive component (γ_{LV}^D e.g., London dispersion forces) and polar component (γ_{LV}^P e.g., hydrogen bonding) such that $\gamma_{LV} = \gamma_{LV}^D + \gamma_{LV}^P$. Likewise, the solid SFE, γ_{SV} , is the sum of dispersive and polar components such that $\gamma_{SV} = \gamma_{SV}^D + \gamma_{SV}^P$. The relationship between liquid surface tension, solid surface free energy, and the contact angle between the liquid and the solid is described by the Owens-Wendt-Rabel-Kaelble (OWRK) equation (K. L. Mittal, 2009):

$$\gamma_{LV}(1 + \cos\theta) = 2[(\gamma_{SV}^D \gamma_{LV}^D)^{1/2} + (\gamma_{SV}^P \gamma_{LV}^P)^{1/2}]$$

where θ is the contact angle between the liquid and the solid. It should be noted that the polar and dispersive parameters used to calculate the surface free energy of the solid in equation 1, were determined by the Biolin Scientific apparatus. These were used in the OWRK equation to obtain the final surface free energy of the substrates.

It should be noted that the Photoresist-coated silicon wafer substrate is etched by TMAH etching solution, while etching of the aluminum oxide-coated silicon wafer is carried out using PAN etchant. The chrome etching solution is utilized to etch a chromium-coated silicon wafer and BOE etchant for the glass substrate.

To measure the contact angle of the etching solutions on substrates

and estimate the surface free energy of the substrates, the Biolin Scientific Attension Theta Flex apparatus was used, and the ASTM D5946 test method was followed. Diiodomethane, glycerol, and deionized water were used to measure the surface free energy of the substrates.

2.2.4.1. Statistical analysis of the contact angle measurements. The contact angle measurements were subjected to statistical analysis to determine the significance of the observed variations. An initial one-way analysis of variance (ANOVA) (Zar, 2010) was employed to compare the means of the contact angles across the three groups of etching solutions with no surfactant, with PFAS surfactants, and with alternatives. ANOVA is a robust statistical technique used to assess differences between groups and determine the presence of statistically significant variations. Subsequently, post hoc comparisons were conducted using Tukey's Honestly Significant Difference (HSD) (Fowler et al., 1998), and a test significance level of $p = 0.05$ was adopted to establish statistical significance. Analyses were conducted using the statistical package SPSS v. 20.0.

2.2.5. Toxicological assessment

To evaluate the safety of the alternative surfactant chemicals, a chemical hazard assessment using the P2OASys tool was conducted. The P2OASys tool evaluates data from the following eight categories: acute human effects, chronic human effects, ecological hazards, environmental fate/transport, atmospheric hazards, physical properties, process factors, and life cycle factors.

Each category includes several subcategories. For instance, the "Acute Human Effects" category includes the following nine subcategories: inhalation toxicity, oral toxicity, dermal toxicity, respiratory irritation, dermal irritation, eye irritation, exposure limits, IDLH, and health. Under each subcategory, there are various endpoint options to be completed, for example, a toxicity value from animal studies, a GHS category, or an authoritative body's designation. The tool rates each category based on the information entered for each endpoint within the category. For subcategories that have multiple endpoints, the tool chooses the endpoint with the highest hazard score and assigns that score to the subcategory. At the category level, the tool calculates the average of the two highest hazard values from the subcategories. This average becomes the numerical rating for the category. The overall P2OASys product score is an average of each of the eight categories (Toxics Use Reduction Institute, 2021). This ranking is shown in Table 1.

2.3. Industrial trial

The performance of safer alternative surfactants was evaluated at the industrial scale in collaboration with Transene Company, Inc. The results were followed over several months in a quality-tracking program with consumers in the electronics industry. The quality-tracking procedure is a 'drop-in' method that involves the complete replacement of

the PFAS surfactants with safer alternatives in a pass-or-fail approach. This means that if any key characteristics of the etching solutions including the wettability of the etchant and substrate, shelf-life, or even the physical appearance of the etching solution is impaired by using the PFAS-free surfactants, the alternative surfactant is considered to be a failure.

3. Results

3.1. HLB values

HLB values for BG10, CG50, and CG110 are above 13, and for Brij 35, Brij 58 and Brij S100 are 16.9, 15.7, and 18.8 respectively, as shown in Table 2.

3.2. Compatibility of alternative surfactants with various etchants

The results of a 3-month compatibility test are presented in Table 3, which examines the performance of surfactants used in etching solutions. PFAS surfactants remained transparent and clear throughout the test, indicating compatibility. BG10 in PAN and TMAH, CG50 in BOE and Brij35, and BrijS100 in chrome etchant remained transparent and clear. As shown in Fig. 2, Brij58 was cloudy, in TMAH, PAN, and BOE and with suspending precipitates in the chrome etching solution.

3.3. Surface tension measurements

The surface tension measurement data for each surfactant (PFAS and alternatives) are depicted in Fig. 3. Both PFAS and alternative surfactants reduced the surface tension of the etching solutions.

The surface tension reductions for all etching solutions were compared at 0.1 wt% of PFAS and alternative surfactants.

As shown in Fig. 3a, BG10 reduced the surface tension of the TMAH etching solution to 31.1 mN/m, while Novec 4200 reduced it from 73.4 mN/m to 64.5 mN/m.

Fig. 3b demonstrates that Novec 4300 decreased the surface tension of PAN etchant from 61.5 mN/m to 31.0 mN/m while BG10 reduced it to 40 mN/m.

Fig. 3c reveals that CG50 surfactant reduced the surface tension of BOE from 85.7 mN/m to 28.8 mN/m, while Novec 4200 surfactant reduced it to 22.1 mN/m.

Fig. 3d demonstrates that the surface tension of chrome etchant was decreased from 74.6 mN/m to 31.8 mN/m, using Brij 35, while FC95 reduced it to 61 mN/m.

As shown in Fig. 3e, Brij S100 reduced the surface tension of the chrome etching solution from 74.6 mN/m to 36.37 mN/m while FC95, it was reduced to 70 mN/m.

3.4. Critical micelle concentration values

The CMC values for Novec 4200 in TMAH and BOE etchants were 5.33, and 5.13 mg/ml, respectively, for Novec 4300 in PAN was 6.14 mg/ml, for BG10 it was 3.21 mg/ml in TMAH and 4.72 mg/ml in PAN respectively, and for CG50 in BOE was 1.9 mg/ml. In the chrome etching solution, it was 0.04 mg/ml, 0.1 mg/ml, and 0.02 mg/ml for Brij35, Brij

Table 1
P2OASys Scoring Scale.

Color	Level of Hazard	Score Range
	Low (L)	2.0 to 3.9
	Medium (M)	4.0 to 5.9
	High (H)	6.0 to 7.9
	Very High (VH)	8.0 to 10.0

Table 2
HLB values of the potential alternative surfactants.

Surfactant Family	Surfactant Trade Name	HLB value
Polyoxyethylene	Brij 35	16.9
	Brij 58	15.7
	Brij S100	18.8
	Brij 35	16.9
Alkyl Polyglucoside	BG10	13
	CG50	13.5
	CG110	13.5
	Brij 35	16.9

Table 3
Etching solutions and their compatible surfactants.

Parameter	Etchant			
	BOE	Chrome	PAN	TMAH
pH	pH = 3-5	pH < 1	pH < 2	pH = 13-14
Color	Colorless	Orange	Colorless	Colorless
PFAS-based surfactant	Novec 4200	FC95	Novec 4300	Novec 4200
Compatible Surfactant	CG50	Brij 35 Brij S100	BG10	BG10
Alternative Surfactant				
Incompatible alternative surfactant	Brij35, Brij58, BrijS100 BG10, CG110	Brij58, BG10, CG50, CG110	Brij35, Brij58, BrijS100, CG50 CG110	Brij35, Brij58, BrijS100 CG50, CG110

S100 and FC95 respectively (see Table 4).

3.5. Contact angles of etchant-substrates containing PFAS and alternatives at CMC values

As shown in Fig. 4 the addition of surfactants to the TMAH decreased the contact angle values. 0.1 wt% of Novec 4200 and BG10 decreased the contact angle from 68° with no surfactant (Fig. 4a) to 61° as shown in Fig. 4b and c. The addition of 0.01 wt% of BG10 surfactant reduced the surface tension of the etching solution to 63°.

As shown in Table 5, the contact angle of TMAH decreased from 65.1° with no surfactant to 61.1° with Novec4200, while BG10 reduced it to 32.1°. The contact angle for the PAN etchant with no surfactant was 37.2° and reduced to 28.6° and 33.4° with the addition of Novec4300 and BG10, respectively.

The contact angle for the BOE etchant were measured to be 34.5° with no surfactant and was reduced to 30.7° and 31.3°, upon addition of Novec4200 and CG50 respectively.

3.6. Surface free energy comparison for the semiconductive substrates

Table 6 illustrates the data accumulated on the surface free energy of each substrate.

The highest surface free energy is for the chromium-coated silicon wafer with 72.6 mN/m and the lowest surface energy is shown by the glass substrate which is 35.4 mN/m. The surface energy of the Aluminum oxide-coated, and photoresist-coated silicon wafers are 53.9 mN/m, and 61.1 mN/m, respectively.

3.7. Chemical hazard classification of the potential alternative surfactant chemicals

The P2OASys scoring system ranks chemicals on a scale between 2

and 10, with lower scores given to safer chemicals and higher scores for more hazardous chemicals.

The toxicity scores shown in Table 7 are 7.3 for Novec 4200, 4.5 for BG10, CG50 and CG110, 5.9 for Brij 35 and 5.3 for Brij35 and BrijS100.

3.8. Industrial trials

Over 100 semiconductor companies have conducted drop-in replacement of the PFAS surfactants with alternatives BG10 in TMAH and PAN etchant, CG50 in BOE etchant, and Brij35 and BrijS100 in the chrome etchant, and reported no adverse effects on the final products.

4. Discussion

4.1. Selection of potential safer alternative surfactants

The HLB value is proportional to the ratio of polar to nonpolar sites of the molecule (Golodnizky and Davidovich-Pinhas, 2020) and indicates the surfactant's solubility preference in either oil or water, resulting in the formation of either a water-in-oil or oil-in-water emulsion. Surfactants with low HLB numbers exhibit a higher solubility in oil, while surfactants with high HLB numbers demonstrate a greater solubility in water (Kunjappu and Rosen, 2012). The etching solutions commonly used in the semiconductor industry are predominantly aqueous-based (up to 75% for TMAH, BOE, and chrome etchants) and highly polar in nature (PAN etchant which is a mixture of phosphoric acid, acetic acid, and nitric acid). PFAS-based surfactants are quite soluble in the etching solutions. The alternative surfactants must exhibit similar behavior in these etching solutions. As higher HLB values indicate higher solubility in water or polar solutions, the alternative surfactants must preferably have HLB values higher than 13 (Cheng et al., 2020). Therefore, alkyl polyglucoside surfactants BG10, CG50, and CG110, along with the polyoxyethylene surfactants Brij35, Brij58, and Brij S100, were selected to undergo etchant compatibility testing based on their higher hydrophilicity and improved solubility in polar and aqueous etching solutions.

In the 3-month compatibility test, it was observed that the biobased surfactant CG50 exhibited transparency and demonstrated compatibility with the BOE etching solution. Notably, the polyoxyethylene surfactants Brij35 and Brij S100 formed stable solutions in the chrome etchant. Furthermore, the biobased alkyl polyglucoside surfactant BG10 showed compatibility with TMAH and PAN etching solutions.

Surfactants that exhibited incompatibility, as indicated by turbidity or precipitation in all etching solutions, (e.g., Brij58 and CG110), were excluded from further consideration as potential alternatives.

Fig. 5 shows the molecular structure the potential alternative surfactants from the HLB value and compatibility data results.

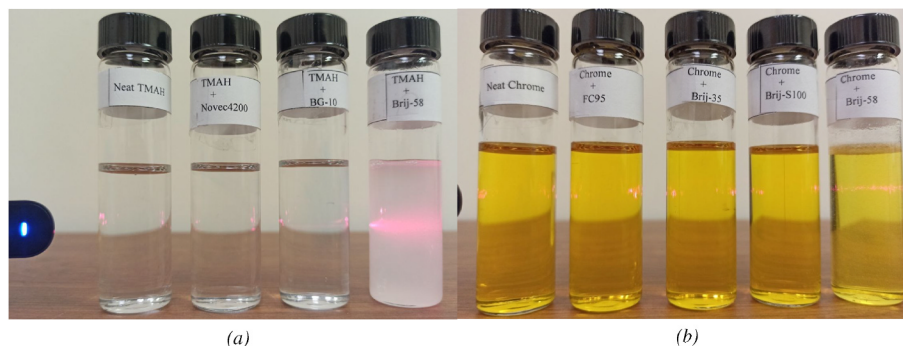


Fig. 2. a. left to right: Neat TMAH etching solution, stable TMAH etching solution with 0.01 wt% of (PFAS surfactant Novec 4200, safer alternative BG10), and TMAH solution with Brij 58 (incompatible). b. left to right: Neat chrome etchant, stable chrome etching solution with 0.01 wt% of (PFAS surfactant FC95, safer alternatives Brij 35, and Brij S100) and chrome solution with Brij 58 (incompatible).

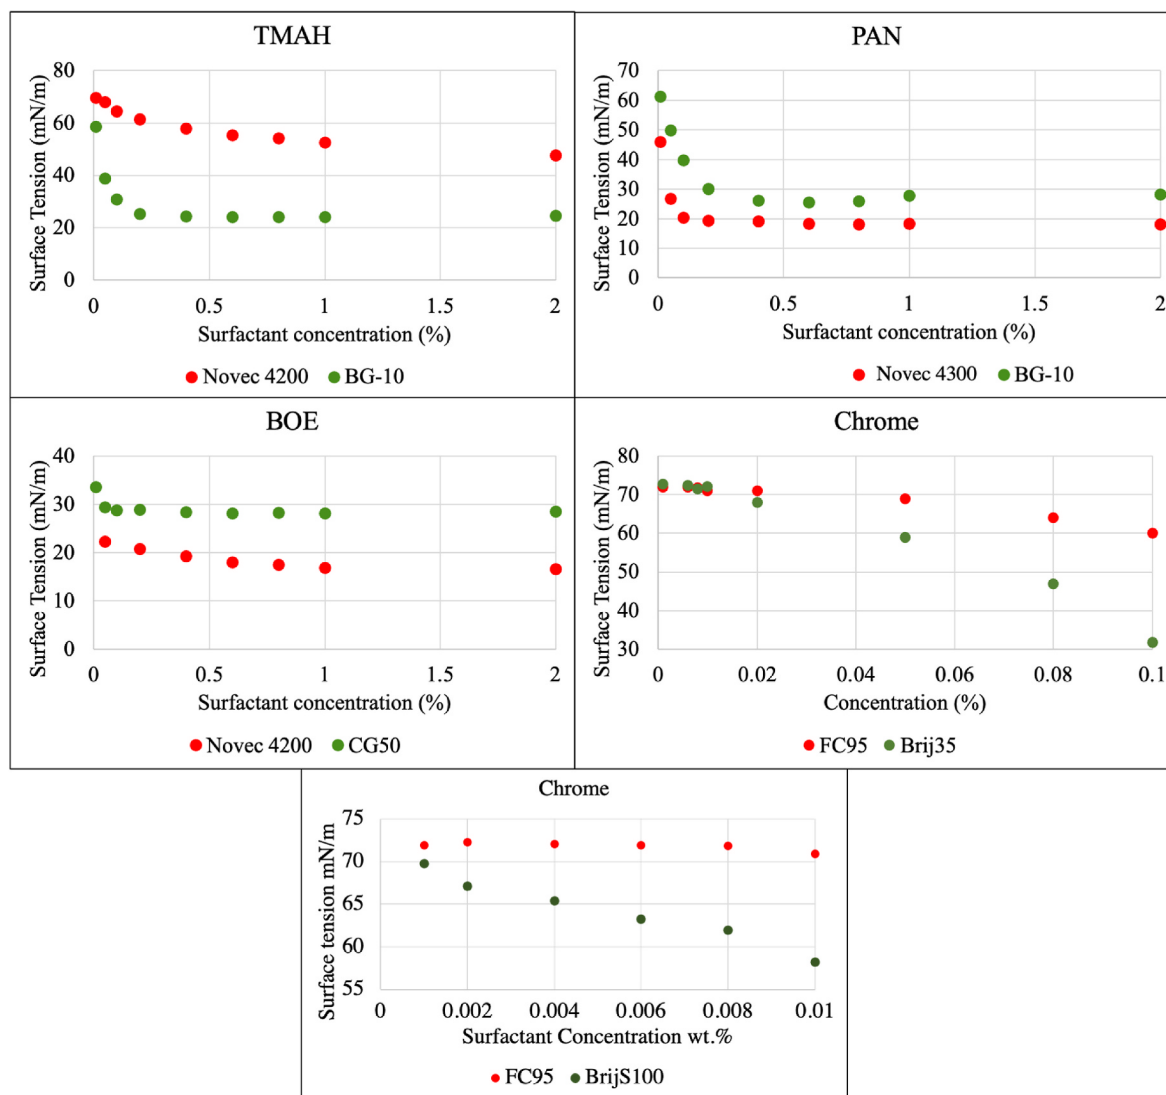


Fig. 3. The surface tension of the etching solution in various PFAS and Alternative surfactant concentrations for (a). TMAH (b). PAN (c). BOE (d) & (e). Chrome etching solutions.

Table 4

CMC values for PFAS and alternative surfactants in the different etching solutions.

Etching solution	CMC (mg/ml)			
	PFAS		Alternative	
TMAH	Novec 4200	5.33 (0.05) ^a	BG10	3.21 (0.07)
PAN	Novec 4300	6.14 (0.06)	BG10	4.72 (0.07)
BOE	Novec 4200	5.13 (0.07)	CG50	1.90 (0.04)
Chrome	FC95	0.02 (0.002)	Brij35	0.04 (0.002)
Chrome	FC95	0.02 (0.002)	Brij S100	0.1 (0.01)

^a Data represent the mean and $\pm$ the standard error.

4.2. Evaluation of the alternative surfactants

Substrate wettability is a key component of etching solutions especially when etching complex geometries or high aspect ratio structures. Etching a straight line might be accomplished using an etchant without a surfactant. But if the chip design necessitates a 90° turn, many etch solutions cannot penetrate the sharp corners. Surfactants can assist in achieving better wettability and coverage of the substrate. Similarly, it may be necessary to etch the sides and bottom of a via or hole in a chip. If

the via has a high aspect ratio (depth vs. diameter), it may be difficult for the etchant to penetrate the via for complete etching. The surfactant in this case is critical in allowing for full etching of the sides and bottom of the via. To ensure that the etching solution wets the solid substrate, the surface free energy of the substrate must be higher than the surface tension of the etching solution and the contact angle between the etchant-substrate must be lower than 90°. (Jothi Prakash and Prasanth, 2021). In this study, since the surface free energy of the substrates are constant, the ability of the surfactant in reducing the surface tension and the contact angle is critical for improving the wettability.

Among alternative surfactants, BG10 in TMAH, Brij35, and BrijS100 in chrome showed superior performance in regard to reducing surface tension compared to PFAS surfactants. As shown in Fig. 3a, the addition of BG10 brought the surface tension down by 57% compared to that of Novec 4200, which affected it only by 12%. Brij35 and BrijS100 in chrome also outperformed PFAS surfactant, FC95. As demonstrated in Fig. 3d the same concentrations of the surfactants Brij 35 and BrijS100 lowered the surface tension by 42% and 52%, respectively compared to that of FC95 which lowered it by only 18%.

In other conditions, such as BG10 in PAN and CG50 in BOE are marginally or less effective compared to that of PFAS. BG10 reduced the surface tension of the PAN solution by 35% while Novec4300 reduced it

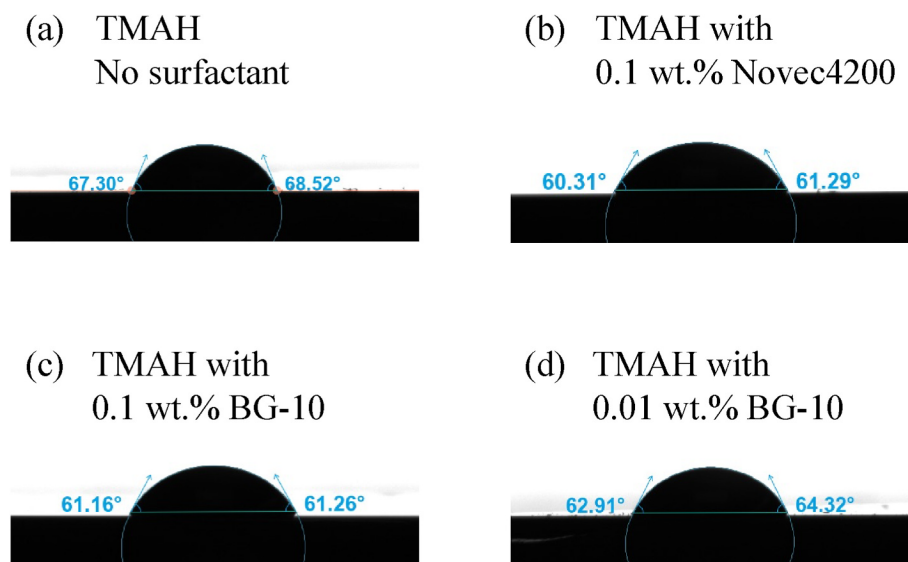


Fig. 4. The contact angle between the photoresist-coated substrate and TMAH etching solution: a. with no surfactant, b. with 0.1 wt% PFAS surfactant *Novec 4200*, c. with 0.1 wt% safer alternative *BG10*, d. with 0.01 wt% *BG10*.

Table 5

The contact angle between the etchants and substrates at CMC values of the surfactant.

Etching Solution	Contact Angle (°)			
	PFAS surfactant	Alternative surfactant		No surfactant
TMAH	Novec4200	61.1 ^b	BG10	32.1 ^c
PAN	Novec4300	28.6 ^b	BG10	33.4 ^{ab}
BOE	Novec4200	30.7 ^b	CG50	31.3 ^{ab}
				34.5 ^a

*Means analyzed with ANOVA and differences separated with Tukey HSD. Values not sharing the same letter indicate a significant difference ($P < 0.05$).

Table 6

Surface free energy of the substrates.

Substrate	Etchant	Surface free energy of the substrates (mN/m)
Aluminum oxide coated silicon wafer	PAN	53.9 (2.1) ^a
Chromium-coated silicon wafer	Chrome	72.9 (3.1)
Photoresist-coated silicon wafer	TMAH	35.4 (4.3)
Glass	BOE	61.52 (3.3)

^a Data represent the mean and $\pm$ the standard error.

Table 7

P2OASys scoring scale.

Chemical	P2OASys Score 10 – Very High Hazard 2 – Low Hazard	Role
3M Novec 4200 Perfluoroalkyl substance (CAS# 484024-67-1)	7.3 High Hazard	Baseline, PFAS chemical to be replaced
Brij 35 Laurel polyethylene glycol ether (CAS# 9002-92-0)	5.9 Medium Hazard	Safer alternative to evaluate
Brij S100 Polyoxyl stearyl ether (CAS# 9005-00-9)	5.3 Medium Hazard	Safer alternative to evaluate
Triton BG10, Triton CG50, and Triton CG110 Decyl octyl glucoside (CAS# 68515-73-1)	4.5 Medium Hazard	Safer alternative to evaluate

by 48%. *CG50* was comparable to the performance of *Novec 4200* in BOE. As shown in Fig. 3c *CG50* affected the surface tension by 66% while *Novec 4200* brought it down by 73%.

Reducing surface tension lowers contact angle resulting in better wettability. The contact angle measurements of etching solutions containing PFAS surfactants, and the alternatives demonstrate the effect of those surfactants on the wettability of the etching solutions and substrates of interest.

BG10 outperformed *Novec4200* in the TMAH etching solution, with a contact angle value of 32.1° compared to 61.1°. The analysis of variance calculations for the TMAH etching solution with no surfactant compared to *Novec4200* and *BG10* resulted in different superscript letters for all three groups. *BG10* superscript letter is “c” compared to “b” for PFAS which confirms that *BG10* performs significantly better than *Novec4200* in improving the wettability of the TMAH.

CG50 performed comparable to *Novec4200* in the contact angle measurements of BOE etchant. The contact angles for the BOE containing *Novec 4200* and its alternative *CG50* were found to be 30.7° and 31.3°, respectively. The superscript “ab” on the contact angle of BOE etchant including *CG50* suggests that the means of contact angle for the BOE including the *Novec4200* and *CG50* are statistically similar to each other, but both groups are statistically different from the contact angle mean of the etchant-substrate without surfactant (Lukas Meier, 2023).

The contact angle for the PAN containing *BG10* was measured to be 33.4°, while was 28.6° for *Novec 4300*. The variation in contact angles observed between the PAN with *Novec 4300* and *BG10* is not substantial enough to justify the exclusion of the alternative surfactant. The superscript “ab” is used to indicate that the means of the two groups, in this case, PAN including PFAS surfactant and PAN including *BG10* surfactant, are not significantly different from each other, but they are both significantly different from the PAN etchant without surfactant (Lukas Meier, 2023).

The contact angle for the chrome etching solution is not reported due to the etchant wetting the substrate instantaneously (contact angle of <5° in 5 s).

As depicted in Fig. 6, at a constant surface free energy of the substrate, the surfactants play a crucial role in reducing the surface tension of the liquid to improve wettability. Higher wetting between the etching solution and substrate leads to improved etching of the substrate. The more the surface tension of the etching solution is reduced by the surfactants, the greater the difference between the surface free energy of the substrate and the etching solution becomes, thus leading to

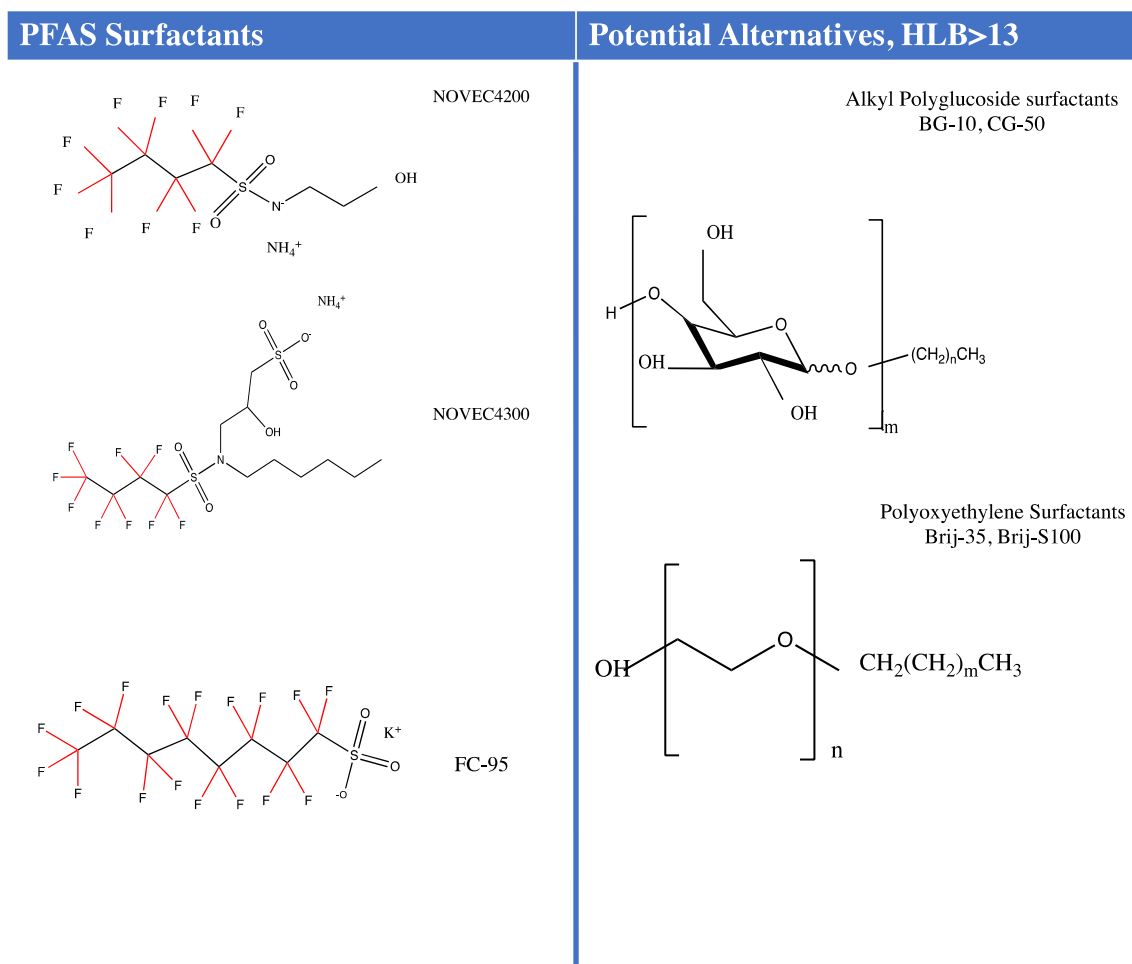


Fig. 5. The molecular structures of the PFAS-based surfactants and the potential alternatives.

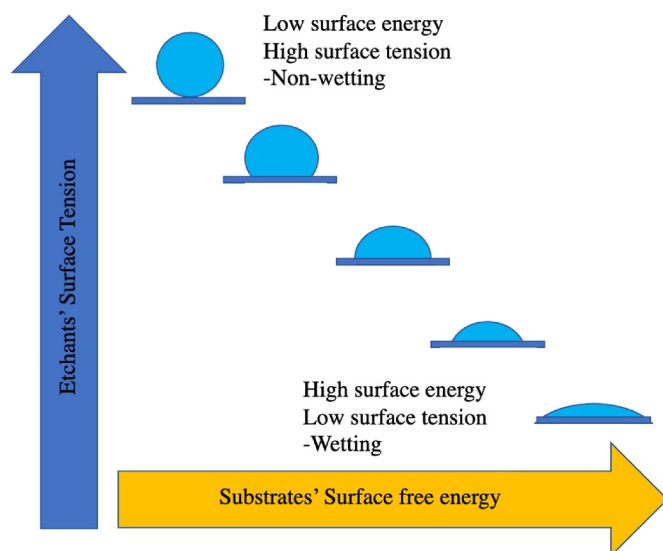


Fig. 6. Relation between Surface tension of the liquid and surface free energy of the substrate in wettability.

improved wetting of the substrate by the etching solution (Jothi Prakash and Prasanth, 2021).

Moreover, the alternative surfactants, namely BG-10, CG50, Brij 35, and Brij S100, exhibited lower P2OASys toxicity scores in comparison to

Novec4200 indicating that these alternative options are less toxic than the PFAS surfactants.

5. Conclusions

Safer and effective alternative surfactants were successfully identified utilizing a novel methodology for the replacement of PFAS surfactants in semiconductor etchants using surface chemistry, surfactants' intrinsic chemical and toxicological properties, and interfacial interactions between etching solutions and solid substrates. The chosen potential alternative surfactants, BG10, CG50, Brij 35 and Brij S100 were investigated using HLB values, surface tension measurements and CMC calculations, compatibility tests, measurement of contact angles in different substrates with different surface free energies, and chemical hazard assessment in four different etching solutions. Biobased alkyl polyglucoside surfactant BG10 was selected as the preferred alternative in TMAH, and PAN, while CG50 was the less toxic alternative in BOE etching solutions to replace Novec4200 and Novec 4300 PFAS surfactants. polyoxyethylene surfactants, Brij 35 and Brij S100 were determined to be less toxic alternatives for FC95 in the chrome etching solution. Safer alternative Surfactants, BG10, CG50, Brij 35, and Brij S100 demonstrated compatibility with etching solutions and simultaneously reduced the etchants' surface tension to improve the substrates' wetting capabilities. Toxicity comparison suggested less hazardous human health effects for the alternatives as compared to the PFAS surfactants. Industrial trials were carried out on the safer alternatives, and currently, approximately 100 semiconductor manufacturers, governments, and educational consumers that are using the safer and effective

non-PFAS alternatives in the etching solutions.

The replacement of PFAS surfactants with safer alternatives is imperative to address the significant health risks and environmental contamination associated with these highly toxic fluorinated substances. Future research should focus on identifying effective and sustainable alternatives to PFAS surfactants in various industrial applications, such as the paint and coating industry where PFAS are widely utilized.

CRedit authorship contribution statement

Rashmi Sharma: Conceptualization, Methodology, Formal analysis, Investigation, Writing – original draft. **Shreyas Shelke:** Conceptualization, Methodology, Formal analysis, Investigation, Writing – original draft. **Mohammad Bagheri Kashani:** Conceptualization, Methodology, Formal analysis, Investigation, Writing – original draft. **Gregory Morose:** Conceptualization, Writing – review & editing, Supervision, Funding acquisition. **Christopher Christuk:** Formal analysis, Writing – review & editing, Supervision, Resources. **Ramaswamy Nagarajan:** Conceptualization, Writing – review & editing, Supervision, Funding acquisition.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data availability

Data will be made available on request.

Acknowledgments

The authors express their gratitude to Prof. James E. Whitten (Department of Chemistry) and Prof. Amy Peterson (Plastics Engineering Department) for granting access to the surface tensiometer (KSV Sigma 70) and surface free energy and contact angle testing apparatus (Biolin Scientific Attension Theta Flex), respectively. The financial support provided by the Toxics Use Reduction Institute (TURI, Lowell, USA), Grant No. 112331 for this research is sincerely acknowledged. The authors extend their appreciation to Transene Company Inc., located in Danvers, MA, for their valuable technical support and provision of materials. Additionally, the authors would like to thank Dr. Joshna Chittigori for her contribution to proofreading the manuscript and Perin Jhaveri for his invaluable efforts in creating graphical illustrations for the paper.

References

- Abdullah, J.A.A., Jiménez-Rosado, M., Guerrero, A., Romero, A., 2022. Biopolymer-based films reinforced with green synthesized zinc oxide nanoparticles. *Polymers* 14, 5202. <https://doi.org/10.3390/polym14235202>.
- Alexander, S., Smith, G.N., James, C., Rogers, S.E., Guittard, F., Sagisaka, M., Eastoe, J., 2014. Low-surface energy surfactants with branched hydrocarbon architectures. *Langmuir ACS J. Surf. Colloids* 30, 3413–3421. <https://doi.org/10.1021/la500332s>.
- Bonefeld-Jørgensen, E.C., Long, M., Fredslund, S.O., Bossi, R., Olsen, J., 2014. Breast cancer risk after exposure to perfluorinated compounds in Danish women: a case-control study nested in the Danish National Birth Cohort. *Cancer Causes Control CCC* 25, 1439–1448. <https://doi.org/10.1007/s10552-014-0446-7>.
- Brendel, S., Fetter, É., Staude, C., Vierke, L., Biegel-Engler, A., 2018. Short-chain perfluoroalkyl acids: environmental concerns and a regulatory strategy under REACH. *Environ. Sci. Eur.* 30, 9. <https://doi.org/10.1186/s12302-018-0134-4>.
- Buck, R.C., Franklin, J., Berger, U., Conder, J.M., Cousins, I.T., de Voogt, P., Jensen, A.A., Kannan, K., Mabury, S.A., van Leeuwen, S.P., 2011. Perfluoroalkyl and polyfluoroalkyl substances in the environment: terminology, classification, and origins. *Integrated Environ. Assess. Manag.* 7, 513–541. <https://doi.org/10.1002/ieam.258>.
- Buck, R.C., Murphy, P.M., Pabon, M., 2012. Chemistry, properties, and uses of commercial fluorinated surfactants. In: Knepper, T.P., Lange, F.T. (Eds.), *The Handbook of Environmental Chemistry*. Springer Berlin Heidelberg, Berlin, Heidelberg, pp. 1–24. https://doi.org/10.1007/978-3-642-21872-9_1.
- Carrizosa, C., Murcia, M., Ballesteros, V., Costa, O., Manzano-Salgado, C.B., Ibarluzea, J., Iniguez, C., Casas, M., Andiaarena, A., Llop, S., Lertxundi, A., Schettgen, T., Sunyer, J., Ballester, F., Vrijheid, M., Lopez-Espinosa, M.-J., 2021. Prenatal perfluoroalkyl substance exposure and neuropsychological development throughout childhood: the INMA Project. *J. Hazard Mater.* 416, 125185. <https://doi.org/10.1016/j.jhazmat.2021.125185>.
- Cheng, K.C., Khoo, Z.S., Lo, N.W., Tan, W.J., Chemmangattuvalappil, N.G., 2020. Design and performance optimisation of detergent product containing binary mixture of anionic-nonionic surfactants. *Heliyon* 6, e03861. <https://doi.org/10.1016/j.heliyon.2020.e03861>.
- Cousins, I.T., Vestergren, R., Wang, Z., Scheringer, M., McLachlan, M.S., 2016. The precautionary principle and chemicals management: the example of perfluoroalkyl acids in groundwater. *Environ. Int.* 94, 331–340. <https://doi.org/10.1016/j.envint.2016.04.044>.
- Cousins, I.T., DeWitt, J.C., Glüge, J., Goldenman, G., Herzke, D., Lohmann, R., Ng, C.A., Scheringer, M., Wang, Z., 2020. The high persistence of PFAS is sufficient for their management as a chemical class. *Environ. Sci. Process. Impacts* 22, 2307–2312. <https://doi.org/10.1039/D0EM00355G>.
- Daly, E.R., Chan, B.P., Talbot, E.A., Nassif, J., Bean, C., Cavallo, S.J., Metcalf, E., Simone, K., Woolf, A.D., 2018. Per- and polyfluoroalkyl substance (PFAS) exposure assessment in a community exposed to contaminated drinking water, New Hampshire, 2015. *Int. J. Hyg. Environ. Health* 221, 569–577. <https://doi.org/10.1016/j.ijheh.2018.02.007>.
- Farn, R.J., 2006. *Chemistry and Technology of Surfactants*. Wiley-Blackwell.
- Fowler, Jim, Cohen, Lou, Jarvis, Philip, 1998. *Practical Statistics for Field Biology*, second ed.
- Gaines, L.G.T., 2022. Historical and current usage of per- and polyfluoroalkyl substances (PFAS): a literature review. *Am. J. Ind. Med.* <https://doi.org/10.1002/ajim.23362>.
- Genualdi, S., Beekman, J., Carlos, K., Fisher, C.M., Young, W., DeJager, L., Begley, T., 2022. Analysis of per- and poly-fluoroalkyl substances (PFAS) in processed foods from FDA's Total Diet Study. *Anal. Bioanal. Chem.* 414, 1189–1199. <https://doi.org/10.1007/s00216-021-03610-2>.
- Glüge, J., Scheringer, M., Cousins, I.T., DeWitt, J.C., Goldenman, G., Herzke, D., Lohmann, R., Ng, C.A., Trier, X., Wang, Z., 2020. An overview of the uses of per- and polyfluoroalkyl substances (PFAS). *Environ. Sci. Process. Impacts* 22, 2345–2373. <https://doi.org/10.1039/D0EM00291G>.
- Golodnizky, D., Davidovich-Pinhas, M., 2020. The effect of the HLB value of sucrose ester on physicochemical properties of bigel systems. *Foods* 9, 1857. <https://doi.org/10.3390/foods9121857>.
- Guardian, M.G.E., Boongaling, E.G., Bernardo-Boongaling, V.R.R., Gamonchuang, J., Boontongto, T., Burakham, R., Arnnok, P., Aga, D.S., 2020. Prevalence of per- and polyfluoroalkyl substances (PFASs) in drinking and source water from two Asian countries. *Chemosphere* 256, 127115. <https://doi.org/10.1016/j.chemosphere.2020.127115>.
- Jothi Prakash, C.G., Prasanth, R., 2021. Approaches to design a surface with tunable wettability: a review on surface properties. *J. Mater. Sci.* 56, 108–135. <https://doi.org/10.1007/s10853-020-05116-1>.
- Kancharla, S., Alexandridis, P., Tsiannou, M., 2022. Sequestration of per- and polyfluoroalkyl substances (PFAS) by adsorption: surfactant and surface aspects. *Curr. Opin. Colloid Interface Sci.* 58, 101571. <https://doi.org/10.1016/j.cocis.2022.101571>.
- Kissa, E., 2001. *Fluorinated surfactants and repellents*. In: expanded, rev (Ed.), *Surfactant Science Series*, second ed. Marcel Dekker, New York.
- Kunjappu, Joy T., Rosen, Milton J., 2012. *Surfactants and Interfacial Phenomena*, fourth ed. Wiley.
- Lukas Meier, 2023. *ANOVA and Mixed Models A Short Introduction Using R*, first ed. Chapman & Hall.
- Mahinroosta, R., Senevirathna, L., 2020. A review of the emerging treatment technologies for PFAS contaminated soils. *J. Environ. Manag.* 255, 109896. <https://doi.org/10.1016/j.jenvman.2019.109896>.
- Mittal, K.L., 2009. *Contact Angle, Wettability and Adhesion*. VSP, Leiden.
- Mousavi, S.E., Delgado-Saborit, J.M., Godderis, L., 2021. Exposure to per- and polyfluoroalkyl substances and premature skin aging. *J. Hazard. Mater.* 405, 124256. <https://doi.org/10.1016/j.jhazmat.2020.124256>.
- Nasalapure, A.V., Chalannavar, R.K., Kasai, D.R., Reddy, K.R., Raghu, A.V., 2021. Novel polymeric hydrogel composites: synthesis, physicochemical, mechanical and biocompatible properties. *Nano Express* 2, 030003. <https://doi.org/10.1088/2632-959X/ac11bf>.
- Ober, C.K., Käfer, F., Deng, J., 2022. Review of essential use of fluorochemicals in lithographic patterning and semiconductor processing. *J. MicroNanopatterning Mater. Metrol.* 21, 010901. <https://doi.org/10.1117/1.JMM.21.1.010901>.
- Perinelli, D.R., Cespi, M., Lorusso, N., Palmieri, G.F., Bonacucina, G., Blasi, P., 2020. Surfactant self-assembling and critical micelle concentration: one approach fits all? *Langmuir* 36, 5745–5753. <https://doi.org/10.1021/acs.langmuir.0c00420>.
- Quiñones, O., Snyder, S.A., 2009. Occurrence of Perfluoroalkyl Carboxylates and Sulfonates in Drinking Water Utilities and Related Waters from the United States. *Environ. Sci. Technol.* 43, 9089–9095. <https://doi.org/10.1021/es9024707>.
- Radley-Gardner, O., Beale, H., Zimmermann, R. (Eds.), 2016. *Fundamental Texts on European Private Law*. Hart Publishing. <https://doi.org/10.5040/9781782258674>.
- Sassi, M., Mattiello, S., Beverina, L., 2020. Syntheses of organic semiconductors in water. Recent advancement in the surfactants enhanced green access to polyconjugated molecules: syntheses of organic semiconductors in water. Recent advancement in the surfactants enhanced green access to polyconjugated molecules. *Eur. J. Org. Chem.* 2020, 3942–3953. <https://doi.org/10.1002/ejoc.202000140>.
- Scher, D.P., Kelly, J.E., Huset, C.A., Barry, K.M., Hoffbeck, R.W., Yingling, V.L., Messing, R.B., 2018. Occurrence of perfluoroalkyl substances (PFAS) in garden

- produce at homes with a history of PFAS-contaminated drinking water. *Chemosphere* 196, 548–555. <https://doi.org/10.1016/j.chemosphere.2017.12.179>.
- Sun, M., Arevalo, E., Strynar, M., Lindstrom, A., Richardson, M., Kearns, B., Pickett, A., Smith, C., Knappe, D.R.U., 2016. Legacy and emerging perfluoroalkyl substances are important drinking water contaminants in the Cape Fear River watershed of North Carolina. *Environ. Sci. Technol. Lett.* 3, 415–419. <https://doi.org/10.1021/acs.estlett.6b00398>.
- Tansel, B., 2022. PFAS use in electronic products and exposure risks during handling and processing of e-waste: a review. *J. Environ. Manag.* 316, 115291 <https://doi.org/10.1016/j.jenvman.2022.115291>.
- Toxics Use Reduction Institute, 2021. Pollution prevention options analysis system: P2OASys. URL: <https://p2oasys.turi.org/>, 1.22.2023.
- Wang, Z., Cousins, I.T., Scheringer, M., Hungerbühler, K., 2013. Fluorinated alternatives to long-chain perfluoroalkyl carboxylic acids (PFCAs), perfluoroalkane sulfonic acids (PFASs) and their potential precursors. *Environ. Int.* 60, 242–248. <https://doi.org/10.1016/j.envint.2013.08.021>.
- Whitehead, H.D., Venier, M., Wu, Y., Eastman, E., Urbanik, S., Diamond, M.L., Shalin, A., Schwartz-Narbonne, H., Bruton, T.A., Blum, A., Wang, Z., Green, M., Tighe, M., Wilkinson, J.T., McGuinness, S., Peaslee, G.F., 2021. Fluorinated Compounds in North American Cosmetics. *Environ. Sci. Technol. Lett.* 8, 538–544. <https://doi.org/10.1021/acs.estlett.1c00240>.
- Zar, J.H., 2010. *Biostatistical Analysis*, fifth ed. Prentice-Hall/Pearson, Upper Saddle River, N.J.
- Zhou, J., Li, S., Liang, X., Feng, X., Wang, T., Li, Z., Zhu, L., 2021. First report on the sources, vertical distribution and human health risks of legacy and novel per- and polyfluoroalkyl substances in groundwater from the Loess Plateau, China. *J. Hazard Mater.* 404, 124134 <https://doi.org/10.1016/j.jhazmat.2020.124134>.