Return to J Eulkins

The AROCLORS

Physical Properties and Suggested Applications

APPLICATION DATA BULLETIN No. P-115

Manufactured by

MONSANTO CHEMICAL COMPANY

ST. LOUIS, U. S. A.

New York - Boston - Chicago - San Francisco
Los Angeles - Detroit - Birmingham
Charlotte - Montreal - London

0475990

TOWOLDMON0032961
WATER_PCB-00017430

FOREWORD

The Aroclors have won a prominent place in the field of synthetics with unique properties to fill requirements not met by materials heretofore available. They have found usefulness in widely differing fields of activity where their properties are of especial value.

Following is a description of the properties of eleven Aroclors, each of which is representative of a series. For almost every Aroclor described in this bulletin there is a dark-colored grade of otherwise approximately the same physical and chemical characteristics. These darker products carry a lower price and can frequently be used where color is not important.

A study of this brief description will suggest means of employing the Aroclors in perfecting still other products, development of which has been delayed by the lack of a material that exactly fulfills particular requirements.

The Aroclors are produced exclusively by Monsanto Chemical Company.

0475991

TOWOLDMON0032962
WATER_PCB-00017431

Page No.

GENERAL PROPERTIES 3

General Physical Properties of Some of the Aroclors 4–5

Adhesiveness 6
Corrosion 6
Density 6
Electrical Properties 6
Densities of Aroclors at Various Temperatures 6
Specific Heat and Thermal Conductivity . 7
Thermal Conductivity of Aroclor 1248 . . 7
Specific Heat of Aroclors 7
Non-drying Properties 7
Noninflammability 7
Stability 7
Toward Alkalies 7
Toward Acids 7
Toward Heat 8
Toward Oxidation 8
Solubility 8
Approximate Solubility of Sulfur in Aroclor 1262 8
Thermoplasticity 8
Solubility of Aroclors in 100 Milliliters of Various Solvents 9
Vapor Pressure of Aroclors 10
Viscosity Ranges of Some of the Aroclors . 11
Toxicity 11
Vaporization Loss 11

APPLICATIONS OF AROCLORS 12

Adhesives 12
Electrical Equipment 12
Expansion Medium 12
Hydraulic Medium 12
Power Transmission 12
Hydraulic Pressure Medium 12
Performance of Aroclor 1242 in a Hydraulic Coupling for Gasoline Engine 12
Lubrication 13
High Temperature 13
Extreme Pressure 13
Submerged Lubrication 13
Suggested Uses for Aroclors in Plastics, Pigments, Lacquers, Paints and Varnishes 14
Compatibility with Various Materials . . 14
Ethyl Cellulose 14
Graphic Arts 14
Impregnation 15
Moisture Proofing 15
Mold Lubricants 15
Diagrams Showing Practical Composition of Lacquers Using Aroclors 1254 and 1262 16-17
Nitrocellulose Coatings 18
Aroclor Lacquers 18
Pigment 18
Paints and Varnishes 18
Rubber and Rubber Substitutes 19
Chlorinated Rubber Finishes 19
Vinyl Resins 19

SANTOWAX 20

OTHER PRODUCTS 20

0475992

TOWOLDMON0032963
WATER_PCB-00017432

General Properties

The Aroclors range in form and appearance from mobile oily liquids to fine white crystals and hard transparent resins. They are non-oxidizing, permanently thermoplastic, of low volatility and non-corrosive to metals. They are not hydrolyzed by water or alkalies. The viscous liquids and the resins will not support combustion when heated alone.

The crystalline Aroclors are relatively insoluble, but the liquid and resinous products are soluble in most of the common organic solvents, thinners and oils. The main exceptions are that all the Aroclors are insoluble in water, glycerine or the glycols, and Aroclor 5460 is insoluble in the lower molecular weight alcohols. Aroclor 4465 is only partly soluble in the lower alcohols.

The excellent electrical properties, fire resistance and inertness of the Aroclors make them useful in many applications not mentioned in this bulletin.

The properties imparted by the Aroclors and their usefulness for particular applications vary in regular gradients over the series so that the selection of the right Aroclor for a specific use can generally be made simply by a comparison of the physical properties of the several Aroclors.

0475993

TOWOLDMON0032964
WATER_PCB-00017433

TABLE

GENERAL PHYSICAL PROPERTIES

		Aroclor 1242	Aroclor 1248	Aroclor 1254	Aroclor 1260
Form		Practically colorless mobile oil	Yellow tinted oily liquid	Yellow tinted viscous oil	Light yellow soft sticky resin
Color—NPA		0.5 Max.	0.5 Max.	1.0 Max.	1.0 Max.
Acidity—Maximum (Mgm. KOH per Gm.)		0.01	0.01	0.01	0.015
Coefficient of Expansion	cc/cc/°C	0.000678 (25°–65°C)	0.000702 (25°–65°C)	0.000661 (25°–65°C)	—
	cc/cc/°F	0.000377 (77°–149°F)	0.000389 (77°–149°F)	0.000367 (77°–149°F)	—
Density—Specific Gravity 25°/25°C (77°/77°F)		1.378 to 1.388	1.447 to 1.457	1.538 to 1.548	1.618 to 1.629
Pounds per Gallon—25°C (77°F)		11.50	12.08	12.83	13.50
Distillation Range—ASTM D-20 Mod.	°C	322°–365°C Uncorr.	330°–370°C Uncorr.	365°–390°C	385°–420°C
	°F	612°–689°F Uncorr.	626°–698°F Uncorr.	689°–734°F	725°–788°F
Evaporation Loss—%—ASTM D-6 Mod. 163°C 5 hrs.		3.04 to 3.64	3.0 to 4.0	1.06 to 1.28	—
100°C 6 hrs.		—	—	0.4	0.0 to 0.2
Flash Point—Cleveland Open Cup	°C	176°–180°C	193°–196°C	None	None
	°F	348°–356°F	379°–384°F		
Fire Point—Cleveland Open Cup	°C	334°C	None	None	None
	°F	633°F			
Pour Point—ASTM	°C	−17.7° to −20.7°C	−7°C	8° to 12°C	26° to 36°C
	°F	−0.2° to −5.2°F	19.4°F	46° to 54°F	79° to 97°F
Softening Point—ASTM	°C	—	—	—	—
	°F	—	—	—	—
Refractive Index—D-line—20°C		1.627–1.629	1.630–1.631	1.637–1.639 at 25°C	—
Viscosity—Saybolt Universal Sec. (ASTM—D-88)	210°F (98.9°C)	34.0–34.6	36.0–37.0	43.5–48.5	70 82
	130°F (54.4°C)	49–56	69–78	260–400	2600–4500
	100°F (37.8°C)	80–93	185–240	1800–3800	—

0475994

TOWOLDMON0032965
WATER_PCB-00017434

I

OF SOME OF THE AROCLORS

Aroclor 1262 Light yellow sticky clear resin	Aroclor 1268 Pale yellow opaque brittle resin	Aroclor 1270 White crystalline powder	Aroclor 4465 Yellow transparent brittle resin	Aroclor 5442 Yellow transparent sticky resin	Aroclor 5460 Yellow transparent resin	Aroclor 2565 Brown-black opaque resin
1.2 Max.	—	—	1.5 Max.	—	2.0 Max.	—
0.02	—	0.175	0.05	0.028	0.07	1.26
0.000640 (25°–90°C)	—	—	0.000611 (25°–65°C)	0.00123 (25°–99°C)	0.00179 (25°–124°C)	0.000656 (25°–65°C)
0.000355 (77°–194°F)	—	—	0.000339 (77°–149°F)	0.000683 (77°–210°F)	0.000994 (77°–255°F)	0.000364 (77°–149°F)
1.646 to 1.653	1.804 to 1.811	1.944 to 1.960	1.712 to 1.723	1.432 to 1.447	1.740 to 1.745	1.724 to 1.740
13.72	15.13	16.24	14.28	11.96	14.50	14.41
373°–404°C Uncorr.	—	450°–460°C	Requires vacuum	—	Requires vacuum	—
703°–759°F Uncorr.	—	842°–860°F	Requires vacuum	—	Requires vacuum	—
0.48 to 0.56	0.15 to 0.24	0.0 to 0.1	0.23 to 0.29	2.0	0.025	0.21 to 0.24
—	—	—	—	0.012	1.51 to 1.71 (at 260°—5 hrs.)	—
None	None	None	None	247°C 477°F	None	None
None	None	None	None	>350°C >662°F	None	None
34.9° to 38.0°C	—	—	—	46°C	—	—
95° to 100.4°F	—	—	—	115°F	—	—
—	135° to 160°C (hold pt.)	294° to 300°C (hold pt.)	60° to 66°C	48.5° to 53°C	100° to 105.5°C	70° to 77°C
—	275° to 320°F (hold pt.)	561° to 572°F (hold pt.)	140° to 151°F	119° to 127°F	212° to 222°F	158° to 171°F
1.6501–1.6517	—	—	1.664–1.667	—	1.660–1.665	—
90–103	—	—	92–156 (266°F or 130°C)	313.5	—	—
600–850 at 160°F	—	—	—	—	—	—
—	—	—	—	—	—	—

0475995

TOWOLDMON0032966
WATER_PCB-00017435

Adhesiveness

The Aroclor resins adhere strongly to smooth surfaces — to glass and metal or to smooth varnished or lacquered surfaces.

The softer Aroclors are suggested for difficult adhesive problems where a flexible non-drying waterproof material is necessary.

The Aroclor adhesives are thermoplastic; are readily applied hot without solvent; do not require high temperatures for easy application, and are set immediately upon cooling.

Corrosion

The Aroclors show practically no corrosive effect on metals within normal ranges of temperature and only very slight corrosion even at elevated temperatures, as shown in the following table:

	Penetration — inches/year at 325°C (617°F)	
	Aroclor 1248	Aroclor 1254
Mild steel	0.0028	0.0045
Yellow brass	0.00047	0.0030
Copper	0.00145	0.0650

Density

All the Aroclors are heavier than water, a valuable property for many applications. Densities are shown in Figure 1.

Electrical Properties

The Aroclors have extremely interesting electrical characteristics: high dielectric constant, resistivity, dielectric strength, and low power factor.

FIG. 1

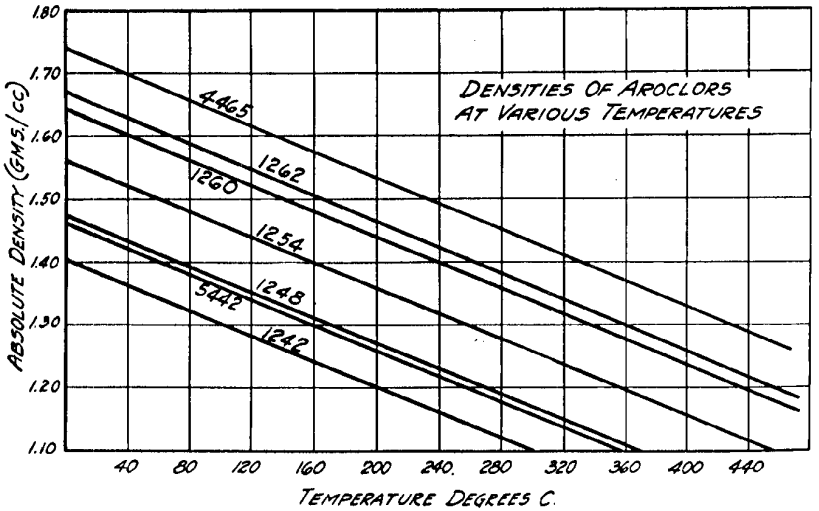

0475996

TOWOLDMON0032967
WATER_PCB-00017436

Specific Heat and Thermal Conductivity

The specific heat at different temperatures of several of the Aroclors is shown in Figure 2. This, together with the thermal conductivity data given in Table II, is of value in calculations involved in the use of Aroclor as a high temperature-low pressure fluid heat transfer medium.

TABLE II

Thermal Conductivity of Aroclor 1248

Temperature °C	Temperature °F	Density g/cc.	Thermal Conductivity Btu./Hr./Sq. Ft./°F/Ft.	Viscosity Sayboll Univ. Sec.
30	90	1.441	0.0613	360
60	140	1.411	0.0698	60
100	212	1.370	0.0800	36

FIG. 2

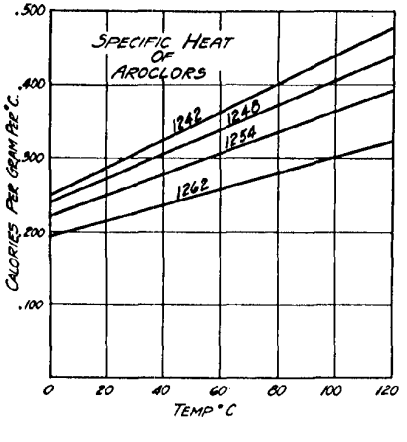

Non-Drying Properties

The Aroclors are non-drying, and when they are exposed to the air, even in thin films, no noticeable oxidation or hardening takes place. However, when used as ingredients of lacquers, they do not retard the rate of drying of the lacquer films. Quick drying varnishes and paints may be made with Aroclor resins.

Noninflammability

The viscous Aroclor oils and the resins do not support combustion when heated alone, even at their boiling points — temperatures above 350°C. Most of the Aroclors flux readily with resinous and pitch-like materials to give a product having a decreased fire hazard. When incorporated in nitrocellulose films the Aroclors retard the rate of burning.

Stability

Toward Alkalies

The Aroclors are remarkably resistant to the action of either hydrolyzing agents or high temperature. They are not affected by boiling with sodium hydroxide solution.

Toward Acids

Experiments were made to determine whether hydrogen chloride is evolved during the treatment of Aroclors with sulfuric acid. Aroclor 1254 (selected as typical) was stirred with an equal volume of ten per cent sulfuric acid for a period of 150 hours. Any gases escaping from the reaction flask had to pass through a trap filled with silver nitrate solution, which solution would give a precipitate of silver chloride if any HCl came in contact with it. After 150 hours of treatment, neither the trap solution nor the acid layer in the treating flask showed any hydrogen chloride present. Even prolonged treatment (255 hours) with concentrated sulfuric acid indicated only a slight trace (too small for quantitative measurement) of hydrogen chloride in the acid layer.

0475997

TOWOLDMON0032968
WATER_PCB-00017437

Toward Heat

Because of their stability to heat, the Aroclors are useful heat-transfer media. Aroclor 1254 and particularly the less viscous Aroclor 1248 are recommended for this purpose because they may be heated at temperatures up to 325°C (617°F) in a closed system for long periods without appreciable decomposition and are at the same time noninflammable.

Toward Oxidation

When Aroclor is subjected to a bomb test at 140°C with 250 pounds per square inch oxygen, there is no evidence of oxidation as judged by development of acidity or formation of sludge.

Solubility

The Aroclor oils and resins are easily soluble in most of the common organic solvents and drying oils. The hard crystalline materials are in general less soluble than the Aroclor oils or softer resins. All Aroclors are insoluble in water. Solubilities of some of the Aroclors in the more common substances are shown in Table III.

The solubility of sulfur in Aroclor 1260 is shown in Figure No. 3. Compatibility data on Aroclors in nitrocellulose lacquers are shown on page 16.

Thermoplasticity

The Aroclors are permanently thermoplastic. They apparently undergo no condensation or hardening upon repeated melting and cooling. The clear Aroclor resins are now being produced with softening points up to 110°C. The opaque crystalline solids are produced with initial melting points up to approximately 290°C.

FIG. 3

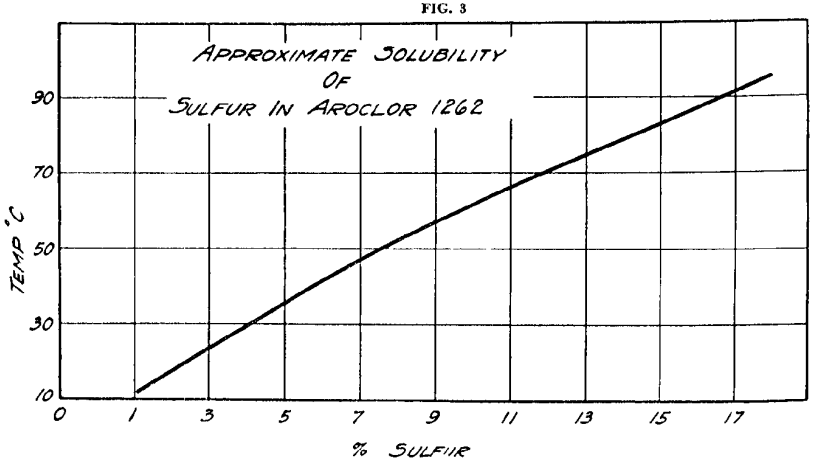

0475998

TOWOLDMON0032969
WATER_PCB-00017438

TABLE III — Solubility of Aroclors in 100 Milliliters of Various Solvents

Type of Solvent (Aroclor)	1242 Cold	1242 Hot	1248 Cold	1248 Hot	1254 Cold	1254 Hot	1270 Cold	1270 Hot	4465 Cold	4465 Hot
Acid										
Acetic Acid	S	S	—	—	S	S	—	—	SS	S
Oleic Acid	S	S	—	—	S	S	—	—	S	VS
Benzoic Acid	10.0 31°C	—	10.0 32°C	—	—	—	—	—	—	—
Aldehyde										
40% Formaldehyde	I	I	I	I	I	I	I	I	I	I
Furfural	VS	VS	VS	VS	VS	VS	S	VS	VS	VS
Amine										
Aniline	S	S	—	—	S	S	—	—	VS	VS
Pyridine	132.5 86°C	440 99°C	—	—	114 31°C	425 100°C	—	—	VS	VS
Chlors — derivative										
Amyl chlorides — mixed	S	S	S	S	S	S	—	—	VS	VS
Carbon Tetrachloride	S	S	S	S	S	S	3.65	—	VS	VS
Chloroform	S	S	S	S	S	S	—	—	VS	VS
Dichlorethylene	—	—	—	—	—	—	3.06	—	VS	VS
Ethylene Dichloride	S	S	S	S	S	S	—	—	VS	VS
Monochlorobenzene	S	S	S	S	S	S	2.89	—	VS	VS
Orthodichlorobenzene	—	—	—	—	—	—	—	—	VS	VS
Tetrachlorethane	S	S	S	S	S	S	—	—	VS	VS
Trichlorethane	S	S	S	S	S	S	3.31	—	VS	VS
Trichlorethylene	S	S	S	S	S	S	—	—	VS	VS
Drying Oil										
Tung Oil	S	S	S	S	S	S	—	—	VS	VS
Linseed Oil	S	S	S	S	S	S	—	—	VS	VS
Ester										
Amyl Acetate	S	S	S	S	S	S	—	—	VS	VS
Butyl Acetate	S	S	S	S	S	S	—	—	VS	VS
Cellosolve Acetate	S	S	S	S	S	S	—	—	VS	VS
Cottonseed Oil	S	S	S	S	S	S	—	—	S	VS
Dibutyl Pathalate	S	S	S	S	S	S	—	—	S	VS
Diethyl Phthalate	S	S	S	S	S	S	—	—	S	VS
Ethyl Acetate	S	S	S	S	S	S	—	—	S	VS
Ethyl Lactate	S	S	S	S	S	S	—	—	VS	VS
Ethylene Glycol Diacetate	S	S	S	S	S	S	—	—	VS	VS
Methyl Acetate	S	S	S	S	S	S	—	—	S	S
Tricresyl Phosphate	S	S	S	S	S	S	—	—	SS	S
Ether: Ethyl Ether	S	S	S	S	S	S	S	S	S	—
Ether Alcohol										
Carbitol	224 31°C	307 99°C	VS	VS	173 26°C	259 99°C	—	—	SS	—
Cellosolve	S	S	S	S	S	S	—	—	S	—
Diethylene Glycol	—	—	—	—	—	—	—	—	SS	—
p-p' Dihydroxy Ethyl Ether	16.9 23°C	19 99°C	SS	SS	8 30°C	10 100°C	—	—	SS	—
Hydrocarbon										
Benzene	VS	VS	VS	VS	VS	VS	3.5	—	VS	VS
Gasoline	VS	VS	VS	VS	VS	VS	—	—	VS	VS
Kerosene	VS	VS	VS	VS	VS	VS	—	—	VS	VS
Mineral Spirits	VS	VS	VS	VS	VS	VS	—	—	VS	VS
Paraffin	2.0 27.5°C	S	2.0 28°C	S	—	S	—	—	< 5.0	S
Pine Oil	S	S	VS	VS	S	S	—	—	S	S
Toluene	VS	VS	VS	VS	VS	VS	—	—	VS	VS
Turpentine	VS	VS	VS	VS	VS	VS	—	—	VS	VS
Xylene	VS	VS	VS	VS	VS	VS	—	—	VS	VS
Hydroxy — derivative										
Amyl Alcohol	S	S	—	—	S	S	—	—	S	S
n-Butyl Alcohol	S	S	—	—	S	S	—	—	SS	S
Ethyl Alcohol (3-A)	23.3 29°C	80.0 70°C	—	—	10 27°C	28 75°C	—	—	SS	—
Glycerin	I	I	I	I	I	I	I	I	I	I
Methyl Alcohol	42.5 29°C	88.5 60°C	—	—	15 26°C	22.2 61°C	—	—	SS	—
Phenol — 90%	194 30°C	S	—	—	SS	S	—	—	S	S
Ketone										
Acetone	S	S	—	—	S	S	—	—	S	S
Miscellaneous										
Carbon Disulfide	S	S	—	—	S	S	—	—	VS	VS
Nitrobenzene	S	S	—	—	S	S	—	—	VS	—
Water	I	I	I	I	I	I	I	I	I	I

I — Insoluble S — Soluble SS — Slightly Soluble VS — Very Soluble

Figures of show grams Aroclor per 100 milliliters of solvent at 25°C unless otherwise indicated.

0475999

TOWOLDMON0032970
WATER_PCB-00017439

FIG. 4

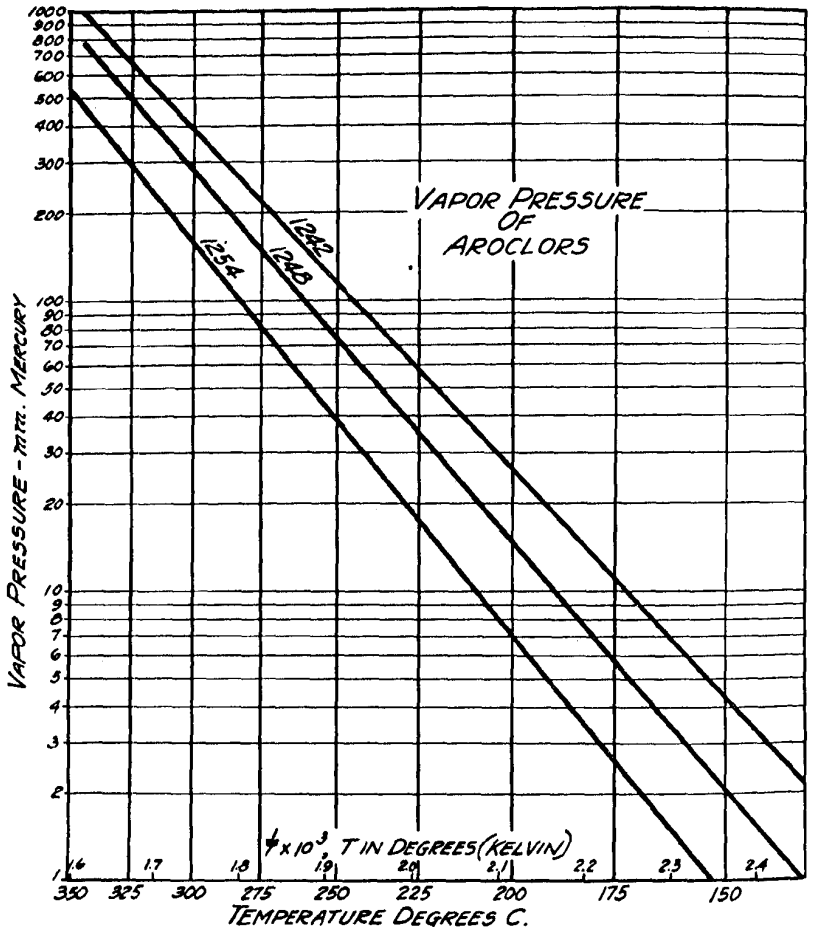

0476000

TOWOLDMON0032971
WATER_PCB-00017440

FIG. 5

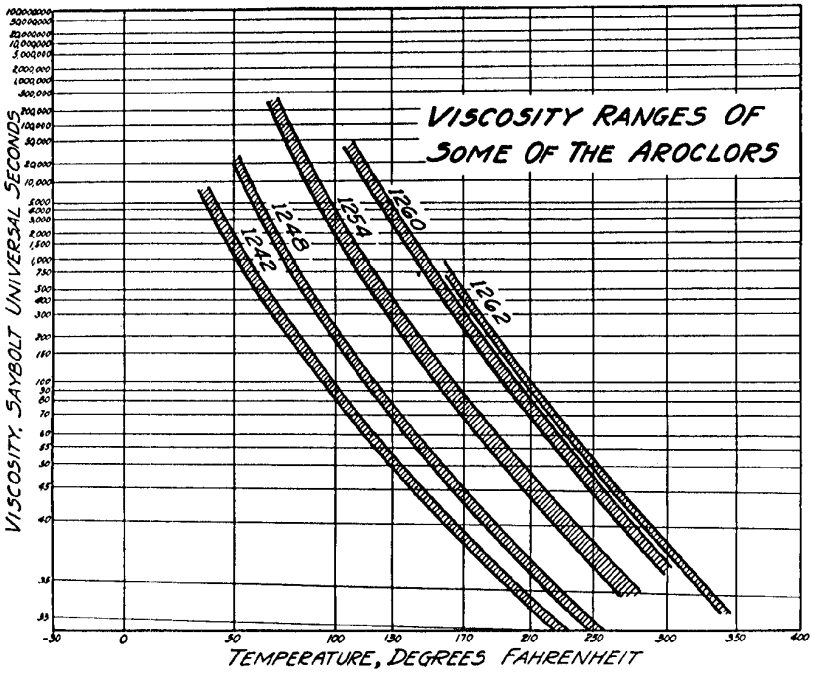

Toxicity

Experimental work on animals shows that prolonged exposure to Aroclor vapors evolved at high temperatures or by repeated oral ingestion will lead to systemic toxic effects.

Repeated bodily contact with liquid Aroclors may lead to an acne-form skin eruption.

Suitable draft ventilation to control the vapors evolved at elevated temperatures, as well as protection by suitable garments from extensive bodily contact with liquid Aroclors, should prevent any untoward effect.

Vaporization Loss

The Aroclors have low vaporization losses as shown in the data in the table of physical properties.

0476001

TOWOLDMON0032972
WATER_PCB-00017441

APPLICATIONS

Adhesives

The heavier resinous Aroclors, because of their excellent adherence to smooth surfaces, are very adaptable to compounding in water-insoluble adhesives. Aroclors 1260, 1262, 4465 and 5460 are suggested for this use.

Electrical Equipment

Because of their noninflammability, high dielectric constant, resistivity, dielectric strength and low power factor, the liquid and resinous Aroclors are extremely useful materials for the electrical industry.

Expansion Medium

Because of their stability under variations in temperature and freedom from gum formation from oxidation, the Aroclors are useful as expanding media in bellows controls and in thermostats.

Hydraulic Medium

Power Transmission

The Aroclors are superior hydraulic media for power transmission. Because of their greater density and E. P. characteristics they approach more closely the theoretical transmission values for mechanical power as illustrated in Figure No. 6. This greater efficiency makes possible a reduction in the size of the hydraulic coupling design.

In order to meet extremely low-temperature weather conditions, it is necessary to adjust the freezing point of the Aroclor selected by the addition of a pour point depressant. Suitable adjustments can be made in the composition to reach a pour point of minus 65°F.

The steepness of the viscosity-temperature curve of the Aroclors is a handicap to the application of Aroclors to many types of fluid transmission. This curve can be flattened to a marked degree by introduction of a viscosity-index corrector. Information will be gladly furnished.

Hydraulic Pressure Medium

It is customary to employ a D. T. Light Oil (mineral base) as a hydraulic medium in many types of pressure operations. A widespread use is in the operation of zinc alloy die casting machines where pressures of 800 to 1500 pounds per square inch are encountered. Condensate from the atmosphere above the liquid level in the breather tank frequently introduces water, which, having a greater density, sinks to the bottom and is drawn into the system. Under the influence of heat and pressure the water causes hydrolysis of the hydrocarbon oil, forming fatty acids which corrode the pump vanes and the regulating valves of the system, causing loss of pressure, lowered production rate and final shut down for repairs. A break in the hydraulic system around the open flames necessary to maintain the molten condition of the die-casting alloy almost invariably results in a fire with its attendant hazards.

Aroclors 1242 or 1248 are recommended to overcome these difficulties. They are heavier than water, thus excluding it from the system. They are stable — not hydrolyzed under heat and pressure — and thus avoid corrosion and expensive delays for repairs. They are not inflammable, thus adding to the safety of the operators and to continuity of production.

FIG. 6

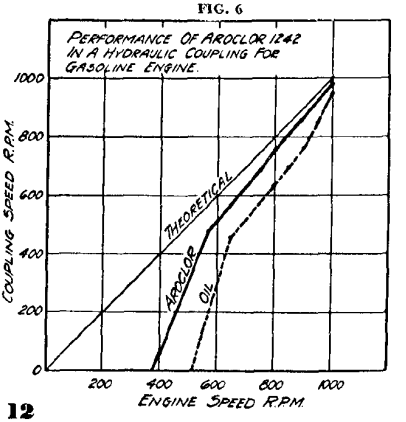

0476032

TOWOLDMON0032973
WATER_PCB-00017442

Lubrication

High Temperature

The heat-resisting, noninflammable characteristics of the Aroclors make them attractive as lubricants under conditions of high temperature, as, for example, in governor systems of central power stations. Aroclor 1248 is well suited to this application. Straight Aroclor 1254 gave excellent results on a roller bearing test operating at 255°. 260°F with much less carbonization or decomposition than the usual spindle oil under the same conditions.

Extreme Pressure

It is a well accepted hypothesis in the lubrication industry that by the addition of certain elements such as chlorine, sulfur and others in the proper form to a lubricating oil, a certain chemical combination takes place with the iron or steel metal bearing surfaces. These surface compositions tend to prevent seizure of the rubbing surfaces under extreme loads and under which loads, if the sole lubricant were a pure mineral oil, seizure or scoring would result at once through film failure.

As an extreme pressure (E. P.) lubricant base added to a petroleum hydrocarbon oil in amounts up to approximately 15% by weight, Aroclors 1248 and 1254 materially increase the load-carrying properties without reducing the viscosity of the resulting composition. These Aroclors represent one of the more adequate carriers for the element chlorine as an extreme pressure base, possessing the following advantages:

1. *Stability.* They are stable, even at higher temperatures, which permits neither separation of components nor appreciable change in physical or chemical properties during long periods of operation and should not cause continued chemical action on metal parts except the particular chemical metal surface combination which is necessary to effect high load-carrying capacities.

2. *Non-volatile.* Many other types of chlorine bearing compounds are so volatile as to render them unfit for long periods of service because of the escape of the elements from the lubricant. The Aroclors are non-volatile at normal temperatures.

3. *Non-oxidizing.* Aroclors do not oxidize or thicken up to an objectionable degree.

4. *Non-corrosive.* Aroclors are non-corrosive toward metal surfaces.

5. *Non-abrasive.* Aroclors exert no abrasion on the machined surfaces.

6. *Non-hydrolysis.* Aroclors do not hydrolyze in the presence of water, thus avoiding the generation of hydrochloric acid.

7. *Compatibility.* Aroclors are completely miscible with mineral oils.

8. *Color.* Aroclors do not darken or change the color of the lubricating oil.

Submerged Lubrication

Under conditions of lubrication subjected to exposure to water displacement such, for example, as lubrication of bridge rollers, a heavier-than-water lubricant can be prepared from mixtures of Aroclor and oil, of which the following are typical examples:

Mix No.	—% by Wt.— Oil*	Aroclor 1148	Pour Point	Gravity at 15.5°C	Approx. lbs./gal.
1	50	50	0°F	1.1263	9.4
2	25	75	+5°F	1.2703	10.6

*Bright Stock: Gravity API 22-23
Viscosity 210°F—160 Secs. Sayholt
Color ASTM—7-8
Flash Point—545°F
Pour Point—15°F

0476003

TOWOLDMON0032974
WATER_PCB-00017443

SUGGESTED USES FOR AROCLORS
in
PLASTICS, PIGMENTS, LACQUERS, PAINTS and VARNISHES

The Aroclors are compatible with most of the common plastic materials (see compatibility table on this page). The degree of flexibility imparted by the Aroclors diminishes progressively in the order of liquid Aroclor — soft resin — hard resin. The hardness of the resulting compositions increases in the same order. Usually a satisfactory balance between flexibility and hardness can be obtained either by selecting the Aroclor of proper physical characteristics or by using a mixture of two or more Aroclors.

Compatibility With Various Materials

Asphalt	C
Benzyl Cellulose	C
Cellulose Acetate	I
Chlorinated Rubber	C
Coumarone and Indene Resins	C
Dammar Resin	C
Ester Gum	C
Ethyl Cellulose	C
Manila Gum	I
Nitrocellulose	C
Paraffin	C
Phenolic Resins	Varies.*
Polystyrene Resins	C
Rosin	C
Rubber	C
Sulfur	C
Vinyl Resins	C

C — indicates compatibility to a degree sufficient to be of value.

I — indicates incompatibility.

* Not compatible in final stage.

Ethyl Cellulose

The Aroclors are very compatible with ethyl cellulose, the liquids imparting great flexibility and the resinous products great hardness. 75 parts by weight of Aroclor 1242 with 100 parts of ethyl cellulose produces great flexibility and just a slight tackiness. Aroclor 5460 in the same proportion produces a very hard and somewhat brittle composition. Aroclor 4465 produces hard films which are not brittle at ordinary temperature.

For coatings of high gloss and exceptional weathering qualities to be applied to rigid surfaces, compositions containing equal parts by weight of Aroclor 5460 and ethyl cellulose are suggested. If greater flexibility is required, one of the softer Aroclors should be used, either alone or as a replacement for part of the Aroclor 5460 and the proportion of Aroclor should be decreased.

A typical formula is as follows:

Ethyl Cellulose	15%
Aroclor 1260	15%
Toluene	56%
Butanol	14%
	100%

Graphic Arts

The Aroclors are used as vehicles for carrying pigments employed in glass decoration. When the decorations have been applied and the glass is fired, the Aroclors volatilize without carbonization and thus avoid discoloration of the glass. Aroclors 1254 and 4465 are used.

0476004

TOWOLDMON0032975
WATER_PCB-00017444

Aroclor 4465 is a useful resin for compounding rotogravure inks.

A mimeograph ink suitable for use on bond paper may be prepared as follows:

Aroclor 4465	40%
Lubricating Oil (SUV 1200 @ 100°F)	35%
Paraffin Oil (SUV 76 @ 100°F)	20%
Carbon Black	4%
Oil Soluble Dye	1%

Aroclor 4465 may also be used in the preparation of imitation gold leaf. A thin coating of the Aroclor is applied hot to one side of paper. While it is still hot, bronze powder is spread upon the coating. The bronze powder adheres to the Aroclor completely covering the paper. This product is used in making the "gold leaf" letters on books, etc. The paper treated with Aroclor and bronze powder is placed upon the book binding. A hot die is pressed upon it. The Aroclor softens and sticks the bronze to the binding and forms a coating over it to protect it from tarnishing.

Impregnation

The Aroclors may be used to impregnate cloth, paper, wood or asbestos in order to impart moisture and gas resistance, adhesion, insulating properties, alkali or other chemical resistance, flame resistance, or lubricating qualities. For this type of work they are used in combinations with other materials such as waxes, inorganic pigments, asphalt, tars, aluminum stearate, sulphur, etc., in order to obtain exactly the physical characteristics desired for the specific purpose. Aroclors 1254, 4465 and 5460, or the corresponding dark-colored products, are suggested as most applicable.

Moisture Proofing

For use as moisture proof coatings the Aroclors are best combined with waxes, such as paraffin or carnauba, oils such as mineral oil, and resins such as ester gum or other synthetic resins. The simplest compositions contain only Aroclor and paraffin. A moisture proofing compound composed of 96% (by weight) of Aroclor 5460 and 4% of paraffin (melting point 54°C) has an ASTM softening point of about 82°C and is very efficient. Substituting Aroclor 4465 for Aroclor 5460 produces a compound with a softening point of about 58°C.

Softening point and viscosity when melted may be further decreased by using mixtures of Aroclors. For example, a composition containing 40% of Aroclor 1260, 56% of Aroclor 5460 and 4% of paraffin will be very soft at ordinary temperatures. Increased proportions of paraffin will also produce softer compounds.

Mold Lubricants

Because of their inertness and low volatility, the Aroclors are excellent mold lubricants. As an example — the addition of 1% of Aroclor 1242 or 5460 to a vinyl formal resin produces great improvement in case of molding operation as well as in the appearance of the molded pieces. The molded pieces slip easily from the mold and possess extremely high water resistance and good dielectric strength. An excess does not retard hardening action.

The Aroclors are equally applicable to other molding compositions, the particular one to be selected and the method of use being governed, of course, by the molding material and the conditions of operation.

0476005

TOWOLDMON0032976
WATER_PCB-00017445

DIAGRAMS SHOWING PRACTICAL COMPOSITION

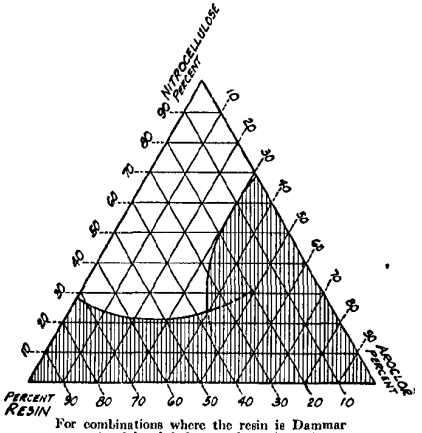

For combinations where the resin is Dammar or a resin of the phthalic anhydride-glycerol type and where the Aroclor is Aroclor 1262.*

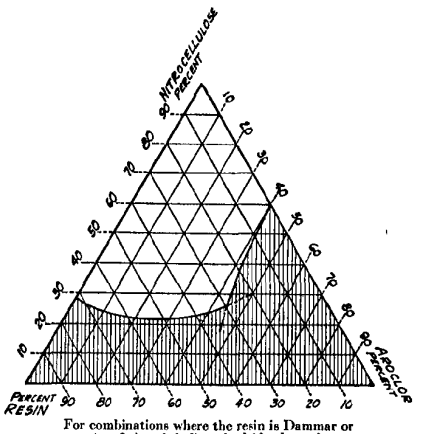

For combinations where the resin is Dammar or a resin of the phthalic anhydride-glycerol type and where the Aroclor is Aroclor 1254.

*Aroclor 1260 may be substituted without material change.

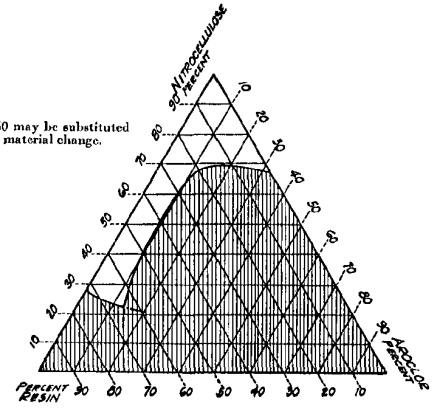

For combinations where the resin is Ester Gum or Amberol and where the Aroclor is Aroclor 1254 or Aroclor 1262.

0476006

TOWOLDMON0032977
WATER_PCB-00017446

)F LACQUERS USING AROCLORS 1254 AND 1262

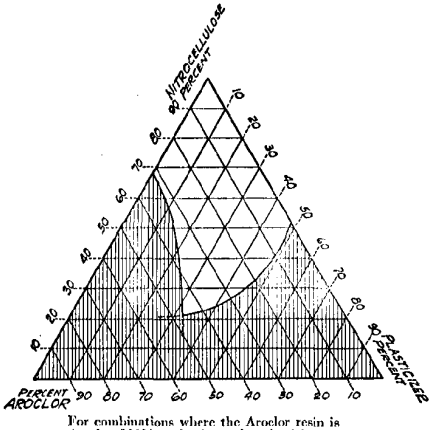

For combinations where the Aroclor resin is Aroclor 1262* and where the plasticizer is Dibutyl Phthalate.

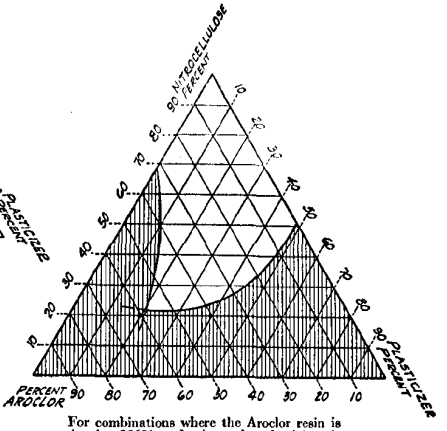

For combinations where the Aroclor resin is Aroclor 1262* and where the plasticizer is Tricresyl Phosphate.

In the trilinear diagrams the compositions, represented by any point in the unshaded areas, are those which produce homogeneous lacquer films. On the other hand compositions represented by points in the shaded areas produce impractical, segregated, brittle or soft films. For detailed information as to the derivation and use of these diagrams reference is made to the following articles:

Jenkins & Foster, "Compatibility Relationships of the Aroclors in Nitrocellulose Lacquers," Ind. Eng. Chem. *23*, 1362 (1931).

Hofmann & Reid, "Graphical Methods in Lacquer Technology," Ind. Eng. Chem. *20*, 431 (1928); "Formulation of Nitrocellulose Lacquers," Ind. Eng. Chem. *20*, 687 (1928).

0476007

TOWOLDMON0032978
WATER_PCB-00017447

Nitrocellulose Coatings

The Aroclors function both as plasticizers and resins and may be used alone with the nitrocellulose or in combinations with other plasticizers or resins. They impart weather resistance, luster, adhesion and decreased burning rate. Their excellent electrical characteristics (high dielectric constant and resistivity and low power factor) and their property of retarding the passage of moisture and gases through nitrocellulose films make the Aroclors of special value in coatings for electrical insulating materials.

The accompanying trilinear diagrams show the practical compatibility limits of Aroclors 1254 and 1262 when used in conjunction with some other resins and plasticizers. Aroclor 1260 gives values almost the same as those shown for 1262. The less viscous Aroclors have greater and the more resinous Aroclors less compatibility than for those shown. (See trilinear diagrams on pages 16 and 17.)

To illustrate the differences possible to obtain by changes in formulation, three formulas are given below. All have excellent durability but the third is much softer and more flexible than the other two. Only the solids contents are given.

The amounts tabulated are parts by weight.

Aroclor Lacquers

	No. 1	No. 2	No. 3
½ second Nitrocellulose (dry)	100	100	100
Dammar resin	80	—	—
Ester Gum	—	80	—
Aroclor 1260	20-39	20	80-70
Dibutyl Phthalate	20- 0	20	—
Tricresyl Phosphate	—	—	39-70

No. 1 and No. 2 have excellent sanding and polishing qualities. No. 3 is very flexible but too soft for sanding.

Where extremely high flexibility is desired, as for example in lacquers for high tension automotive cables, the following composition is suggested: 15 — 20 sec. R. S.

Nitrocellulose..... 8 parts by weight
Tricresyl Phosphate.....10 parts by weight
Aroclor 1242..... 7 parts by weight

Pigment

Aroclor 1270 is a hard, white crystalline product of high melting point, insoluble in most solvents, resistant to chemicals and to oxidation. When ground to a fine powder it makes an excellent organic pigment for use with the various plastics. It may be used alone or with conventional pigments.

Paints and Varnishes

The Aroclors are soluble in paint and varnish oils and impart properties corresponding to the physical character of the particular Aroclor. The hard resinous Aroclors tend to give increased hardness to the films while the viscous resins impart flexibility.

The Aroclors do not react chemically with oils, hence there is no advantage in heating together in making a varnish. They are best added as a "chill back" or as a cold cut in the thinning operation. As far as incorporation of the Aroclors is concerned, the only reason for heating is to make the Aroclors liquid so that they can be readily mixed with the oils.

0476008

TOWOLDMON0032979
WATER_PCB-00017448

Aroclors 4465 and 5460 will produce paints that are very quick drying and yet have excellent durability. The weight of Aroclor used should be from 30% to 50% of the weight of the oils.

Aroclor 1260 is best for short oil varnishes that are required at the same time to be flexible. The Aroclor may be considered to play the same role as oil, with the difference that it does not oxidize and lose its flexibility on exposure. Resins of the alkyd, phenolic or ester gum type, or a harder Aroclor such as 5460, may be used in making varnish formulations. It is suggested that for two parts by weight of oil, one part of Aroclor 1260 and one part of other resin be used. These proportions can be varied as required. The Aroclors impart water and alkali resistance and in these qualities enhance the value of the other resins used in the varnish.

Rubber and Rubber Substitutes

The Aroclors when in a liquid condition have a solvent action on rubber. Aroclors 1254 and 1260 are milled into rubber in order to impart permanent tackiness and adhesion. A small amount of Aroclor 1260 added to hard rubber acts as a plasticizer and reduces the brittleness.

Aroclor 1270, being a hard crystalline material of high melting point, can be ground to a powder and then milled into rubber. The milling temperature being below the melting point of the Aroclor, the latter is dispersed through the mass of rubber and acts as an efficient flame reducer. This same procedure can be used with the so-called synthetic rubbers (such as neoprene) to impart fireproofness. From 5% to 25% of Aroclor 1270 based on the weight of the plastic is required.

Aroclor 1262 is recommended as a plasticizer for crepe rubber resin in paint compositions. Used in concentrations of 5% to 50%, based on the weight of the rubber resin, it increases the gloss and alkali resistance of the film without detracting from its adhesiveness toward steel.

Chlorinated Rubber Finishes

Aroclors 1242, 1254 and 1260 are recommended as plasticizers for chlorinated rubber. They give tough flexible compositions and may be used alone or together with the resins and oils commonly employed in chlorinated rubber formulations. From 40 to 60 parts to each 100 parts by weight of chlorinated rubber is suggested. The Aroclors are especially valuable as finishes for alkaline surfaces such as concrete, brick, stucco, etc., and for acid and alkali resistant coatings.

Vinyl Resins

The Aroclors are compatible with all the vinyl resins. The properties imparted depend upon the particular Aroclor and the vinyl resin used. The selection of the correct Aroclor for a particular use can usually be made by consideration of the physical properties of the Aroclor series.

0476009

TOWOLDMON0032980
WATER_PCB-00017449

SANTOWAX

A high melting point, yellow, waxy solid, having a density greater than water.

Density @ 25°C	1.097 gm./cc.

Solidification — Temperature (uncorrected):

Primary hold point	140°C (284°F)
Secondary hold point	56°C (133°F)

Distillation Range (uncorrected):

First drop	265°C (689°F)
95% point	402°C (756°F)

Solubility	Grams Santowax per 100 ml. of solvent	
Solvent	25°C	75°C
95% Alcohol	0.03	1.3
Benzene	5.00	34.0

Suggested Uses for Santowax

Polishes and Waxes

For compounding where a high melting wax of excellent stability is desired.

Plasticizer

As a plasticizer in synthetic resin finishes and for resin and plastic materials.

Rubber

For the prevention of sun checking of rubber.

OTHER PRODUCTS OF OUR PHOSPHATE DIVISION

Phosphorus
Phosphoric Acid
Tetra Phosphoric Acid (Phospholeum)
Phosphorus Pentoxide
Mono Sodium Phosphate
Di Sodium Phosphate
Tri Sodium Phosphate
Acid Sodium Pyrophosphate
Tetra Sodium Pyrophosphate
Tetra Potassium Pyrophosphate
Calcium Phosphates (Mono-, Di-, Tri-)
Ammonium Phosphates (Mono-, Di-)
Phosphoric Acid Paste
Wetting Agents

0476010

TOWOLDMON0032981
WATER_PCB-00017450

NOTICE

The information contained in this booklet is to our best knowledge true and accurate, but all recommendations or suggestions are made without guarantee, since the conditions of use are beyond our control. Monsanto Chemical Company disclaims any liability incurred in connection with the use of these data or suggestions.

Furthermore, nothing contained herein shall be construed as a recommendation to use any product in conflict with existing patents covering any material or its use.

0476011

TOWOLDMON0032982
WATER_PCB-00017451