

Wire brush to remove dirt and loose particles

Wire brush to remove dirt and loose particles

move old paint with gasoline blow torch and steel scraper, and wire brush the surface. Then proceed as per above directions for new surfaces. (We do not recommend the use of a paint remover containing wax, on concrete, cement, stucco, brick or stone, because subsequent coatings will not adhere.)

METAL WORK.—Where it is desired to coat exposed metal (window frames, cornices, down spouts, etc.) with Suncolor Liquid Cement Coating, the first coat should be equal parts of Gildren Suncolor Mixing Liquid and Gildren Suncolor Liquid Cement Coating of shade selected. After 24 to 36 hours, or when dry, apply a second coat of Suncolor Liquid Cement Coating, shade selected, without retinting. In case where a light color is used, the first coat may be necessary to cover dark metal.

When coating zinc or galvanized iron, wash surface with one part muriatic acid and four parts water. This produces murate of zinc upon the surface to which plain zinc materials adhere much better than on the hands by dipping them in lard oil and rubbing it into the skin, then partially wiping off, then applying the diluted muriatic acid to the metal by means of a cloth or brush moistened with the solution. It should be wiped dry immediately after application and followed by a first coat composed of equal parts of Stoddard's Liquid Cement Coating and Stetson's Mixing Liquid. When dry apply a second coat of Stoddard's Liquid Cement Coating, shade selected, without redrawing.

WOODWORK—When it is desired to coat exposed window frames and other outside woodwork with Stuccolor Liquid Cement Coating, first shingle all knots and sappy places and then prime with equal parts of Stuccolor Mixing Liquid. Allow 24 hours to 36 hours, or until dry, then apply second coat of Stuccolor Liquid Cement Coating as it comes from the package with a flat tinning or trowling.

STUCCOLORTM MIXING LIQUID



HIDDEN Stucco Mixing Liquid is a light colored, transparent drying liquid which contains no linseed oil. It is, however, of about the same gravity as linseed oil and works easily under the brush. When spread in an even, thin layer it dries in about 18 hours, forming a tough, elastic film.

It is obvious that thinning vehicles such as turpentine or benzene are wholly unsuited for use where Glidden Silecolor Mixing Liquid is specified.

Stuccoair Mixing Liquid is in the nature of a prepared Spar Oil, and is especially adapted for exterior use on cement, concrete, stucco, brick, stone and unglazed tile surfaces.

Because of its high acid point it is not so readily saponified (converted into soap) by the alkali of the cement as linseed oil; hence its superiority as a painting vehicle for the purposes mentioned.

Suicolor Mixing Liquid is used in conjunction with Suicolor Liquid Cement Coatings as a thinning vehicle where its need is indicated in above directions.

COVERING PROPERTIES OF GLIDEMEN
STUCOLOR LIQUID CEMENT COATING

Since Liquid Cement Coating is used on concrete, cement, stucco, unglazed tile, brick or stone with coverage from 1½ to 250 square feet per gallon (U.S. Measure) and 196 to 208 square feet per gallon (Imperial Measure), one coat, depending on the density and nature of the surface. When used on metal or other surfaces of the same texture, also over old painted surfaces, the covering capacity is about 1½ to 3 per sq. ft. (Metric).

Children Concrete Patching Compound contains about 1% of calcium hydroxide to neutralize the acid.

CONCRETE PATCHING COMPOUND.



LIDDED Concrete Patching Compound is used as a leveling material to fill depressions or imperfections in the general surface of concrete due to bulging of forms, air holes, etc., and to fill irregular cracks so as to make a smooth surface on which to apply Stuccolor Liquid Cement Coatings.


This material is a heavy dense mass for use with a putty knife or trowel. It can also be used for brush work when reduced with benzine to the consistency of heavy cream.

There is no other product on the market which answers the purpose of Chidden Concrete Patching Compound. Laying a new concrete patch is only a makeshift, as the majority of these patches break off, owing to the fact that they establish no bond to the old surface.

Glidden Concrete Patching Compound applied as directed, makes a perfect bond and can be so quickly smoothed to a level surface as to make it an inexpensive method of obtaining a uniform level surface upon either walls or floors.



GLD 041865

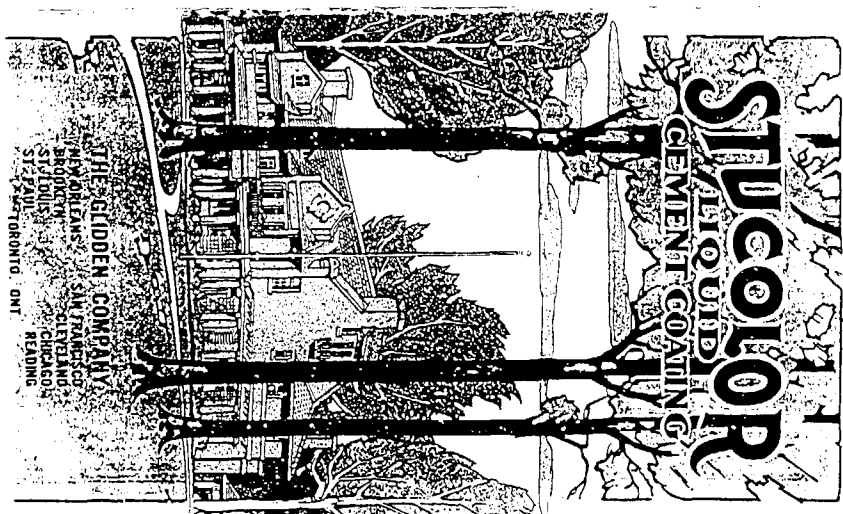

STUCOLOR




LIDDEN Stucolor Liquid Cement Coating is used for dampproofing and rendering uniform the color of exterior and interior surfaces of concrete, cement, stucco, unglazed tile, brick or stone, without changing the surface texture, producing a pleasing, decorative effect. It is composed of a modified inert pigment, incorporated with a vehicle that is extremely durable and water-resisting. The coloring matter is chemically pure.

Stucolor Liquid Cement Coating dries with an eggshell or semi-gloss finish which "weathers" within about ninety days to a cement or stone texture.

Where a porcelain surface, resembling glazed tile, is desired, apply one or two coats of Glidden White Cement Enamel over two coats of Glidden Stucolor Liquid Cement Coating (White).

DIRECTIONS

WHERE THE WEATHER has been rainy or damp for a continued period, the surface usually absorbs a certain amount of moisture; therefore, before commencing work be sure that the surface has had plenty of time to thoroughly dry out. To insure best results do not apply Stucolor Liquid Cement Coating over a surface containing moisture or frost. Never apply at a lower temperature than 50° F. and then only under good drying conditions. When applied at a temperature below 60° F. a longer drying time must be allowed for each coat.



No. 22



No. 26



No. 20



No. 5



No. 1



Also made in White, which can be tinted as desired



No. 17



No. 24



No. 13



No. 1



Also made in White, which can be tinted as desired



Also made in White, which can be tinted as desired

GLD 041866

STUCOLOR

On opening the package pour off about half the liquid and thoroughly mix up the pigment with a paddle. Slowly add, while constantly stirring, a little of the liquid from time to time, until all the liquid has been returned and thoroughly mixed.

A thorough and even mixing of the pigment and the liquid is essential. The material should be stirred occasionally while using to prevent settling and to insure uniformity.

NOTE—In some cases the alkali in concrete or cement is especially active and where such a condition exists, we recommend a wash coat composed of a solution of Zinc Sulphate and water. This solution is made by dissolving the sulphate in the proportion of one pound of Zinc Sulphate to one gallon of water. Brush the surface thoroughly with this mixture before applying the first or priming coat of Stucolor Liquid Cement Coating.

New Surfaces of Concrete, Cement, Stucco, Brick, Stone and Unglazed Tile (Exterior and Interior) Surface to be thoroughly dry, well seasoned and free from dust and loose foreign matter.

First Coat—To each gallon of Glidden Stucolor Liquid Cement Coating, of shade selected, thoroughly stirred, add one pint of Stucolor Mixing Liquid. The first coat is a soak coat, and is to be applied liberally in order to thoroughly penetrate the surface. Work into the pores of the surface, spreading the material uniformly in a thin film or coat.

Allow not less than 24 hours for drying—preferably 48 hours or as long an interval as can be given before applying the finishing coat. Apply second or finishing coat just as the material comes from the package (after thoroughly stirring to insure complete incorporation, as directed above) brushing it out evenly and uniformly over the surface.