MD-3-A

PACKAGE TICKET (DRY AND PASTE ONLY)

CODE K0906 LOT 35718

NET WT/PKG	NO. PKG	PACK. WGT	LOCATION	PO
2533	1		T-196	
2514	1		T-136	
	STUMP	LUMN 5077		

TOTAL NET WT. 5047 PKG. N-CODE —

PROD. SPVR.	DATE	WHSE. OPER.
WG	5/14	

N34572

DUP050104464

25

CG 04 CODE KO-906-D PKG. ____

MAY-8 3578

EST. WGT. 1377 LBS.

MAY 8 1980

TOTAL WEIGHT 5077# (Req. ____)

PROCESSING INSTRUCTIONS: BATCH UNIT

PROCESSES	APPROVED BY
KO-906-D (C)	EWK 1/24/78
	DCG 1/26/78
TYPED BY	
rj 3/6/78	

MAKING NOTES

REMARKS

NAME: KROLOR® ORANGE R NON-BLEEDING

INSTRUCTIONS –PRESSING– RECORD

VAT	297					
DATE	5-9-80					
TIME	2:15 P					
RELEASED BY	C. [illegible]					
PRESS	2	22	23	(24)	25	
NO. OF CAKES	46	46	46	52	48	

PRESS with AGITATION
WASH TO 2000 OHMS with 135-145°F water
TEST AFTER 3 HOURS
LOAD on 6 cars

PRESSLOAD #	1ST	2ND	3RD	4TH	5TH
STARTED	3:30				
CAKES USED	240				
WATER ON	2:00 AM				
HRS. WASHED	6				
OHMS	2800				
HRS. WASHED					
OHMS					
HRS. WASHED					
OHMS					
CAKE CONDITION					
NO. CARS LOADED	7				
EXPLAIN LOSSES					

SAMPLES 8 oz Jar
DELIVER TO CTI for color

SAMPLED BY RELEASED BY

–DRYING–

DRY 24 HOURS AT 180 °F

LUMP: – OK – WET – SALTS – CONTAMINATED

ADDITIONAL DRYING HOURS REQUIRED

NO. DRUMS 15

SAMPLES
DELIVER TO

NO. CARS PULLED LUMP WGT. 5077

SAMPLED BY RELEASED BY

–GRINDING–

3/32

MILL 938 HSP ~~1/8~~" RP SCREEN 3500 RPM
MAX. TEMP. 170 °F

SCREEN RPM
MAX. TEMP. °F

EXPLAIN LOSSES

SAMPLE / WITHOUT MIXING
SAMPLES 1 Env + 1 Pt can
DELIVER TO C T L

DATE MIXED

SAMPLED BY RELEASED BY

DUP050104465

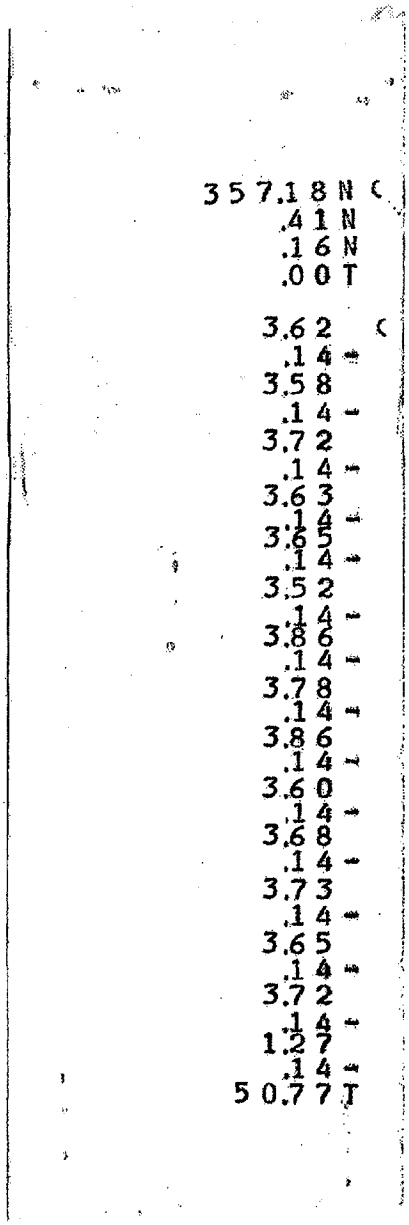
357.18 N
.41 N
.16 N
.00 T
3.62
.14
3.58
.14
3.72
.14
3.63
.14
3.65
.14
3.52
.14
3.86
.14
3.78
.14
3.86
.14
3.60
.14
3.68
.14
3.73
.14
3.65
.14
3.72
.14
1.27
.14
50.77 T