MD-3-A

PACKAGE TICKET (DRY AND PASTE ONLY)

CODE Ky. 788 LOT 34929

NET WT/PKG	NO. PKG	PACK. WGT	LOCATION	PO
50	70	3500		
	STUMP			

TOTAL NET WT. 3500 PKG. N-CODE 1135

PROD. SPVR.	DATE	WHSE. OPER.
[illegible]	3/20/80	

N 2656

22/240

CG 03 CODE KY-788-D PKG. ____

→ MAR 17 34929

EST. WGT. ~~960~~ 860 LBS.

OK / KP

PROCESSING INSTRUCTIONS: BATCH UNIT

22/240	PROCESSES	APPROVED BY
	KY-788-D (J)	EWK 9/22/76
		DCG 9/27/76
	TYPED BY	
	NE 2/17/77	

MAKING NOTES

REMARKS

3460

Total Wgt. ~~3560~~# Req(____)

AME: "KROLOR" YELLOW - LIGHT NON-BLEEDING

INSTRUCTIONS				-PRESSING- RECORD						
AT	240			PRESSLOAD	1ST	2ND	3RD	4TH	5TH
ATE	3-18-80 SA			STARTED	3:35 PM				
TIME	2:30 PM			CAKES USED	54				
ELEASED BY	E.M.			WATER ON	78 RPM				
RESS	22	23	24	HRS. WASHED	2 Hrs				
O. OF CAKES	46	46	46	OHMS	2000				
RESS With		AGITATION		HRS. WASHED					
ASH TO 2000		OHMS with 35-75°F water		OHMS					
EST AFTER 2		HOURS		HRS. WASHED					
OAD on 6 cars				OHMS					
				CAKE CONDITION					
				NO. CARS LOADED	6				
				EXPLAIN LOSSES					

SAMPLES 1- 8oz JAR

DELIVER TO CTL for Color

SAMPLED BY HDJ RELEASED BY

-DRYING-

Dry 12 hrs at 220 °F Then Dry 8 hrs at 160 °F

LUMP: - OK - WET - SALTS - CONTAMINATED

ADDITIONAL DRYING HOURS REQUIRED

No Drums 15

SAMPLES

DELIVER TO

NO. CARS PULLED LUMP WGT. 3565

SAMPLED BY RELEASED BY

-GRINDING-

MILL 939 HSP 3/32" RP SCREEN 3500 RPM

MAX. TEMP. 150 °F

SCREEN RPM

MAX. TEMP. °F

EXPLAIN LOSSES

SAMPLE AFTER / WITHOUT MIXING

SAMPLES 1 Env. & 1 Pt can

DELIVER TO C T L

DATE MIXED

SAMPLED BY RELEASED BY

N 26561.01

DUP050094608

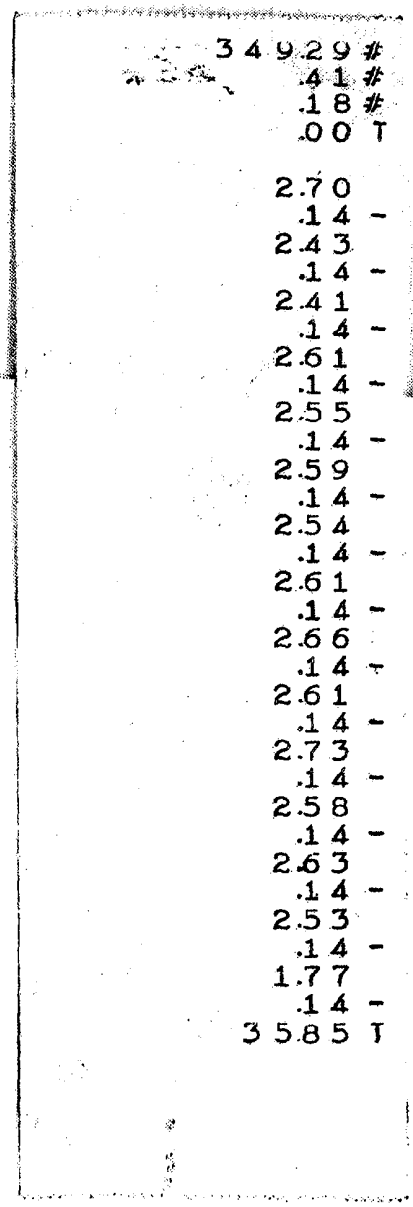

DUP050094609