MD-3-A

PACKAGE TICKET (DRY AND PASTE ONLY)

CODE Ky. 788 LOT 38093

NET WT/PKG	NO. PKG	PACK. WGT	LOCATION	PQ
1790	1	T-173		
1740	1	T-285		
	[redacted]	LUMP	3585	

TOTAL NET WT. 3530 PKG. N—CODE

PROD. SPVR.	DATE	WHSE. OPER.
[illegible]	12/5/80	

244

CG 03 CODE KY-788-D PKG. ____

→ DEC--2 80 38093

EST. WGT. 960 LBS.

OK / 18

Total Wgt 3560#

PROCESSING INSTRUCTIONS: BATCH UNIT

PROCESSES	APPROVED BY
KY-788-D (K)	EWK 9/22/76
Alternate	DCG 9/27/76
TYPED BY	
NE 2/24/76	

MAKING NOTES

REMARKS

NAME: "KROLOR" YELLOW - LIGHT

NON-BLEEDING

-PRESSING-

INSTRUCTIONS

VAT	244				
DATE	12-3-80	JM			
TIME	1:35 Am				
RELEASED BY					
PRESS	22	23	24	24	
NO. OF CAKES	46	46	46	52	

PRESS with AGITATION

WASH TO 2000 OHMS with 35-75°F water

TEST AFTER 2 HOURS

LOAD on 6 cars

TDS

SAMPLES 1- 8oz JAR

DELIVER TO CTL for color

RECORD

PRESSLOAD	1ST	2ND	3RD	4TH	5TH
STARTED	2:30 pm				
CAKES USED	5-2				
WATER ON	6 pm				
HRS. WASHED	5				
OHMS	2000				
HRS. WASHED					
OHMS					
HRS. WASHED					
OHMS					
CAKE CONDITION					
NO. CARS LOADED	7				

EXPLAIN LOSSES

SAMPLED BY 472 RELEASED BY

-DRYING-

Dry 12 hrs at 220 °F

Then Dry 8 hrs at 160 °F

m

SAMPLES

DELIVER TO

LUMP: - OK - WET - SALTS - CONTAMINATE

ADDITIONAL DRYING HOURS REQUIRED

No. Drums 15

NO. CARS PULLED 7 LUMP WGT. 3585

SAMPLED BY RELEASED BY BLL

-GRINDING-

MILL 939 HSP 3/32" RP SCREEN 3500 RPM

MAX. TEMP. 150 °F

SAMPLE WITHOUT MIXING

SAMPLES 1 Env & 1 Pt Can

DELIVER TO C T L

SCREEN RPM

MAX. TEMP. °F

EXPLAIN LOSSES

DATE MIXED

SAMPLED BY RELEASED BY

DUP050104075

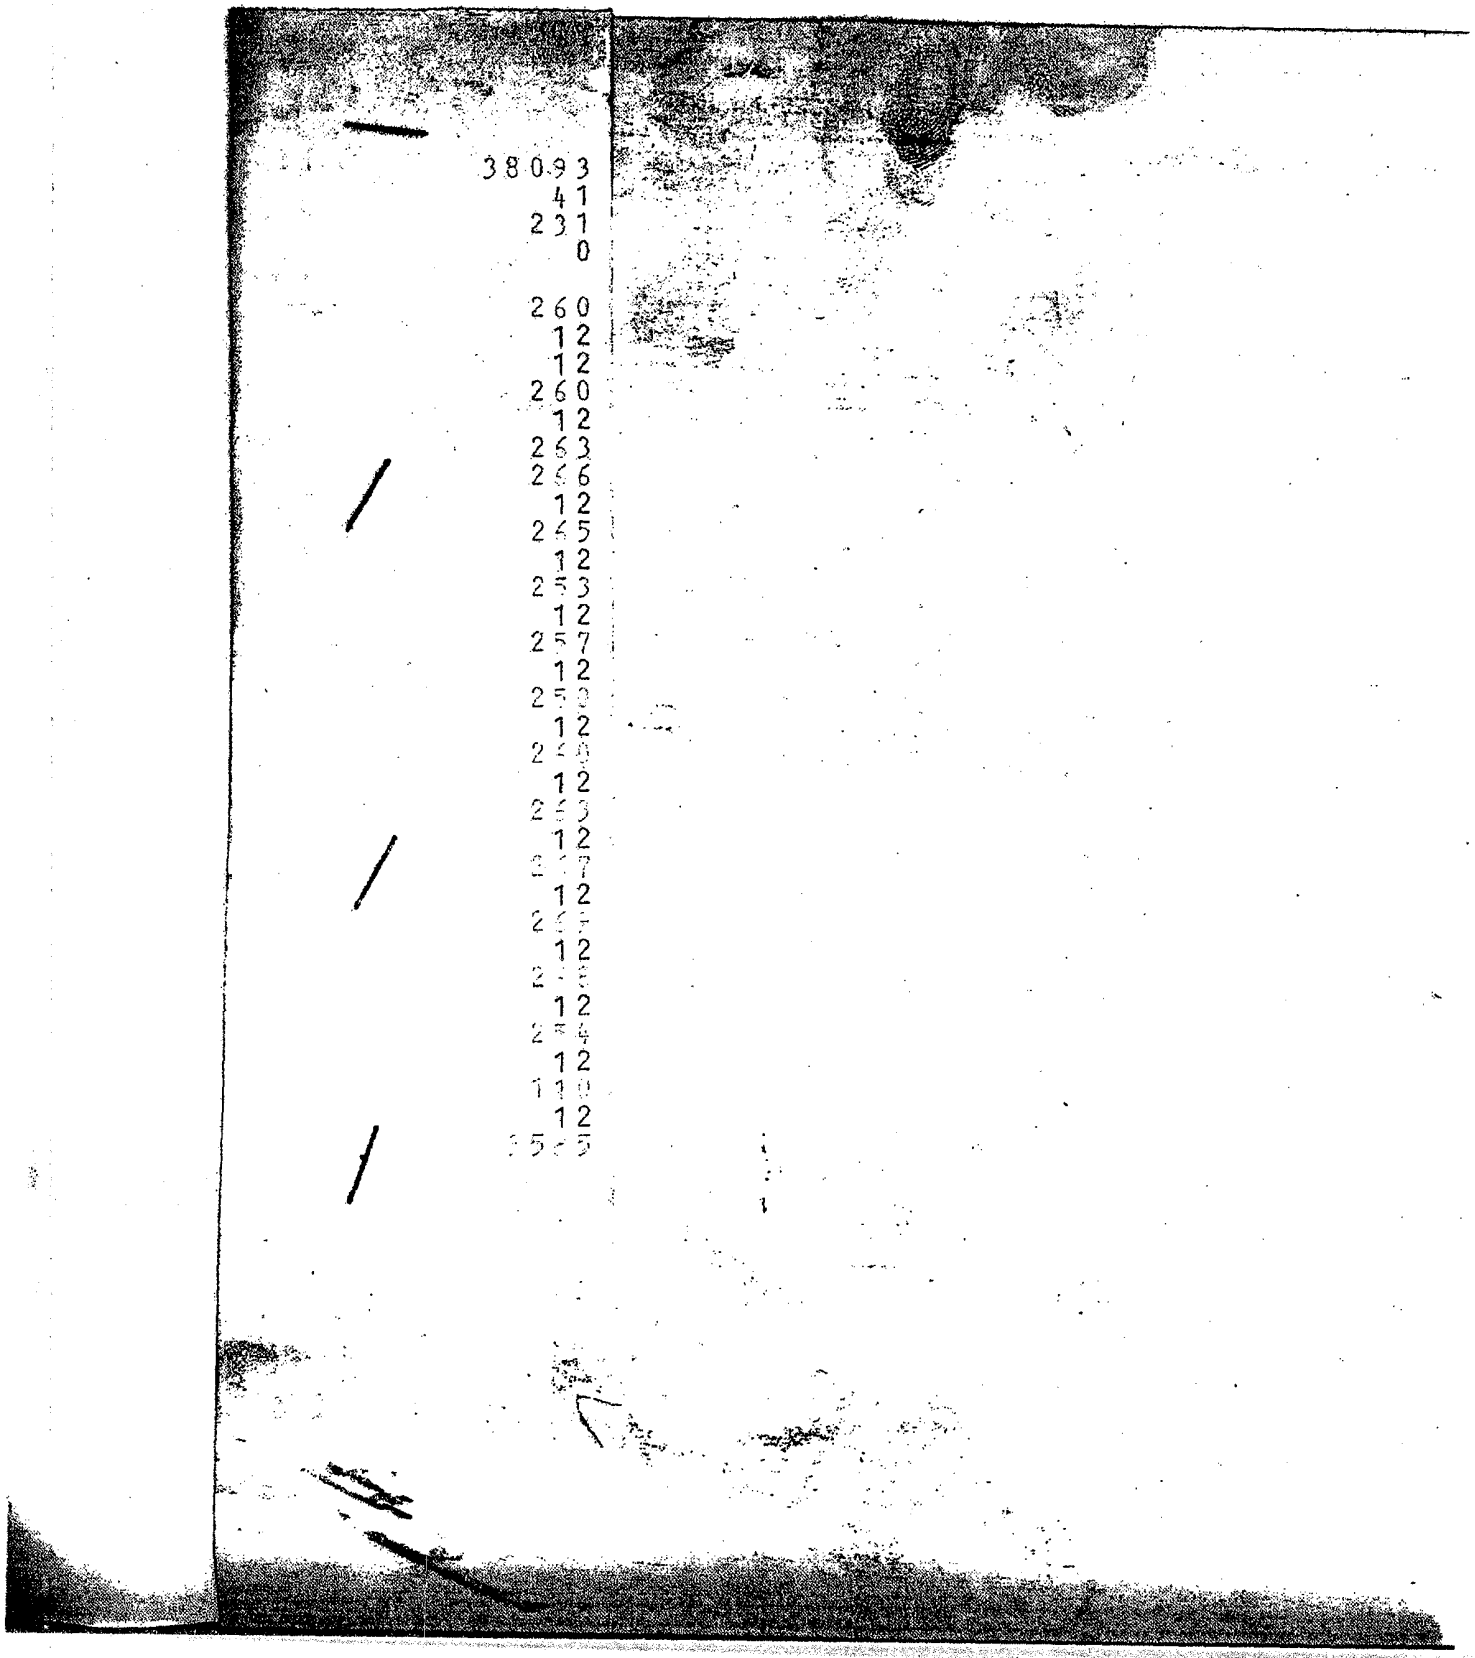
38093
41
231
0
260
12
12
260
12
263
266
12
265
12
253
12
257
12
12
12