

## TECHNICAL SPECIFICATIONS

FORM P927

CERTAIN-TEED PRODUCTS CORPORATION  
PIPE DIVISION

## SPECIFICATIONS CLASSIFICATION:

Standard Purchasing Specification

T.C.O. REF. NO.

11

SPECIFICATION NO:

532

PAGE NO.:

1

SUPERSEDES:

May 26, 1969

DATE OF ISSUE:

APR 27 1973

## DESCRIPTION:

Steel Mandrels

**GENERAL:** This specification has been devised to define the steel mandrel requirements for use in the Mazza type manufacture of asbestos-cement pipe.

**MATERIAL:**

Type A - Cold drawn, seamless mechanical steel tubing, nominal carbon content 0.25%, unannealed, chamfered ends.

Type B - Centrifugally cast 1025 carbon steel tubing, stress relieved. O.D. (outside diameter) machined to 125 micro finish, I.D. (inside diameter) as cast, ends faced and radiused. Finish per ASA B 46.1.

Pulling Ring - Flat bar stock, 1040 or 1045 carbon steel.

Pulling Bar - Round bar stock, 1010 min. carbon steel or 1025 carbon steel.

**STRAIGHTNESS:** Maximum curvature per foot not to exceed +0.010" in sizes up to 5" and +0.015" in sizes over 5", tubing only. Cast steel mandrels shall have a T.I.R. (Total Indicator Reading) not to exceed 0.050" at center.

**MARKING:** The pulling ring of each mandrel 7.51" and larger shall be identified with the nominal outside mandrel diameter applied as follows.

Use small stainless steel manual electrode to provide numbers at least 3/4" high, raised approximately 1/8", and completed in a neat, legible manner.

Mandrels below 7.50" having smaller pulling rings are to be identified as above, except numbers shall be reduced in size according to the pulling ring "Y" dimension.

**SHIPPING INSTRUCTIONS:**

**Protective Coating** - All surfaces of each mandrel shall be lightly coated with a protective material which will prohibit the formation of rust during transportation and initial storage and yet be capable of being readily removed at the plant site.

**Packaging** - Mandrels shall be suitably packaged to prevent damage in transit and to allow for handling at the plant site by fork lift trucks.

**Delivery** - Delivery time shall be arranged by the vendor to avoid unnecessary delays at the plant site.

**STATIC BALANCE:** Each Type "B" mandrel shall be statically balanced. Mandrels of 12.00" O.D. and less shall be balanced to within 0.25 pounds. Above 12.00" O.D., the mandrels shall balance within 0.50 pounds. If the total weight is greater than one pound, it shall be divided equally between each end. Weight distribution tolerance is plus or minus 1 pound. Weights shall clear the pull bar and pull ring by minimum of 6.0 inches. Installation of the weights inside the mandrel shall not distort the outer surface of the mandrel. The recommended method is to tack weld bar stock having a width to thickness ratio of approximately 4 to 1.

CTD015079

PREPARED BY:

J.C. Taylor

APPROVED BY:

J.C. Taylor

R. D.

MFG.

SALES

I. E.

OTHERS

J.C. Taylor

J.C. Taylor

J.C. Taylor

J.C. Taylor

J.C. Taylor

## TECHNICAL SPECIFICATIONS

|                                                                                                                                                                     |                                   |                   |           |
|---------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------|-------------------|-----------|
| <br><b>CERTAIN-TEE PRODUCTS CORPORATION</b><br>PIPE DIVISION<br><b>CERTAIN-TEE</b> | SPECIFICATIONS CLASSIFICATION:    |                   |           |
|                                                                                                                                                                     | Standard Purchasing Specification |                   |           |
|                                                                                                                                                                     | T.C.O. REF. NO.                   | SPECIFICATION NO. | PAGE NO.: |
|                                                                                                                                                                     | 10                                | 532               | 2         |
| SUPERSEDES:                                                                                                                                                         |                                   | DATE OF ISSUE:    |           |
| December 26, 1968                                                                                                                                                   |                                   | May 26, 1969      |           |

## DESCRIPTION:

## Steel Mandrels

| Dimensions       |      |                |                  |                    |        |      |
|------------------|------|----------------|------------------|--------------------|--------|------|
| Mandrel O.D.     | Type | Wall Thickness | Wall Tolerance   | O.D. Tolerance     | D      | Y    |
| Up to 4.49"      | A    | 0.250"         | ± 10%            | +0.015"<br>-0.000" | 5/8"   | 5/8" |
| 4.50" to 4.99"   | A    | 0.250"         | ± 10%            | +0.015"<br>-0.000" | 5/8"   | 3/4" |
| 5.00" to 7.50"   | A    | 0.313"         | ± 10%            | ±0.015"            | 5/8"   | 3/4" |
| 7.51" to 7.99"   | A    | 0.313"         | ± 10%            | ±0.015"            | 1"     | 1"   |
| 8.00" to 8.99"   | A    | 0.313"         | ± 10%            | ±0.023"            | 1"     | 1"   |
| 9.00" to 14.50"  | B    | 0.500"         | +0.120", -0.000" | ±0.010"            | 1"     | 1"   |
| 14.51" to 16.99" | B    | 0.563"         | +0.120", -0.000" | ±0.010"            | 1"     | 1"   |
| 17.00" to 23.99" | B    | 0.625"         | +0.120", -0.000" | ±0.010"            | 1 1/2" | 1"   |
| 24.00" to 29.99" | B    | 0.800" Min. *  | +0.160", -0.000" | ±0.010"            | 1 1/2" | 1"   |

\* 1/4 inch may be removed from each side of I.D. for fabrication of pull rings and pull bars.

For Mandrel Size to be ordered, refer to General Standards Manual, Section G, Part B. Unless otherwise directed, the preferred mandrel is to be ordered.

CTD015080

|                     |              |                    |           |             |      |           |
|---------------------|--------------|--------------------|-----------|-------------|------|-----------|
| PREPARED BY:        | APPROVED BY: | R & D              | MFG.      | SALES       | I.E. | OTHERS    |
| <i>J. C. Taylor</i> | <i>OS</i>    | <i>[Signature]</i> | <i>MA</i> | <i>Leat</i> |      | <i>AB</i> |

# TECHNICAL SPECIFICATIONS



CERTAIN-TEED PRODUCTS CORPORATION  
PIPE DIVISION

## SPECIFICATIONS CLASSIFICATION:

Standard Purchasing Specification

T.C.O. REF. NO.

10

SPECIFICATION NO.

532

PAGE NO.:

3

SUPERSEDES:


December 26, 1968

DATE OF ISSUE:

May 26, 1969

## DESCRIPTION:

Steel Mandrels

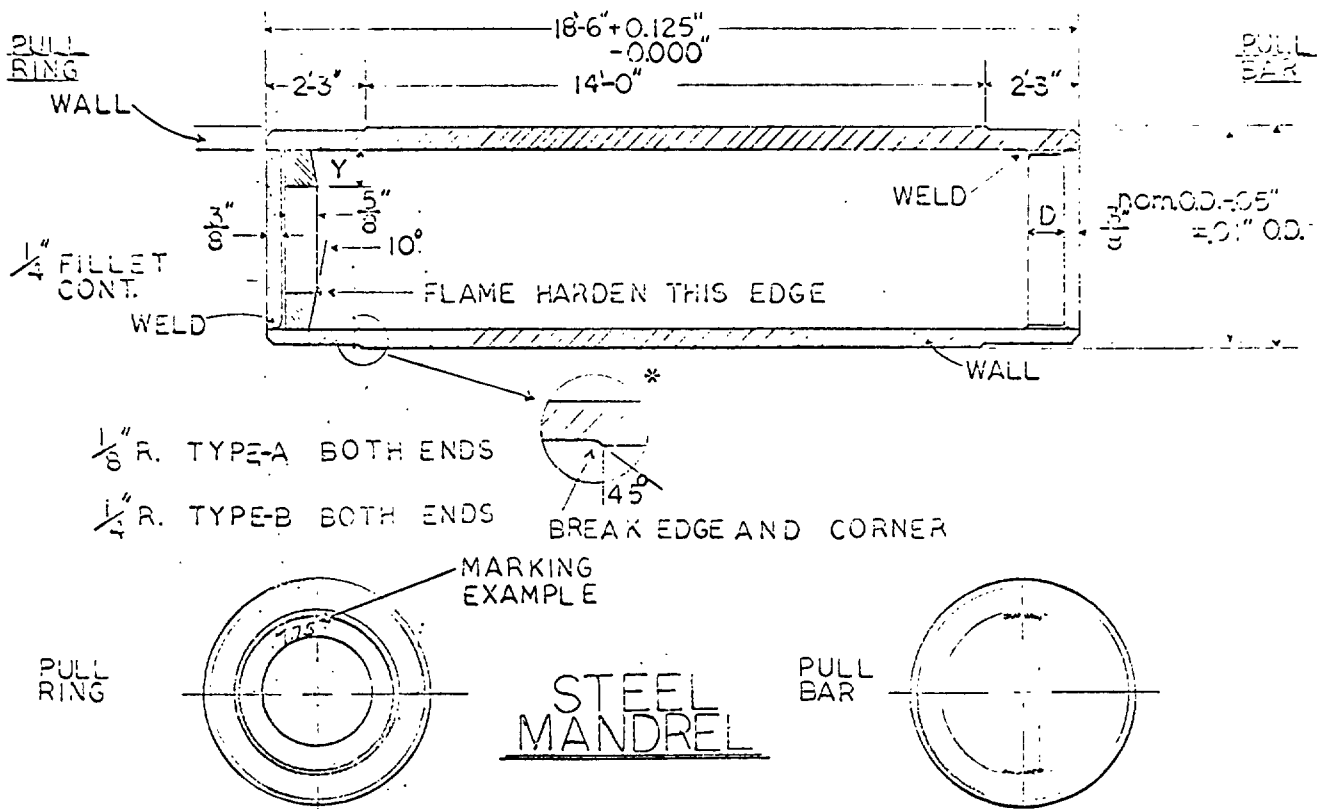

\* Or may be square shouldered.

CTD015081

PREPARED BY:

*J. C. Long*

APPROVED BY:

*J. C. Long*

R & D

MFG.

SALES

I.E.

OTHERS

*[Signature]*

*[Signature]*

*Leit*

*[Signature]*

CONFIDENTIAL DOCUMENT - NOT TO BE DISTRIBUTED TO UNAUTHORIZED PERSONNEL

## TECHNICAL SPECIFICATIONS

|                                                                                                   |                                                    |  |                   |                                   |                |  |
|---------------------------------------------------------------------------------------------------|----------------------------------------------------|--|-------------------|-----------------------------------|----------------|--|
| <br>CERTAIN-TEED | CERTAIN-TEED PRODUCTS CORPORATION<br>PIPE DIVISION |  |                   | SPECIFICATIONS CLASSIFICATION:    |                |  |
|                                                                                                   |                                                    |  |                   | Standard Purchasing Specification |                |  |
|                                                                                                   | T.C.O. REF. NO.                                    |  | SPECIFICATION NO. |                                   | PAGE NO.       |  |
|                                                                                                   | 10                                                 |  | 532               |                                   | 4              |  |
| SUPERSEDES:                                                                                       |                                                    |  |                   |                                   | DATE OF ISSUE: |  |
| November 4, 1968                                                                                  |                                                    |  |                   |                                   | May 26, 1969   |  |
| DESCRIPTION:                                                                                      |                                                    |  |                   |                                   |                |  |
| Steel Mandrels                                                                                    |                                                    |  |                   |                                   |                |  |

NOT TO BE DISTRIBUTED TO VENDORS

Distribution: As this specification represents a special purchasing situation not connected with the normal use of this type of document, the standard distribution list is expanded to include:

Director of Manufacturing and Engineering (2)  
Each Plant Engineer (1)

Additional copies of the specification may be secured from Technical Service as needed.

Approved Vendors: Purchase of mandrels will normally be accomplished through bids extended by Division Purchasing Agent.

Receiving Inspection: Plant Engineer is responsible for acceptance or rejection of mandrels purchased through this specification. Mandrels are to be delivered to plant sites complete and ready for use except for the removal of protective coating. While it is intended that mandrels are to be delivered ready for use, circumstances may require that installation of pull bar and pull ring, chamfering, and static balance be accomplished at the plant.

Special Note: Type A mandrels are available in diameters greater than 9.01" but probably with greater O.D. tolerances. Since Type A mandrels are less costly initially, this alternative should be investigated each time in the 9.01" to 14.00" O.D. range.

The machining of a radius on the mandrel ends may be prohibitive. Therefore, this requirement may be waived and the following substituted:  $1/8" \pm 1/32"$  X  $45^\circ \pm 5^\circ$  chamfer both ends.

Type B Mandrels: Type B mandrels may be made from used steel pipe providing that all the conditions as specified in this specification in reference to wall thickness, straightness, surface finish, O.D., and tolerances are strictly adhered to.

CTD015082

|                     |                 |                    |                    |                    |      |                    |
|---------------------|-----------------|--------------------|--------------------|--------------------|------|--------------------|
| PREPARED BY:        | APPROVED BY:    | R & D              | MFG.               | SALES              | I.E. | OTHERS             |
| <i>C. E. Taylor</i> | <i>J. J. K.</i> | <i>[Signature]</i> | <i>[Signature]</i> | <i>[Signature]</i> |      | <i>[Signature]</i> |

# TECHNICAL SPECIFICATIONS



CERTAIN-TEE PRODUCTS CORPORATION  
PIPE DIVISION

## SPECIFICATIONS CLASSIFICATION:

Standard Purchasing Specification

T.C.O. REF. NO.

1

SPECIFICATION NO.

532-A

PAGE NO.:

1

SUPERSEDES:

None

DATE OF ISSUE:

MAY 6 1974

## DESCRIPTION:

### STEEL MANDREL BLANKS

**GENERAL:** Steel Mandrel Blanks are used in creating steel mandrels (See Purchasing Spec. 532).

**MATERIAL:** Type A is cold drawn, seamless mechanical steel tubing, nominal carbon content 0.25%, unannealed. Type B is centrifugally cast 1025 carbon steel tubing, stress relieved, outside diameter machined to 125 micro-inch max per A.S.A. B46-1

**STRAIGHTNESS:** Type A max curvature of 0.010" per foot in sizes 5" or less and 0.015" per foot in sizes over 5".

Type B 050" max. Total Indicator Reading at center.

## SHIPPING INSTRUCTIONS:

1. Coat each mandrel lightly to prevent rust formation during transportation and initial storage. Coating must be readily removable at plant site.
2. Package mandrels to prevent transit damage and allow for fork-lift truck handling.
3. Delivery time shall be arranged by vendor to avoid unnecessary delays at plant site.

**DIMENSIONS:** 18'6"  $\begin{matrix} + 0.125" \\ - 0.000" \end{matrix}$  over all length, with square cut ends.

### TYPE A

### TYPE B

CTD015083

| Mandrel O.D.    | O.D. Tolerance                                     | Wall Thickness | Wall Tolerance | Mandrel O.D.     | O.D. Tolerance | Wall Thickness | Wall Tolerance                                     |
|-----------------|----------------------------------------------------|----------------|----------------|------------------|----------------|----------------|----------------------------------------------------|
| Up to 4.49"     | $\begin{matrix} +0.015" \\ -0.000" \end{matrix}$   | 0.250"         | $\pm 10\%$     | 9.00" to 14.50"  | $\pm 0.010"$   | 0.500"         | $\begin{matrix} + 0.120" \\ - 0.000" \end{matrix}$ |
| 4.50" to 4.99"  | $\begin{matrix} + 0.015" \\ - 0.000" \end{matrix}$ | 0.250"         | $\pm 10\%$     | 14.51" to 16.99" | $\pm 0.010"$   | 0.563"         | $\begin{matrix} + 0.120" \\ - 0.000" \end{matrix}$ |
| 5.00" to 7.50"  | $\pm 0.015"$                                       | 0.313"         | $\pm 10\%$     | 17.00" to 23.99" | $\pm 0.010"$   | 0.625"         | $\begin{matrix} + 0.120" \\ - 0.000" \end{matrix}$ |
| 7.51" to 7.99"  | $\pm 0.015"$                                       | 0.313"         | $\pm 10\%$     | 24.00" to 29.99" | $\pm 0.010"$   | 0.800"         | $\begin{matrix} + 0.160" \\ - 0.000" \end{matrix}$ |
| 8.00" to 8.99"  | $\pm 0.023"$                                       | 0.313"         | $\pm 10\%$     |                  |                |                |                                                    |
| 9.00" to 14.50" | $\pm 0.023"$                                       | 0.500"         | $\pm 10\%$     |                  |                |                |                                                    |

Receiving Inspection and resultant acceptance/rejection will be done by A/C Plant Engineer.

|                       |              |       |      |       |      |        |
|-----------------------|--------------|-------|------|-------|------|--------|
| PREPARED BY:          | APPROVED BY: | R & D | MFG. | SALES | I.E. | OTHERS |
| Leonard C. Kuykendall | [Signature]  |       |      |       |      |        |



532 A